

RESEARCH ARTICLE

Open Access

In vitro effects of hyaluronic acid on human periodontal ligament cells



Masako Fujioka-Kobayashi^{1,2}, Heinz-Dieter Müller³, Andrea Mueller⁴, Adrian Lussi³, Anton Sculean⁵, Patrick R. Schmidlin⁴ and Richard J. Miron^{3,6,7,8*}

Abstract

Background: Hyaluronic acid (HA) has been reported to have a positive effect on periodontal wound healing following nonsurgical and surgical therapy. However, to date, a few basic *in vitro* studies have been reported to investigating the potential of HA on human periodontal ligament (PDL) cell regeneration. Therefore, the aim of this study was to investigate the effect of HA on PDL cell compatibility, proliferation, and differentiation *in vitro*.

Methods: Either non-cross-linked (HA_ncl) or cross-linked (HA_cl) HA was investigated. Human PDL cells were seeded in 7 conditions as follows (1) Control tissue culture plastic (TCP) (2) dilution of HA_ncl (1:100), (3) dilution of HA_ncl (1:10), (4) HA_ncl directly coated onto TCP, (5) dilution of HA_cl (1:100), (6) dilution of HA_cl (1:10) and (7) HA_cl directly coated onto TCP. Samples were then investigated for cell viability using a live/dead assay, an inflammatory reaction using real-time PCR and ELISA for MMP2, IL-1 and cell proliferation via an MTS assay. Furthermore, the osteogenic potential of PDL cells was assessed by alkaline phosphatase (ALP) activity, collagen1 (COL1) and osteocalcin (OCN) immunostaining, alizarin red staining, and real-time PCR for genes encoding Runx2, COL1, ALP, and OCN.

Results: Both HA_ncl and HA_cl showed high PDL cell viability (greater than 90%) irrespective of the culturing conditions. Furthermore, no significant difference in both mRNA and protein levels of proinflammatory cytokines, including MMP2 and IL-1 expression was observed. Both diluted HA_ncl and HA_cl significantly increased cell numbers compared to the controlled TCP samples at 3 and 5 days. HA_ncl and HA_cl in standard cell growth media significantly decreased ALP staining, COL1 immunostaining and down-regulated early osteogenic differentiation, including Runx2, COL1, and OCN mRNA levels when compared to control samples. When osteogenic differentiation medium (ODM) was added, interestingly, the expression of early osteogenic markers increased by demonstrating higher levels of COL1 and ALP expression; especially in HA 1:10 diluted condition. Late stage osteogenic markers remained inhibited.

Conclusions: Both non-cross-linked and cross-linked HA maintained high PDL cell viability, increased proliferation, and early osteogenic differentiation. However, HA was consistently associated with a significant decrease in late osteogenic differentiation of primary human PDL cells. Future *in vitro* and animal research is necessary to further characterize the effect of HA on periodontal regeneration.

Keywords: Hyaluronic acid, Hyaluronan, Periodontal regeneration, Soft tissue regeneration, Connective tissue regeneration

* Correspondence: rmiron@nova.edu

³Department of Preventive, Restorative and Pediatric Dentistry, School of Dental Medicine, University of Bern, Bern, Switzerland

⁶Department of Periodontology, College of Dental Medicine, Nova Southeastern University, Fort Lauderdale, FL, USA

Full list of author information is available at the end of the article



Background

Hyaluronic acid (HA; also termed hyaluronan or hyaluronate) is an anionic, nonsulfated glycosaminoglycan and considered an optimal biomaterial for tissue engineering, given its broad expression in a connective tissue as well as the significant role it plays during organogenesis, cell migration and development in general [1–4]. Non-cross-linked HA (HA_ncl) is biodegradable, biocompatible, bioresorbable and also well known to improve tissue lubrication in cartilage, guides cell growth and differentiation, and speeds the healing and repair of chronic wounds [5]. Cross-linked HA (HA_cl) has also been utilized for tissue engineering as a scaffold to further improve the overall mechanical performance of the scaffolding material and rigidity supporting the growth of various cells [6–9]. HA has been widely used for patients with knee osteoarthritis due to its ability to provide cartilage tissue integrity [10, 11]. Furthermore, in the oral maxillofacial area, HA injections have been used as a treatment option to manage symptoms of temporomandibular joint disorders [12, 13]. More recently, HA has also been utilized for applications for aesthetic purposes in the oral facial regions primarily to reduce or to eliminate facial creases, interdental papilla loss, and various other abnormalities [8, 14, 15].

Due to the growing use of HA in dentistry, HA has also been hypothesized to have influences on periodontal regeneration [16]. The management of periodontal defects is mainly a result of the cooperative treatment of three unique tissues which comprises the periodontium, the periodontal ligament and the cementum and alveolar bone. [6]. HA is an essential component of the periodontal ligament matrix and has been shown to play various important roles in cell adhesion, migration and differentiation mediated by various HA binding proteins and cell-surface receptors such as CD44 [17]. This CD44 antigen is expressed in periodontal tissues and HA-CD44 interaction has been associated with periodontal ligament (PDL) cell proliferation and mineralization activities [18].

Furthermore, other advantages of HA include its anti-inflammatory activity promoting soft and hard tissue healing response, which may be of significant interest during periodontal regeneration [19]. Based on these assumptions, exogenous HA has already been tested in patients with chronic periodontitis in several clinical studies reporting the beneficial effects of HA on reducing bleeding of probing scores and probing depths [2, 20–23]. However, to date, the in vitro effect of HA on periodontal ligament activity has not been clearly investigated.

Therefore, the aim of the present study was to investigate the effects of HA_ncl and HA_cl on PDL cells by stimulating cells under 3 different conditions of either diluted samples with HA (co-existing at 2 concentrations of 1:10 and 1:100 dilutions) or directly by precoating HA

onto tissue culture plastic. The PDL cells cultured with either HA_ncl or HA_cl were assessed for cell viability at 24 h, inflammatory cytokines expression at 1 day, cell proliferation at 1, 3 and 5 days and osteogenic differentiation marker expression at 7 days and 14 days.

Methods

Reagents and cell culture

HA was kindly provided by Regedent (Zürich, Switzerland) utilizing 2 compositions of HA including non-cross-linked native HA (hyaDENT, BioScience GmbH, Dümmer, Germany) as well as a cross-linked HA (hyaDENT BG, BioScience GmbH). HyaDENT (HA_ncl) contains a formulation of 14.0 mg/mL of sodium hyaluronate (synthesized by bacterial fermentation in *Streptococcus* [24], non-cross-linked), and hyaDENT BG (HA_cl) contains 2.0 mg/mL of sodium hyaluronate and 16.0 mg/mL of sodium hyaluronate cross-linked with butanediol diglycidyl ether (BDDE). The seven groups were tested as follows; (1) control tissue culture plastic (TCP) (2) dilution of HA_ncl (1:100), (3) dilution of HA_ncl (1:10), (4) HA_ncl directly coated onto TCP, (5) dilution of HA_cl (1:100), (6) dilution of HA_cl (1:10) and (7) HA_cl directly coated onto TCP based on our previous report [25]. In short, HA was diluted in standard cell culture growth medium consisting of DMEM (Gibco), 10% fetal Bovine serum (FBS; Gibco) and 1% antibiotics (Gibco). The 100 µl of HA were directly pre-coated in per 24-culture well and then the amount of HA was adjusted the same between 1:10 dilution and coating conditions per well in the end post cell seeding.

The primary human PDL cells were obtained from the middle third portion of each tooth extracted from three healthy patients, with no signs of periodontal disease extracted for orthodontic as previously described [26, 27]. Using discarded tissue for research purposes was approved by the Ethical commission of the Canton Bern without an IRB. All patients gave their consent. Briefly, PDL tissues isolated from the center of the root surface with a surgical scalpel were minced, transferred to TCP with media changes every 2 or 3 days. The PDL cells were detached from TCP using 0.25% EDTA-Trypsin (Gibco, Life Technologies, Carlsbad, CA, USA) prior to reaching confluency. Cells used for experimental seeding were from passages 4–6. Cells were cultured in a humidified atmosphere at 37 °C in the cell growth medium. For in vitro experiments, cells were seeded with HA contained within cell culture media at a density of 10,000 cells in 24 well culture plates for cell proliferation experiments and 50,000 cells per well in 24 well dishes for real-time PCR, ELISA, ALP assay, immunostaining and alizarin red experiments. For experiments lasting longer than 5 days, the medium was replaced twice weekly.

Cell viability

Primary human PDL cells were seeded in at a density of 12,500 cells / cm² with (1) control TCP (2) dilution of HA_ncl (1:100), (3) dilution of HA_ncl (1:10), (4) HA_ncl directly coated, (5) dilution of HA_cl (1:100), (6) dilution of HA_cl (1:10) and (7) HA_cl directly coated, on chamber slides (Sigma, St. Louis, MO, USA). At 1 day post cell seeding, cells were evaluated using a live-dead staining assay according to the manufacturer's protocol (Enzo Life Sciences AG; Lausen, Switzerland) as previously described [28]. Fluorescent images were quantified with a fluorescent microscope (OLYMPUS BX51, Tokyo, Japan).

Proliferation assay

PDL cells were seeded in 24-well plates at a density of 10,000 cells per well in a 24 well culture plate with the same conditions, (1) control TCP (2) dilution of HA_ncl (1:100), (3) dilution of HA_ncl (1:10), (4) HA_ncl directly coated onto TCP, (5) dilution of HA_cl (1:100), (6) dilution of HA_cl (1:10) and (7) HA_cl directly coated onto TCP. Cells were quantified using a fluorescent MTS assay (Promega, Madison, WI, USA) at 1, 3 and 5 days for cell proliferation as previously described [29]. At desired time points, cells were washed with phosphate-buffered saline (PBS, pH = 7.4) and quantified using a ELx808 Absorbance Reader (BIO-TEK, Winooski, VT, USA).

Real-time PCR analysis

PDL cells were first cultured for 1 day with HA in order to investigate its inflammatory marker expressions, including matrix metalloproteinase-2 (MMP2) and interleukin-1 (IL-1). Moreover, in order to investigate the effects of HA on the osteogenic differentiation, the cells were stimulated for 7 days within each concentration of HA with and without osteogenic differentiation medium (ODM), which consisted of DMEM supplemented with 10% FBS, 1% antibiotics, 50 µg/mL ascorbic acid (Sigma) and 10 mM β-glycerophosphate (Sigma) to promote osteogenic differentiation as previously described [30]. The RNA expressions of runt-related transcription factor 2 (Runx2), collagen1a2 (COL1a2), alkaline phosphatase (ALP), osteocalcin (OCN) in either condition were measured. The total RNA was harvested using High Pure RNA Isolation Kit (Roche, Basel, Switzerland). Primer and probe sequences were fabricated with primer sequences according to Table 1. A Nanodrop 2000c (Thermo, Wilmington, DE, USA) was used to quantify the total RNA levels. Real-time RT-PCR was performed using FastStart Universal SYBR Green Master mix (Roche) and quantified on an Applied Biosystems 7500 Real-Time PCR machine. The amplification profile was 40 cycles at 95 °C for 15 s (annealing),

Table 1 PCR primers for genes encoding MMP2, IL-1, Runx2, ALP, COL1a2, OCN and GAPDH

Gene	Primer Sequence
hMMP2 F	ccccaaacggacaaga
hMMP2 R	cttcagcacaacagggtgc
hIL-1 F	ggttgagttaagccaatcca
hIL-1 R	ggtgatgacctaggcttgatg
hRunx2 F	tcttagaacaattctcccttt
hRunx2 R	tgctttggcttgaatacaca
hCOL1a2 F	cccagccaagaactggtatag
hCOL1a2 R	ggctgccagcattgatagtttc
hALP F	gacctctcgaagacactc
hALP R	tgaagggtcttctgtctgtg
hOCN F	agcaaaggtgcagcctttgt
hOCN R	gcgcttggtctcttctact
hGAPDH F	agccacatcgctcagacac
hGAPDH R	gcccaatcagaccaatcc

followed by 60 °C for 60 s (elongation). The $\Delta\Delta C_t$ method was used to calculate gene expression levels normalized to the expression of glyceraldehyde 3-phosphate dehydrogenase (GAPDH).

Inflammatory cytokine quantification with ELISA

The supernatant culture media were collected at 1 and 3 days post cell seeding. MMP2 (DY902, range = 0.625–20.00 ng/mL) and IL-1β/IL-F2 (DY201, range = 3.91–250 pg/mL) were quantified using an ELISA assays (R&D Systems, Minneapolis, MN, USA) according to manufacturer's protocol as previously described [31, 32]. Briefly, 100 µL of assay diluents and 100 µL of sample were incubated for 2 h at room temperature in antibody-precoated 96-well plates. Wells were washed 3 times with washing buffer, incubated for 2 h with peroxidase-conjugated antibody solution, washed again, followed by the addition of 100 µL of substrate solution for 20 min and 50 µL of stopping solution for 20 min. Absorbance was measured at 450 nm and 570 nm on an ELx808 Absorbance Reader and subtract at 570 nm from the readings at 450 nm.

ALP activity assay

PDL cells were stimulated within each concentration of HA with and without ODM. At 7 days, cells were quantified for alkaline phosphatase expression utilizing a cell imaging system. Alkaline phosphatase activity was monitored using a Leukocyte alkaline phosphatase kit (procedure No. 86, Sigma) as previously described [33]. PDL cells were fixed by immersion in a citrate-acetone-formaldehyde fixative solution for 5 min. The alkaline-dye mixture was prepared by mixing 1 mL Sodium

Nitrite Solution and 1 mL of a fast red violet alkaline solution dissolved in 45 mL of distilled water and 1 mL of Naphtol AS-BI alkaline solution. Surfaces were then placed in an alkaline dye mixture solution for 15 min protected from light followed by rinsing in deionized water. All images were captured on a Wild Heerbrugg M400 ZOOM Makroskop (WILD HEERBRUGG, Heerbrugg, Switzerland) at the same magnification and light intensity and imported into Image J software (NIH, Bethesda, MD, USA). Image segmentation (Thresholding) was used to generate percent stained values for each field of view.

Immunofluorescent staining

At 14 days post PDL cell seeding, the cells were fixed with 4% formaldehyde for 10 min, followed by permeabilized within PBS containing 0.2% Triton X-100 and blocked in PBS containing 1% bovine serum albumin (BSA, Sigma) for 1 h. Subsequently, cells incubated overnight at 4 °C either with a polyclonal rabbit to collagen type I antibody (sc-28657, Santa Cruz, CA, USA) or a polyclonal rabbit to osteocalcin antibody (sc-30044, Santa Cruz) at a dilution of 1:75 in PBS containing 1% BSA. After washing with PBS, cells were incubated for 1 h at 37 °C with TR-conjugated-goat-anti-rabbit antibodies (sc-2780, Santa Cruz) (1:100) diluted in PBS containing 1% BSA. Prior to viewing, samples were mounted with Vectashield containing DAPI nuclear staining (Vector, Burlingame, CA, USA). Images were captured from each surface with an OLYMPUS BX51 fluorescence microscope. The optical density (OD) of the fluorescent staining was quantified from 3 independent experiments using Image J software.

Mineralization assay

Alizarin red staining was performed to determine the presence of extracellular matrix mineralization. PDL cells were stimulated for 14 days within each concentration of HA in ODM. After 14 days, cells were fixed in 96% ethanol for 15 min and stained with 0.2% alizarin red solution (Alizarin Red S, Sigma) in water (pH 6.4) at room temperature for 1 h as previously described [30]. All images were captured and the percentage of staining was evaluated in the same manner as the ALP assay.

Statistical analysis

All experiments were performed in triplicate with three independent experiments for each condition. Mean and standard error (SE) were analyzed for statistical significance using a one-way analysis of variance with Tukey post hoc test (*, p values < 0.05 was considered significant) by GraphPad Prism 6.0 software (GraphPad Software, Inc., La Jolla, CA, USA).

Results

Cell viability and proliferation in response to HA

To investigate the biocompatibility of HA towards human PDL cells, the alive / dead assay was utilized. It was determined that both HA_ncl or HA_cl maintained a high level of cell viability (over 90%) in the presence of HA at various concentrations (Fig. 1). Moreover, the mRNA expression of inflammatory cytokine genes encoding MMP2 and IL-1 of PDL cells treated with either HA_ncl or HA_cl demonstrated little differences at 1 day post seeding when compared to control samples (Fig. 2a, c). Inflammatory cytokine release of MMP and IL-1 from PDL cells treated with either HA_ncl or HA_cl was investigated at 1 day and 3 days post cell seeding (Fig. 2b, d). There was no significant difference


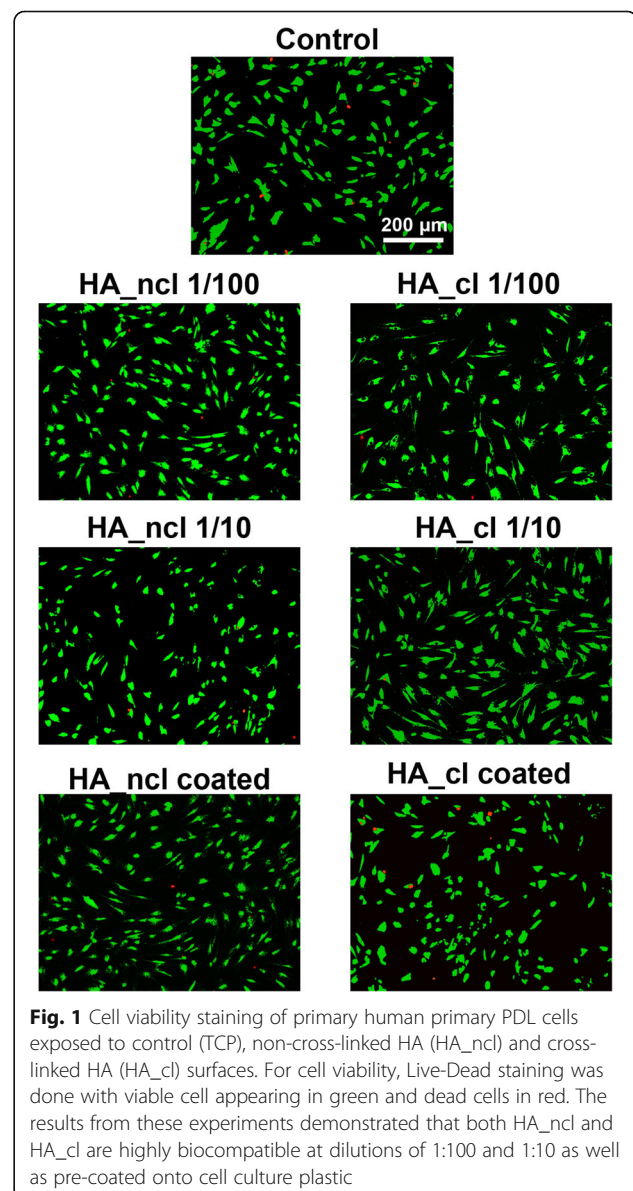


Fig. 1 Cell viability staining of primary human primary PDL cells exposed to control (TCP), non-cross-linked HA (HA_ncl) and cross-linked HA (HA_cl) surfaces. For cell viability, Live-Dead staining was done with viable cell appearing in green and dead cells in red. The results from these experiments demonstrated that both HA_ncl and HA_cl are highly biocompatible at dilutions of 1:100 and 1:10 as well as pre-coated onto cell culture plastic

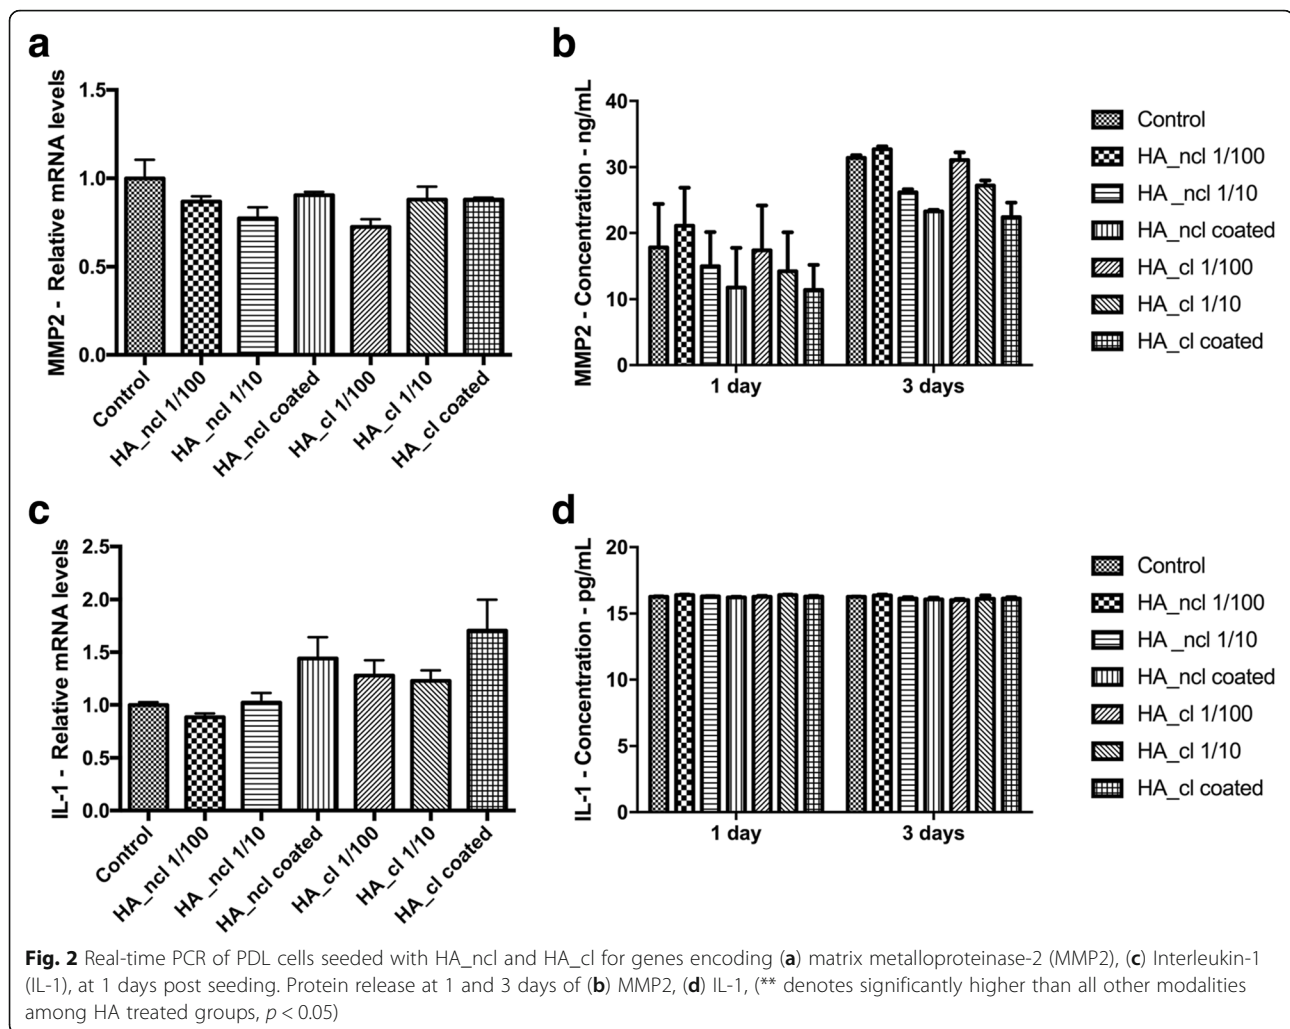


between MMP2 and IL-1 release among both HA_ncl and HA_cl treated groups as well as mRNA expression (Fig. 2b, d). Thereafter, PDL cell proliferation was investigated in response to HA_ncl and HA_cl at 1, 3 and 5 days post seeding (Fig. 3). It was found that while cell numbers were indifferent at 1 day post seeding (Fig. 3a), a significant increase was observed at 3 and 5 days in either diluted condition for both HA_ncl and HA_cl (Fig. 3b, c).

Cell differentiation in response to HA

Thereafter, the primary human PDL cells were investigated for their ability to differentiate when cultured with HA_ncl and HA_cl (Figs. 4, 5, 6 and 7). The mRNA expression of osteogenic markers was compared by real-time PCR for genes encoding Runx2, COL1a2, ALP and OCN at 7 days (Fig. 4). All HA_ncl and HA_cl treatments significantly downregulated Runx2, COL1a2, ALP and OCN mRNA levels when compared with control samples (Fig. 4a, c, e, g), in normal growth medium. When ODM supplement was added to culture media, it

was found that no significant difference was observed in the Runx2 mRNA expression (Fig. 4b), whereas both HA_ncl and HA_cl in 1:10 diluted condition demonstrated a 3-fold significant increase in COL1a2 mRNA levels (Fig. 4d) and a 20-fold increase in ALP levels. Nevertheless, the OCN mRNA expression was still significantly downregulated in either 1:10 diluted or coated conditions for both HA_ncl and HA_cl despite culture with ODM at 7 days post cell seeding (Fig. 4h).

Moreover, it was generally found that HA_ncl significantly decreased ALP staining. HA_cl treatment demonstrated no significant changes in the ALP staining at 7 days likely as a result of the cross-linking HA (Fig. 5a). Interestingly, when ODM was added to cell culture media to promote osteogenic differentiation, HA_ncl at a dilution of 1:10 significantly increased up to 5-fold ALP staining when compared to all other treatment modalities (Fig. 5b, depicted by **). In addition, both HA_ncl and HA_cl coated samples demonstrated a significant increase in ALP staining under ODM supplement

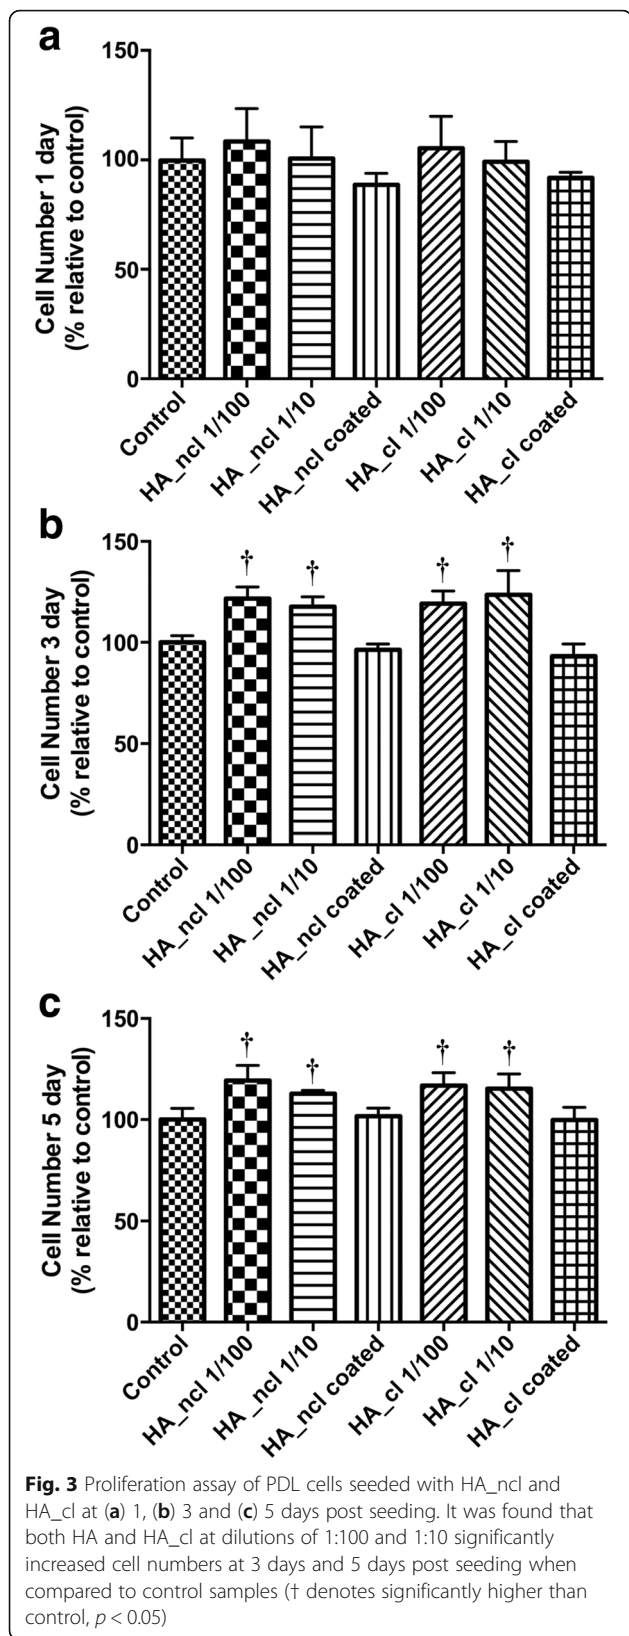

when compared to control TCP at 7 days (Fig. 5b). Thereafter, it was demonstrated that both HA_ncl and HA-cl significantly decreased COL1 immunofluorescent staining at 14 days post seeding (Fig. 6a, c) as well as mRNA expression via real-time PCR at 7 days (Fig. 4c).

Cells were further investigated by OCN immunostaining and alizarin red staining when induced by HA_ncl and HA_cl treatment (Figs. 6b, d, and 7). All HA_ncl and HA_cl treatment significantly decreased OCN protein expression and alizarin red staining when compared to control samples as well as OCN mRNA expression (Fig. 4g, h).

Discussion

In the present study, the effect of high molecular weight (HMW) HA_ncl and HA_cl were evaluated on in vitro periodontal ligament cell behavior. It was first found that both HA_ncl and HA_cl did not elucidate PDL cell apoptosis even at high concentrations (Fig. 1). Both compositions of HA were shown to be biocompatible on PDL cells without any noticeable differences between their in vitro conditions (diluted in culture media versus pre-coated onto TCP).

We then sought to investigate the inflammatory response of HA on PDL cells. It has previously been shown that low molecular weight (LMW, 100–500 kDa) HA, but not the native HMW HA molecules (~4,000 kDa), stimulated inflammatory cells [34]. Nakatani et al. reported that the expression of MMP-1 in cultured human PDL cells was enhanced by the treatment with HA-oligo through p38MAPK signaling pathway, suggesting that the degradation of the periodontal tissues under pathologic conditions may involve MMP-1 induction by HA-oligo [35]. On the other hand, the majority of products used in connection with periodontal therapy contain HMW HA [8]. The mechanism of anti-inflammatory effects of HMW HA has been widely investigated previously due to the pronounced impact and desire for treatment modalities in the field of osteoarthritis and periodontitis. HA has been shown to modulate inflammation in articular chondrocytes and synovocytes, due to the specific inhibition of MMPs [19, 36] and down-regulation of TNF- α , IL-8, and inducible nitric oxide synthase [37]. In the present study, HMW HA and HA_cl did not affect the mRNA expressions of inflammatory cytokines, including MMP-2 and IL-1 at 1 day post seeding in healthy PDL cells (Fig. 2). The present study was assessed only in utilizing healthy human PDL cells, whereas in the presence of inflammation, HMW HA within these tissues is reportedly broken down to LMW HA by reactive oxygen species or by bacterial hyaluronidase [8, 38–40]. Therefore, these combined results suggest that although HA demonstrated the little influence on the inflammation in the current study utilizing healthy PDL cells, a more pronounced effect could be observed in diseased tissues due to gingival tissue inflammation in periodontitis.

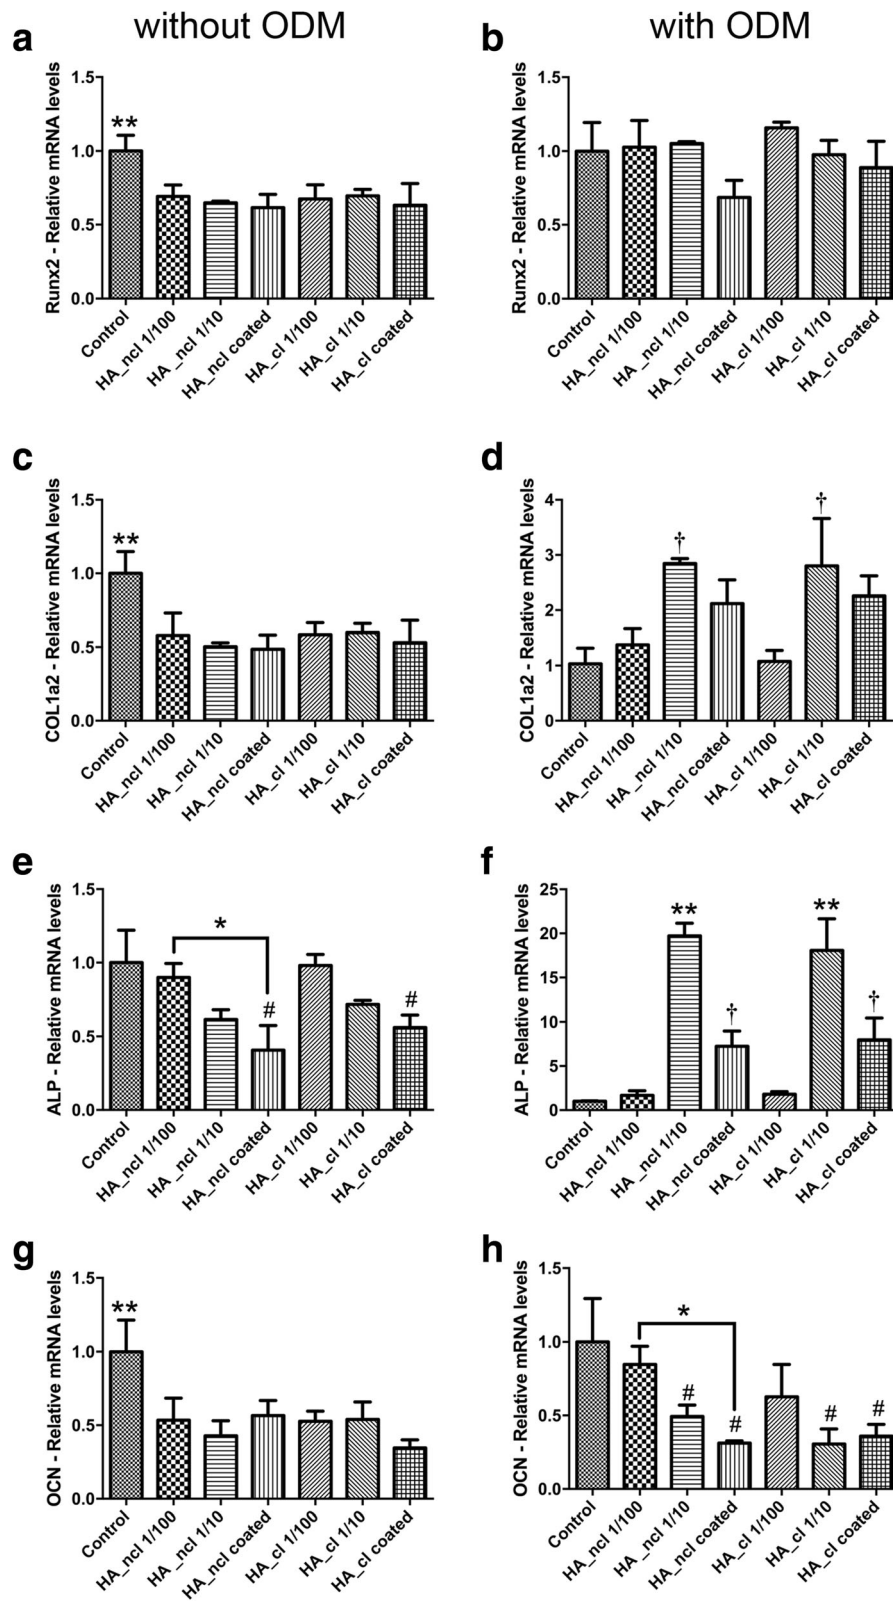


Fig. 4 (See legend on next page.)

(See figure on previous page.)

Fig. 4 Real-time PCR of PDL cells seeded with HA_ncl and HA_cl treatment for genes encoding (a, b) Runx2, (c, d) Collagen 1 alpha 2 (COL1a2), (e, f) alkaline phosphatase (ALP) and (g, h) osteocalcin (OCN) at 7 days post seeding. Cells were treated (a, c, e, g) in regular growth medium or (b, d, f, h) with ODM. (* denotes significant difference, $p < 0.05$; # denotes significantly lower than control, $p < 0.05$; † denotes significantly higher than control, $p < 0.05$; ** denotes significantly higher than all other treatment modalities, $p < 0.05$)

Thereafter, the effects of HA demonstrated an increase in PDL cell proliferation (Fig. 3). During the granulation phase of periodontal tissue repair, HA has been shown to be a key protein highly expressed in various tissues responsible for promoting cell proliferation, migration, and granulation tissue organization [19]. In non-mineralized tissues, HA is transiently elevated during the formation of tissue repair and helps with the re-establishment of the epithelium [38]. In our study, both 1:100 and 1:10 dilution of HA_ncl, as well as HA_cl, promoted cell proliferation at 3 and 5 days post PDL cell seeding (Fig. 3). It was previously shown by Takeda et al. in the same manner that HMW HA enhanced cell adhesion and proliferation of human periodontal ligament cells [9]. In our study, both diluted HA compositions and pre-coated HA promoted PDL cell proliferation, which suggests a positive effect for periodontal tissue regeneration.

The effect of HMW HA on cell differentiation has however had controversial findings. To date, most studies reported that cell differentiation was increased by low-MW HA [16, 41–43]. Huang et al. [41] reported an osteogenic cell behavior of HMW HA in a concentration-dependent manner on rat mesenchymal stem cells. Moreover, it was demonstrated that sulfated HMW HA could enhance the osteogenic differentiation of human mesenchymal stem cells [44]. On the other

hand, studies have also shown that cell differentiation was not affected by HMW HA [16, 45–48]. For example, Kaneko et al. demonstrated that HA inhibited BMP-induced osteoblastic differentiation through the CD44 receptor in osteoblasts [45]. Noteworthy, in a pure bone defect model, it was demonstrated that HA-gelatin hydrogels loaded into biphasic calcium phosphate (BCP) ceramics in rabbit femurs promoted the new bone formation and collagen mineralization [46]. HA gel has further been shown to accelerate the healing process in the tooth sockets of rats, stimulating the expression of osteogenic proteins such as bone morphogenetic protein (BMP)-2 and osteopontin (OPN) in vivo [47]. On the other hand, Atilgan et al. reported that the demineralized bone matrix (DBM) + tricalcium phosphate + HA combination showed more new bone formation without HA [48]. Therefore, there remains great interest to determine what may be causing the reported variability in the literature.

In the present study, the expression of osteogenic markers stimulated by HA_ncl and HA_cl was investigated with and without ODM. Both HA_ncl and HA_cl down-regulated Runx2, COL1a2 and OCN mRNA levels, suggesting that HA treatment of PDL cells inhibits osteogenesis in a regular cell culture medium (Fig. 4). Moreover, it was observed that HA significantly decreased ALP activity at 7 days, COL1 and OCN

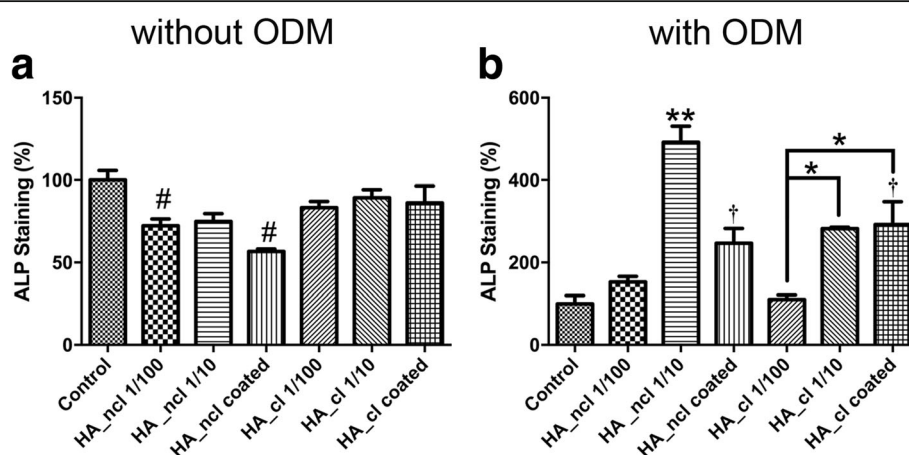


Fig. 5 Alkaline phosphatase staining of PDL cells treated by HA_ncl and HA_cl (a) in growth medium or (b) within ODM at 7 days post seeding. Both HA_ncl and HA_cl significantly decreased ALP staining without ODM while with ODM both HA_ncl and HA_cl significantly increased ALP staining when compared to control samples (* denotes significant difference, $p < 0.05$; # denotes significantly lower than control, $p < 0.05$; † denotes significantly higher than control, $p < 0.05$; ** denotes significantly higher than all other treatment modalities, $p < 0.05$)

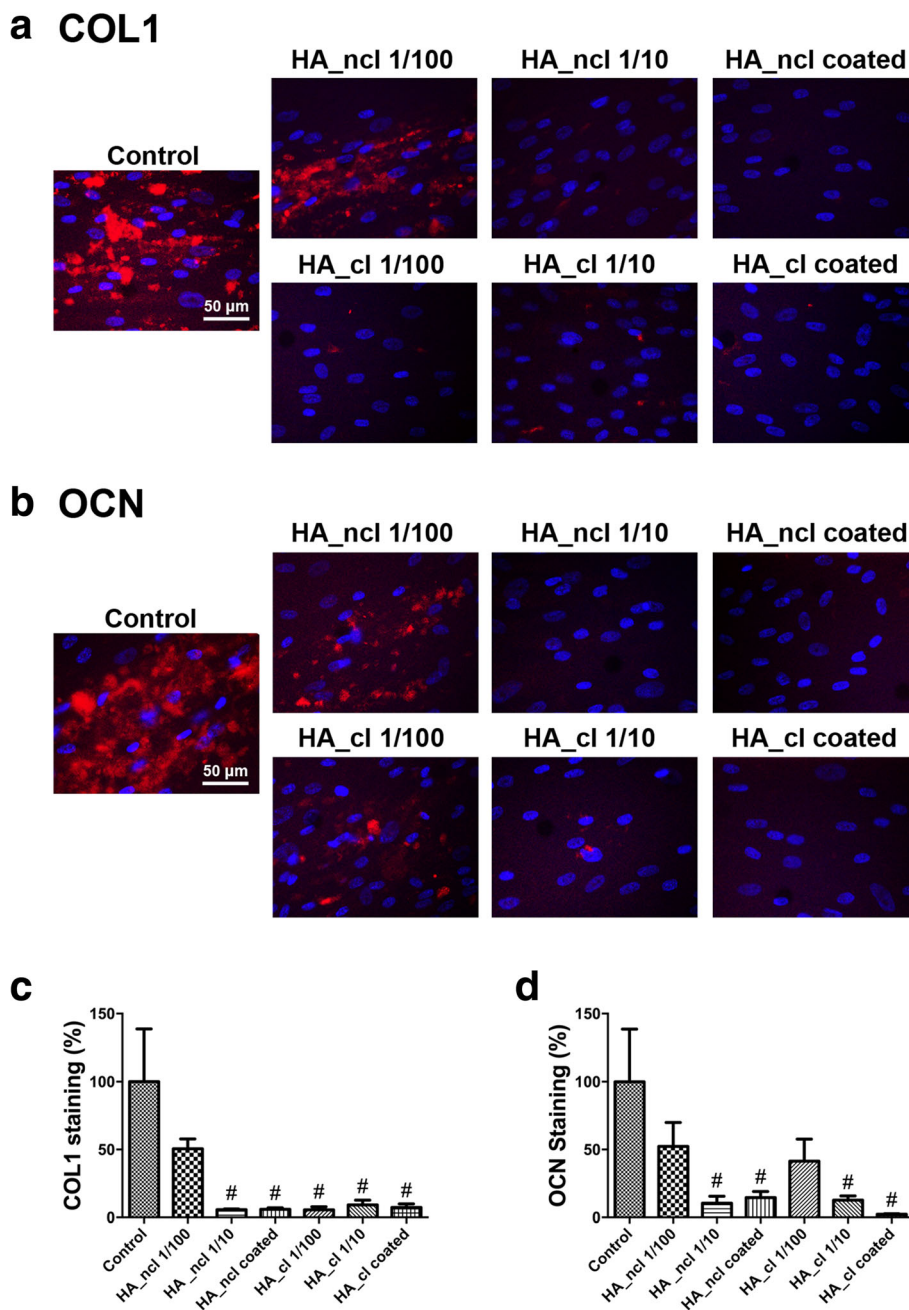


Fig. 6 Immunofluorescent COL1 staining and OCN staining at 14 days post cell seeding with HA_ncl and HA_cl. **(a)** The merged images of immunofluorescent detection of COL1 (red) and DAPI (blue). **(b)** The merged images of immunofluorescent detection of OCN (red) and DAPI (blue). **(c, d)** Quantified data of **(c)** COL1 and **(d)** OCN immunostaining at 14 days (# denotes significantly lower than control, $p < 0.05$)

immunofluorescent staining at 14 days when compared to control samples (Figs. 5a, 6). Interestingly, however, when ODM was added to promote osteoblast differentiation, it was found that both HA_ncl or HA_cl in 1:10 diluted condition demonstrated a 3-fold and 20-fold increase in COL1a2 and ALP mRNA levels respectively in ODM (Fig. 4d, f). Moreover, HA_ncl at a dilution of 1:10 demonstrated a 5-fold significant increase in ALP staining

compared to control samples in the presence of ODM (Fig. 5b). Therefore, it may be concluded that if granted the right culture conditions, the HA may be used to promote early osteogenic differentiation. Interestingly, however, was the finding that irrespective of the addition of ODM, both HA compositions consistently down-regulated late osteoblast differentiation as assessed by OCN mRNA expression as well as alizarin red staining (Fig. 7).

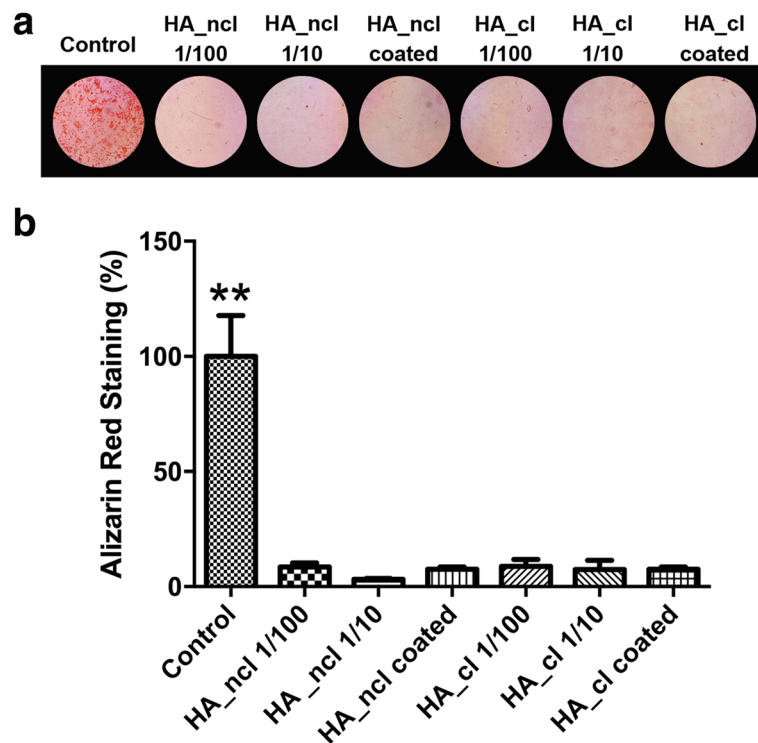


Fig. 7 Alizarin red staining denoting mineralization at 14 days post seeding. (a) Alizarin red staining images and (b) quantified data of alizarin red staining from colour thresholding software for PDL cells treated with HA_ncl or HA_cl (** denotes significantly higher than all other treatment modalities, $p < 0.05$). It was found that both HA_ncl and HA_cl treatment significantly decreased alizarin red staining

For periodontal regeneration, HMW HA has previously been investigated in a dog intrabony defect model and neither significant periodontal tissue nor bone tissue regeneration was observed [9]. Interestingly, in another canine model, Kim et al. reported that HA improved wound healing and bone formation of hemisection performed extraction sockets with communication of the periodontal lesion [49]. The effect of HMW-HA on periodontal regeneration remains somewhat controversial, however, its contradiction might be explained due to the variety of HA molecular weight, modification methods, concentration, existence of inflammation and also cell types. It may be that HA requires an osteoconductive matrix during periodontal regeneration to improve the osteogenic phase of PDL regeneration, however, this hypothesis certainly requires further investigation.

Conclusion

Both HA_ncl and HA_cl were shown to be extremely biocompatible and at both concentrations were associated with a significant increase in PDL cell numbers. The early osteogenic differentiation markers such as Runx2, COL1 and ALP were significantly downregulated in standard cell growth media. Interestingly, with the addition of ODM, the expression of early osteogenic markers was shown to significantly increase COL1 and ALP levels, especially at

higher concentration (1:10) utilizing both HA_ncl and HA_cl diluted condition. Nevertheless, the late stage osteogenic marker such as OCN as well as calcium formation was inhibited regardless of the ODM addition. Future in vitro models including in inflammatory conditions, as well as animal research, are necessary to further characterize the optimal uses as well as delivery systems of HA for improved clinical use.

Abbreviations

ALP: Alkaline phosphatase; BCP: Biphasic calcium phosphate; BDDE: Butanediol diglycidyl ether; BSA: Bovine serum albumin; COL: Collagen; DBM: Demineralized bone matrix; DMEM: Dulbecco's modified eagle medium; EDTA: Ethylenediaminetetraacetic acid; FBS: Fetal Bovine serum; GAPDH: Glyceraldehyde 3-phosphate dehydrogenase; HA: Hyaluronic acid; HA_cl: Cross-linked HA; HA_ncl: Non-cross-linked hyaluronic acid; HMW: High molecular weight; IL-1: Interleukin-1; LMW: Low molecular weight; MMP2: Matrix metalloproteinase-2; MTS: 3-(4,5-dimethylthiazol-2-yl)-5-(3-carboxymethoxyphenyl)-2-(4-sulfophenyl)-2H-tetrazolium; OCN: Osteocalcin; OCN: Osteocalcin; OD: Optical density; ODM: Osteogenic differentiation medium; OPN: Osteopontin; PBS: Phosphate buffered saline; PDL: Periodontal ligament; RT-PCR: Reverse transcription polymerase chain reaction; Runx2: Runt-related transcription factor 2; SE: Standard error; TCP: Tissue culture plastic.

Acknowledgement

The authors thank Catherine Solioz for her careful technical assistance in helping with the experiments.

Funding

The authors received funding from Regedent who provided the HA materials utilized in the present manuscript.

Availability of data and materials

The datasets used and/or analyzed during the current study available from the corresponding author on reasonable request.

Authors' contributions

MFK, HDM, AM, AL, AS, PRS and RJM have made substantial contributions to conception and design, MFK, HDM, AM and PRS have made the acquisition of data, and MFK, HDM, AL, AS, and RJM have performed analysis and interpretation of data. MFK, AS and RJM have been involved in drafting the manuscript or revising it critically for important intellectual content. MFK, HDM, AM, AL, AS, PRS and RJM have given final approval of the version to be published.

Competing interests

Patrick Schmidlin has received a research grant from Regedent, Switzerland. Both non-cross-linked and cross-linked HA utilized in the present study were also provided by Regedent. All other authors declare that they have no competing interests to disclose.

Consent for publication

Not applicable.

Ethics approval and consent to participate

Not applicable. The primary human PDL cells within the present manuscript did not require an ethical approval as the tissues were to be discarded and was performed in accordance with the Declaration of Helsinki and approved by the Ethics Committee of the Canton of Bern, University of Bern, Switzerland. All patients gave their consent.

Author details

¹Department of Cranio-Maxillofacial Surgery, Bern University Hospital, Inselspital, Bern, Switzerland. ²Department of Oral Surgery, Institute of Biomedical Sciences, Tokushima University, Tokushima, Japan. ³Department of Preventive, Restorative and Pediatric Dentistry, School of Dental Medicine, University of Bern, Bern, Switzerland. ⁴Clinic of Preventive Dentistry, Periodontology and Cariology, Center of Dental Medicine, University of Zurich, Zürich, Switzerland. ⁵Department of Periodontology, School of Dental Medicine, University of Bern, Bern, Switzerland. ⁶Department of Periodontology, College of Dental Medicine, Nova Southeastern University, Fort Lauderdale, FL, USA. ⁷Cell Therapy Institute, Center for Collaborative Research, Nova Southeastern University, Fort Lauderdale, FL, USA. ⁸Department of Periodontics and Oral Medicine, University of Michigan School of Dentistry, Ann Arbor, MI, USA.

Received: 2 August 2016 Accepted: 11 January 2017

Published online: 16 January 2017

References

- Toole BP. Hyaluronan in morphogenesis. *Semin Cell Dev Biol*. 2001;12(2):79–87.
- Bertolami CN, Messadi DV. The role of proteoglycans in hard and soft tissue repair. *Crit Rev Oral Biol Med*. 1994;5(3–4):311–37.
- Pilloni A, Rimondini L, De Luca M, Bernard GW. Effect of hyaluronan on calcification-nodule formation from human periodontal ligament cell culture. *J Appl Biomater Biomech*. 2003;1(1):84–90.
- Chen WY, Abatangelo G. Functions of hyaluronan in wound repair. *Wound Repair Regen*. 1999;7(2):79–89.
- Donegan GC, Hunt JA, Rhodes N. Investigating the importance of flow when utilizing hyaluronan scaffolds for tissue engineering. *J Tissue Eng Regen Med*. 2010;4(2):83–95.
- Bartold PM, Xiao Y, Lyngstaadas SP, Paine ML, Snead ML. Principles and applications of cell delivery systems for periodontal regeneration. *Periodontol*. 2006;41:123–35.
- Choi SC, Yoo MA, Lee SY, Lee HJ, Son DH, Jung J, Noh I, Kim CW. Modulation of biomechanical properties of hyaluronic acid hydrogels by crosslinking agents. *J Biomed Mater Res A*. 2015;103(9):3072–80.
- Collins MN, Birkinshaw C. Hyaluronic acid based scaffolds for tissue engineering—A review. *Carbohydr Polym*. 2013;92(2):1262–79.
- Takeda K, Sakai N, Shiba H, Nagahara T, Fujita T, Kajiya M, Iwata T, Matsuda S, Kawahara K, Kawaguchi H, et al. Characteristics of high-molecular-weight hyaluronic acid as a brain-derived neurotrophic factor scaffold in periodontal tissue regeneration. *Tissue Eng A*. 2011;17(7–8):955–67.
- Ishijima M, Nakamura T, Shimizu K, Hayashi K, Kikuchi H, Soen S, Omori G, Yamashita T, Uchio Y, Chiba J, et al. Intra-articular hyaluronic acid injection versus oral non-steroidal anti-inflammatory drug for the treatment of knee osteoarthritis: a multi-center, randomized, open-label, non-inferiority trial. *Arthritis Res Ther*. 2014;16(1):R18.
- Brzusek D, Petron D. Treating knee osteoarthritis with intra-articular hyaluronans. *Curr Med Res Opin*. 2008;24(12):3307–22.
- Manfredini D, Piccotti F, Guarda-Nardini L. Hyaluronic acid in the treatment of TMJ disorders: a systematic review of the literature. *Cranio*. 2010;28(3):166–76.
- Guarda-Nardini L, Cadorin C, Frizziero A, Ferronato G, Manfredini D. Comparison of 2 hyaluronic acid drugs for the treatment of temporomandibular joint osteoarthritis. *J Oral Maxillofac Surg*. 2012;70(11):2522–30.
- Cohen JL, Dayan SH, Brandt FS, Nelson DB, Axford-Gatley RA, Theisen MJ, Narins RS. Systematic review of clinical trials of small- and large-gel-particle hyaluronic acid injectable fillers for aesthetic soft tissue augmentation. *Dermatol Surg*. 2013;39(2):205–31.
- Becker W, Gabitov I, Stepanov M, Kois J, Smidt A, Becker BE. Minimally invasive treatment for papillae deficiencies in the esthetic zone: a pilot study. *Clin Implant Dent Relat Res*. 2010;12(1):1–8.
- Zhao N, Wang X, Qin L, Zhai M, Yuan J, Chen J, Li D. Effect of hyaluronic acid in bone formation and its applications in dentistry. *J Biomed Mater Res A*. 2016;104(6):1560–9. doi:10.1002/jbma.35681. Epub 2016 Apr 9.
- Oksala O, Salo T, Tammi R, Hakkinen L, Jalkanen M, Inki P, Larjava H. Expression of proteoglycans and hyaluronan during wound healing. *J Histochem Cytochem*. 1995;43(2):125–35.
- Yeh Y, Yang Y, Yuan K. Importance of CD44 in the proliferation and mineralization of periodontal ligament cells. *J Periodontol Res*. 2014;49(6):827–35.
- Dahiya P, Kamal R. Hyaluronic Acid: a boon in periodontal therapy. *N Am J Med Sci*. 2013;5(5):309–15.
- Johannsen A, Tellefsen M, Wikesjo U, Johannsen G. Local delivery of hyaluronan as an adjunct to scaling and root planing in the treatment of chronic periodontitis. *J Periodontol*. 2009;80(9):1493–7.
- Bertl K, Bruckmann C, Isberg PE, Klinge B, Gotfredsen K, Stavropoulos A. Hyaluronan in non-surgical and surgical periodontal therapy: a systematic review. *J Clin Periodontol*. 2015;42(3):236–46.
- Briguglio F, Briguglio E, Briguglio R, Cafiero C, Isola G. Treatment of infrabony periodontal defects using a resorbable biopolymer of hyaluronic acid: a randomized clinical trial. *Quintessence Int*. 2013;44(3):231–40.
- Fawzy El-Sayed KM, Dahaba MA, Aboul-Ela S, Darhous MS. Local application of hyaluronan gel in conjunction with periodontal surgery: a randomized controlled trial. *Clin Oral Investig*. 2012;16(4):1229–36.
- Saranraj P. Hyaluronic Acid Production and its Applications A Review. *Int J Pharm Biol Arch*. 2013;4(5):853–59.
- Mueller A, Fujioka-Kobayashi M, Mueller HD, Lussi A, Sculean A, Schmidlin PR, Miron RJ. Effect of hyaluronic acid on morphological changes to dentin surfaces and subsequent effect on periodontal ligament cell survival, attachment, and spreading. *Clin Oral Investig*. 2016. [Epub ahead of print].
- Miron RJ, Bosshardt DD, Hedbom E, Zhang Y, Haenni B, Buser D, Sculean A. Adsorption of enamel matrix proteins to a bovine-derived bone grafting material and its regulation of cell adhesion, proliferation, and differentiation. *J Periodontol*. 2012;83(7):936–47.
- Miron RJ, Caluseru OM, Guillemette V, Zhang Y, Gemperli AC, Chandad F, Sculean A. Influence of enamel matrix derivative on cells at different maturation stages of differentiation. *PLoS One*. 2013;8(8):e71008.
- Sawada K, Caballe-Serrano J, Bosshardt DD, Schaller B, Miron RJ, Buser D, Gruber R. Antiseptic solutions modulate the paracrine-like activity of bone chips: differential impact of chlorhexidine and sodium hypochlorite. *J Clin Periodontol*. 2015;42(9):883–91. doi:10.1111/jcpe.12447. Epub 2015 Sep 28.
- Miron RJ, Saulacic N, Buser D, Iizuka T, Sculean A. Osteoblast proliferation and differentiation on a barrier membrane in combination with BMP2 and TGFbeta1. *Clin Oral Investig*. 2013;17(3):981–8.
- Miron RJ, Hedbom E, Saulacic N, Zhang Y, Sculean A, Bosshardt DD, Buser D. Osteogenic potential of autogenous bone grafts harvested with four different surgical techniques. *J Dent Res*. 2011;90(12):1428–33.
- Kobayashi E, Flückiger L, Fujioka-Kobayashi M, Sawada K, Sculean A, Schaller B, Miron RJ. Comparative release of growth factors from PRP, PRF, and advanced-PRF. *Clin Oral Investig*. 2016;20(9):2353–60. Epub 2016 Jan 25.
- Sawada K, Fujioka-Kobayashi M, Kobayashi E, Schaller B, Miron RJ. Effects of Antiseptic Solutions Commonly Used in Dentistry on Bone Viability, Bone Morphology, and Release of Growth Factors. *J Oral Maxillofac Surg*. 2016;74(2):247–54.

33. Miron RJ, Oates CJ, Molenberg A, Dard M, Hamilton DW. The effect of enamel matrix proteins on the spreading, proliferation and differentiation of osteoblasts cultured on titanium surfaces. *Biomaterials*. 2010;31(3):449–60.
34. Eberlein M, Scheibner KA, Black KE, Collins SL, Chan-Li Y, Powell JD, Horton MR. Anti-oxidant inhibition of hyaluronan fragment-induced inflammatory gene expression. *J Inflamm (Lond)*. 2008;5:20.
35. Nakatani Y, Tanimoto K, Tanaka N, Tanne Y, Kamiya T, Kunimatsu R, Tanaka E, Tanne K. Effects of hyaluronan oligosaccharide on the expression of MMP-1 in periodontal ligament cells. *Arch Oral Biol*. 2009;54(8):757–63.
36. Prasadam I, Mao X, Shi W, Crawford R, Xiao Y. Combination of MEK-ERK inhibitor and hyaluronic acid has a synergistic effect on anti-hypertrophic and pro-chondrogenic activities in osteoarthritis treatment. *J Mol Med (Berl)*. 2013;91(3):369–80.
37. Wang CT, Lin YT, Chiang BL, Lin YH, Hou SM. High molecular weight hyaluronic acid down-regulates the gene expression of osteoarthritis-associated cytokines and enzymes in fibroblast-like synoviocytes from patients with early osteoarthritis. *Osteoarthritis Cartilage*. 2006;14(12):1237–47.
38. Bartold PM, Page RC. The effect of chronic inflammation on gingival connective tissue proteoglycans and hyaluronic acid. *J Oral Pathol*. 1986;15(7):367–74.
39. Yamalik N, Kilinc K, Caglayan F, Eratalay K, Caglayan G. Molecular size distribution analysis of human gingival proteoglycans and glycosaminoglycans in specific periodontal diseases. *J Clin Periodontol*. 1998;25(2):145–52.
40. Scott D, Siboo R, Chan EC, Siboo R. An extracellular enzyme with hyaluronidase and chondroitinase activities from some oral anaerobic spirochaetes. *Microbiology*. 1996;142(Pt 9):2567–76.
41. Huang L, Cheng YY, Koo PL, Lee KM, Qin L, Cheng JC, Kumta SM. The effect of hyaluronan on osteoblast proliferation and differentiation in rat calvarial-derived cell cultures. *J Biomed Mater Res A*. 2003;66(4):880–4.
42. Gu H, Huang L, Wong YP, Burd A. HA modulation of epidermal morphogenesis in an organotypic keratinocyte-fibroblast co-culture model. *Exp Dermatol*. 2010;19(8):e336–339.
43. Zou L, Zou X, Chen L, Li H, Mygind T, Kassem M, Bunger C. Effect of hyaluronan on osteogenic differentiation of porcine bone marrow stromal cells in vitro. *J Orthop Res*. 2008;26(5):713–20.
44. Hempel U, Moller S, Noack C, Hintze V, Scharnweber D, Schnabelrauch M, Dieter P. Sulfated hyaluronan/collagen I matrices enhance the osteogenic differentiation of human mesenchymal stromal cells in vitro even in the absence of dexamethasone. *Acta Biomater*. 2012;8(11):4064–72.
45. Kaneko K, Higuchi C, Kunugiza Y, Yoshida K, Sakai T, Yoshikawa H, Nakata K. Hyaluronan inhibits BMP-induced osteoblast differentiation. *FEBS Lett*. 2015;589(4):447–54.
46. Nguyen TB, Lee BT. A combination of biphasic calcium phosphate scaffold with hyaluronic acid-gelatin hydrogel as a new tool for bone regeneration. *Tissue Eng A*. 2014;20(13–14):1993–2004.
47. Mendes RM, Silva GA, Lima MF, Calliari MV, Almeida AP, Alves JB, Ferreira AJ. Sodium hyaluronate accelerates the healing process in tooth sockets of rats. *Arch Oral Biol*. 2008;53(12):1155–62.
48. Atilgan HI, Demirel K, Kankaya Y, Oktay M, Sahiner C, Korkmaz M, Koca G, Kocer U, Kankaya D. Scintigraphic and histopathologic evaluation of combined bone grafts. *J Craniofac Surg*. 2013;24(6):1902–7.
49. Kim JJ, Song HY, Ben Amara H, Kyung-Rim K, Koo KT: Hyaluronic Acid Improves Bone Formation in Extraction Sockets With Chronic Pathology: A Pilot Study in Dogs. *J Periodontol*. 2016;87(7):790-5. doi:10.1902/jop.2016.150707. Epub 2016 Mar 18.

Submit your next manuscript to BioMed Central and we will help you at every step:

- We accept pre-submission inquiries
- Our selector tool helps you to find the most relevant journal
- We provide round the clock customer support
- Convenient online submission
- Thorough peer review
- Inclusion in PubMed and all major indexing services
- Maximum visibility for your research

Submit your manuscript at
www.biomedcentral.com/submit

