Chemistry A European Journal



European Chemical Societies Publishing



Accepted Article

Title: Driving the Emission Towards Blue by Controlling the HOMO-LUMO Energy Gap in BF2-functionalized 2-(imidazo[1,5-a]pyridin-3-yl)phenols

Authors: Gioele Colombo, G. Attilio Ardizzoia, Julien Furrer, Bruno Therrien, and Stefano Brenna

This manuscript has been accepted after peer review and appears as an Accepted Article online prior to editing, proofing, and formal publication of the final Version of Record (VoR). This work is currently citable by using the Digital Object Identifier (DOI) given below. The VoR will be published online in Early View as soon as possible and may be different to this Accepted Article as a result of editing. Readers should obtain the VoR from the journal website shown below when it is published to ensure accuracy of information. The authors are responsible for the content of this Accepted Article.

To be cited as: Chem. Eur. J. 10.1002/chem.202101520

Link to VoR: https://doi.org/10.1002/chem.202101520

WILEY-VCH

FULL PAPER

Driving the Emission Towards Blue by Controlling the HOMO-LUMO Energy Gap in BF₂-functionalized 2-(imidazo[1,5-a]pyridin-3-yl)phenols

Gioele Colombo, [a,b] G. Attilio Ardizzoia, [a,b] Julien Furrer, [c] Bruno Therrien [d] and Stefano Brenna*[a,b]

G. Colombo, Prof. Dr. G. A. Ardizzoia, Prof. Dr. S. Brenna

Department of Science and High Technology

University of Insubria

Via Valleggio, 9 – 22100 Como (Italy)

E-mail: stefano.brenna@uninsubria.it

G. Colombo, Prof. Dr. G. A. Ardizzoia, Prof. Dr. S. Brenna

Consorzio Interuniversitario Reattività Chimica e Catalisi (CIRCC), Bari, Italy

[c] Prof. Dr. J. Furrer

Department für Chemie, Biochemie und Pharmazie

Universität Bern

Freiestrasse 3, CH-3012 Bern (Switzerland)

[d] Prof. Dr. B. Therrien

Institute of Chemistry

Université de Neuchâtel

Avenue de Bellevaux 51, CH-2000 Neuchâtel (Switzerland)

Supporting information for this article is given via a link at the end of the document.

Abstract: Several boron compounds with 2-(imidazo[1,5-a]pyridin-3-yl)phenols, differentiated by the nature of the substituent (R) in the para position of the hydroxy group, have been synthesized and thoroughly characterized both in solution (1 H, 13 C, 11 B, 19 F NMR) and in the solid state (X-ray). All derivatives displayed attractive photophysical properties like very high Stokes shift, high fluorescence quantum yields and a good photostability in solution. Time-Dependent Density Functional Theory (TD-DFT) calculations allowed to define the main electronic transitions as intra ligand transitions (11 LT), which was corroborated by the Natural Transition Orbitals (NTOs) shapes. The HOMO-LUMO energy gap was correlated to the electronic properties of the substituent R on the phenolic ring, as quantified by its σ_p Hammett constant.

Introduction

In recent years there has been a growing attention towards luminescent compounds suitable for different devices such as Organic Light Emitting Diodes (OLEDs),^[1] Light Emitting Electrochemical Cells (LECs),^[2] Dye Sensitized Solar Cells (DSSCs)^[3] or as fluorescent sensors.^[4] These compounds are mostly based on rare and expensive transition metals, like platinum(II),^[5] iridium(III),^[6] ruthenium(II)^[7] or rhenium(I)^[8] and, therefore, not convenient from an economic point of view. In order to offer a valid alternative to these efficient but high-cost compounds, the interest has been moved to low-cost organic dyes^[9] and to coordination compounds of cheaper metals, usually in a d¹⁰ electronic configuration, such as copper(I)^[10] or zinc(II).^[11,12] Boron is also another interesting element which is known to give fluorescent coordination compounds,^[13-15] with boron dipyrromethene (BODIPY) being the most renown and

studied derivatives.^[16] Thanks to their photophysical properties, these species are known to play a significant role in numerous application fields, ranging from biomolecular probes^[17] to optoelectronic.^[18] Even more interesting is the possibility to tune the emission of these species, by introducing small modifications^[19,20] and/or extending the conjugation around the fluorescent core.^[21] BODIPY type species are extremely versatile as well, thanks to their high photo^[22] and chemical stability^[23] and their high solubility even in aqueous media.^[24] Other classes of ligands, either N,N^[25] or N,O^[26] chelating, proved to be useful in the synthesis of highly emissive boron compounds as well.

Among our research group, we also focused on a series of organic dyes, namely the imidazo[1,5-a]pyridines, whose biological^[27] and photophysical properties^[28] have been largely studied and reported in the literature, the latter including large Stokes shifts and high quantum yields.^[29,30] Furthermore, they are known to act as ligands in the synthesis of luminescent transition metal coordination compounds,[31-35] or in the fabrication of OLEDs.[36-38] In previous works, the photophysical properties of this class of coordination compounds were investigated on both zinc(II)[39-41] and silver(I),[42] using opportunely derivatized imidazo[1,5-a]pyridine ligands. More recently, a series of hydrogenated dyes deriving from this class of molecules has also been studied and demonstrated to be efficient blue emissive materials in solution and in thin film.[43] Surprisingly, only few examples of boron derivatives with imidazo-pyridines have been reported in the literature. [44,45] In the recent past, we also investigated the previously cited hydrogenated ligands in the synthesis of boron difluoride coordination compounds, which showed excellent optical properties like high fluorescence quantum yields.[46]

For all these reasons, we decided to prepare a series of new boron compounds, using imidazo[1,5-a]pyridines functionalized

with a phenolic ring, with various substituents R para to the hydroxyl group. The photophysical properties of this class of boron containing compounds are described, focusing especially on the correlation between their electronic properties and their fluorescent behavior.

Results and Discussion

Syntheses and characterization

(Imidazo[1,5-a]pyridin-3-yl)phenols ^RIPP were prepared following published methods, ^[47] by condensation of 2-acetylpyridine and the corresponding 5-substituted salicylaldehydes, in the presence of ammonium acetate as a source of the imidazolic nitrogen (Scheme 1). The boron difluoride coordination compounds were obtained by reaction of ^RIPP with boron trifluoride diethyl etherate, in dichloromethane at room temperature, in the presence of triethylamine (Scheme 1). The purity of the products was confirmed by elemental analysis and solution ¹H and ¹³C{¹H} NMR spectroscopy.

Scheme 1. Synthesis of ^RIPP and reaction with boron trifluoride diethyletherate to obtain ^RIPP_BF₂. i) 2-Acetylpyridine:aldehyde:NH₄OAc 1:2:5; AcOH, r.t., 7 days. ii) BF₃·Et₂O, Et₃N, CH₂Cl₂, r.t.

When R = H, a partially hydrated species <code>HIPP_BF2·xH2O</code> was obtained, as also confirmed by the TGA analysis conducted on one batch (Figure S1, Supporting). The water content cannot be exactly quantified since <code>HIPP_BF2·xH2O</code> is indeed a mixture of two products, as resulted from the analysis of X-ray powder spectra (see Figure S2-S3). In diluted solutions <code>HIPP_BF2·xH2O</code> easily loses water and <code>HIPP_BF2</code> is recovered as the only product after removal of the solvent. The purity of the latter was verified by comparison of its X-ray powder diffraction pattern with the one calculated from the CIF file of the related X-ray single crystal structure (vide infra).

¹H NMR spectra of RIPP_BF₂ recorded in CD₂Cl₂ (Figures S4-S35) exhibit as expected several resonances belonging to the aromatic protons between 6.50 and 8.50 ppm, and a singlet between 2.40 and 2.70-ppm ascribed to the methyl group on the imidazolic ring. The corresponding resonances in the ¹³C NMR spectra were identified between 116 and 132 ppm (aromatic CH) and at about 9-10 ppm for the methyl group (Figures S4-S35). The ¹⁹F NMR spectra (CD₂Cl₂, 25°C) exhibit a non-binomial quartet around -140 ppm, with a coupling constant ${}^{1}J_{F-B} \approx 15 \text{ Hz}$ due to the coupling with ¹¹B. The small shoulder appearing downfield from the main resonance was attributed to the resonance of ¹⁹F bound to ¹⁰B (unresolved J-coupling). The possibility that this shoulder could also result from a resonance due to inequivalent fluorine atoms could be ruled out by low temperature experiments: in the ¹⁹F NMR spectrum of ^HIPP_BF₂ recorded at -25°C (Figure S36), this additional shoulder is not visible anymore. Even if there is a general broadening of the resonances, no second resonance that would speak for a rotamer is visible. The ^{11}B NMR spectra (Supporting) exhibit a triplet centered around 0.5-1.0 ppm, with the $^1J_{\text{F-B}}\approx 15$ Hz. The fact that a real triplet and not a doublet of doublet is observed for the ^{11}B NMR resonance fully agrees with the expected tetrahedral geometry at the boron center, confirmed by X-ray crystal structure analysis.

The infrared spectra (ATR) support the NMR data, showing among other a series of bands between 1000 and 1100 cm⁻¹, consistent with the presence of BF₂ derivatives (Figures S37-S45).

X-ray crystal structure analysis

Compounds HPP_BF₂ and OMeIPP_BF₂ were characterized by single-crystal X-ray structure analysis (Figure 1 and Figure S46). As expected, the boron center shows a tetrahedral geometry, with the (imidazo[1,5-a]pyridine-3-yl)phenol entity chelating the boron atom in a N,O-bidentate mode. In the crystal of OMeIPP_BF₂ two independent molecules, labeled A and B, are observed (Figure S46). In both compounds, bond distances and angles are comparable with those reported for similar systems (Table 1). At 1. The structure of the H-derivative shows a nearly planar arrangement between the imidazolyl ring and the phenolic residue, with an angle between these planes of 0.000(4)°. On the other hand, for the methoxy derivative, the same angles measure 20.3(1)° (molecule A) and 18.2(1) (molecule B) respectively, thus revealing a higher degree of distortion from planarity for this IPP-derivative.

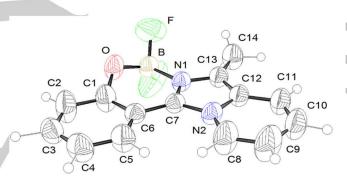


Figure 1. ORTEP representation of ^HIPP_BF₂ at 50% probability level ellipsoids, with atom labeling scheme.

Table 1. Selected bond lengths (Å) and angles (°) for $^{H}IPP_BF_2$ and $^{OMe}IPP_BF_2$ (molecules A and B).

	HIPP_BF2	OMeIPP_BF2 (molecule A) ^[a]	OMeIPP_BF2 (molecule B) ^[a]
B-N(1)	1.578(5)	1.577(8)	1.581(8)
B-O	1.440(6)	1.446(8)	1.440(8)
B-F(1)	1.337(3)	1.393(8)	1.394(7)
B-F(2)	1.337(3)	1.370(7)	1.380(8)
N(1)-B-O	108.5(3)	107.4(5)	107.2(5)
N(1)-B-F(1)	109.3(3)	108.3(5)	109.4(5)
N(1)-B-F(2)	109.3(3)	109.6(5)	109.1(5)
F(1)-B-O	125.3(4)	111.3(5)	108.7(5)
F(2)-B-O	125.3(4)	109.8(5)	112.6(5)
F(1)-B-F(2)	106.8(4)	110.4(5)	109.7(5)

[a] See Supporting (Figure S46).

Optical properties

All RIPP_BF₂ derivatives show an intense fluorescence in solution. First, in order to evaluate any possible solvent effect on the photophysical properties of these compounds, we recorded the absorption, excitation and emission spectra of HIPP_BF₂ in various solvents with different polarity (Table 2).

The absorption spectra show very similar characteristics, with a main absorption at about 345-350 nm and a second one at 235-245 nm (Figure S47, Table 2). The spectra recorded in acetone, N,N-dimethylformamide, ethyl acetate and toluene did not present the second absorption band, due to the strong absorption of the solvent in that range (Figure S47). The excitation spectra largely reproduce the UV-Vis spectra, being comparable with each other as well. The emission spectra are characterized by a broad emission band centered at about 447 nm (Figure S47, Table 1). The emission spectrum recorded in toluene showed a more structured band, due to the vibronic structure. In any case, compound HIPP_BF2 is always characterized by a bright blue fluorescence emission, without experiencing any interesting shifting (range from 441 to 450 nm) of the maxima. In all cases, mono-exponential lifetime decays are observed, with T values in the range of 3.2-4.4 ns (Table 2). Also, fluorescence quantum yields are very similar (Table 2) and no dramatic quenching was observed in these solvents. The other RIPP_BF2 derivatives have a similar behavior, as demonstrated by the absorption and emission spectra recorded in different solvents for MeIPP BF2 and ci**IPP_BF**₂ (Figures S48-S49). Regardless the solvent, for these compounds the emission is always centered respectively at 450 (MeIPP_BF₂) and 438 (CIPP_BF₂) nm. Also, absolute quantum yields and lifetime decays (see Tables S2-S3 in Supporting) are analogous in the various solvents. The only exception in the RIPP_BF₂ series is represented by the NO₂-substitued compound, which indeed shows a significant dependence of the emission from the solvent used (Figure S50 and Table S4). As shown below, the topology of the NTOs describing to the low energy excitation transitions can explain this behavior.

Table 2. Photophysical data for compound HIPP_BF₂ recorded in solution (5·10⁻⁵ M) in different solvents.^[a]

Solvent	λ _{abs}	λ_{exc}	λem	Stokes shift	фрь	т
CH ₂ Cl ₂	347	348	446	0.77	0.21	3.5
acetone	347	352	445	0.74	0.21	3.8
CH₃CN	346	352	445	0.74	0.15	3.9
EtOH	346	347	441	0.76	0.22	3.9
THF	348	348	449	0.80	0.15	4.0
toluene	351	352	450	0.77	0.19	3.8
AcOEt	347	347	446	0.79	0.13	3.7
CHCl₃	348	348	448	0.80	0.11	3.2
DMF	349	353	446	0.73	0.24	4.4

[a] λ_{abs.} λ_{exc}, λ_{em}: nm; Stokes shift: eV; τ: ns.

Based on the aforesaid observations, we continued our investigation on the photophysical properties of ^RIPP_BF₂ compounds in solution using dichloromethane, which represents the best choice in terms of solvent power and photoluminescent performances.

The normalized UV-vis spectra of RIPP_BF2 recorded in solution (CH₂Cl₂, 5·10⁻⁵ M) (Figure S51, Supporting) are characterized by two main absorption bands, respectively centered at about 240 nm and 345-365 nm, depending on the substituent. NO2IPP_BF2 also showed one additional absorption at 307 nm, with lower intensity with respect to the others. The normalized excitation and emission spectra recorded in solution (CH₂Cl₂, 5·10⁻⁵ M) for all RIPP_BF2 derivatives are reported in Figure S52 (Supporting): the excitation spectra largely reproduce the absorption traces; all the emission maxima (Figure 2, Table 3) are positioned in the deep blue region of the visible spectrum (440-463 nm). As documented by the corresponding CIE 1931 plot (Figure S53), (x,y) color coordinates for RIPP BF2 are very close to those expected for standard blue (0.16, 0.10). [49] The only exception is represented by the nitro-substituted derivative NO2IPP BF2, characterized by a λ_{max} centered in the orange region (597 nm) and a second maximum with lower intensity at 445 nm. To clarify the origin of this dual emission we recorded the excitation spectra of both emission bands (Figure S54 in Supporting). They are the same, and this rules out the presence of two different ground states. Thus, as also observed for other fluorescent dual emitters reported in the literature, [50] the dual emission of NO2IPP_BF2 can be described to originate from a ${}^{1}\pi$ - π * (short-wavelength) and ${}^{1}CT$ transitions (long-wavelength). This is consistent with the analysis of Natural Transition Orbitals (vide infra), showing that the longwavelength emission dominates, in accordance with the presence of solvent effect observed for NO2IPP BF2.

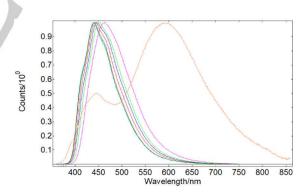


Figure 2. Normalized emission spectra of RIPP_BF₂ compounds recorded in solution (CH₂Cl₂, $5\cdot10^{-5}$ M). Color code: blue (\blacksquare), HIPP_BF₂; green (\blacksquare), MeIPP_BF₂; pink (\blacksquare), MeOIPP_BF₂; red (\blacksquare), FIPP_BF₂; brown (\blacksquare), CIIPP_BF₂; dark green (\blacksquare), BrIPP_BF₂; light blue (\blacksquare), IIPP_BF₂; orange (\blacksquare), NO2IPP_BF₂.

In general, for ^RIPP_BF₂ compounds, λ_{max} is influenced by the substituent R para to the hydroxyl group of the phenolic ring, moving to higher wavelengths with increasing the electron donating character of the substituent (i.e., from 440 for ^BIPP_BF₂ and ^IIPP_BF₂ to 463 for ^{OMe}IPP_BF₂). Worthy of note is the large Stoke shift (0.62-0.80 eV) observed for all ^RIPP_BF₂ compounds __ (Table 3), with a very small superposition between the excitation and the emission spectra. All these compounds showed a fluorescence behavior, with mono-exponential lifetime decays in

FULL PAPER

the range of 3.5-4.1 ns (Table 3 and Figure S55, Supporting). Absolute quantum yields are quite good for almost all the compounds described (Table 3), which is a desired property when combined with large Stokes shift, since the latter are often associated with a lower emission efficiency. [51] The lower quantum yields are observed as expected for NO2IPP_BF2, due to the known quenching effect of nitro groups, [52] and IPP_BF2, this last reasonably experiencing a heavy-atom effect. IPP_BF2 also showed the shortest lifetime decay of just 1.5 ns (Table 3); on the other hand, NO2IPP_BF2 was the only derivative showing a biexponential lifetime decay, with a weighted value of 1.2 ns (Table 3).

A requested feature for dyes to be used in energy-efficiency devices is a good optical stability. Therefore, we performed photostability measurements in dichloromethane solution for compound $^{\text{H}}\text{IPP_BF}_2$, taken again as a representative example of the whole series. A multiple emission scan analysis (Figure S56) was performed over a period of two hours (100 scans, 72 seconds each scan with no delay between scans). No significative loss in the emission intensity was detected ($\Delta_{\text{scan1-scan100}}$ = ca. 0.84%) (Figure S57).

Table 3. Photophysical data for boron difluoride compounds RIPP_BF_2 in dichloromethane solution (5·10⁻⁵ M). $^{[a]}$

R	λ_{abs}	ε	λ_{exc}	λ_{em}	Shift	ф _{PL}	Т	k r	k nr
Н	347	17580	348	446	0.77	0.21	3.5	6.2	2.2
Ме	352	18710	351	452	0.79	0.19	3.5	5.4	2.3
OMe	362	17320	365	463	0.72	0.16	3.7	4.3	2.3
F	357	15950	356	443	0.68	0.22	3.5	6.2	2.2
CI	358	13510	356	442	0.68	0.23	4.1	5.6	1.9
Br	358	16890	357	440	0.66	0.22	4.1	5.4	1.9
1	359	15750	361	440	0.62	0.09	1.5	6.2	6.2
NO_2	350	7310	356	597	0.80	<0.05	1.2 [[]	- \	. 7

[a] λ_{abs} , λ_{exc} , λ_{em} : nm; ϵ : M⁻¹·cm⁻¹; Stokes shift: eV; τ : ns; k_r : ·10⁷ s⁻¹; k_m : ·10⁸ s⁻¹. [b] Biexponential decay, weighted average between τ_1 = 1.1 ns (relative percentage 95%) and τ_2 = 3.0 ns (relative percentage 5%).

DFT calculations

The X-ray crystal structure of compound $^{\text{H}}\text{IPP_BF}_2$ was used as the starting point to obtain the ground state (S₀) optimized geometries of all $^{\text{R}}\text{IPP_BF}_2$ derivatives at the DFT/PBE-D3 level of theory. Calculated and experimental (X-ray) bond distances and angles for $^{\text{H}}\text{TIPP_BF}_2$ and $^{\text{OMe}}\text{TIPP_BF}_2$ are in good agreement. TD-DFT calculations were also useful to determine the nature of the transitions responsible for the absorption processes. Figure 3 proves the good accordance between the

calculated (dashed line) and the experimental (full line) UV-vis spectra in solution (CH_2Cl_2) both for HIPP_BF_2 and $^{NO2}IPP_BF_2$. Vertical bars represent calculated transitions with oscillator strength f > 0.1. The contributions of single orbital transitions to the absorption at lower energy are reported in Table 4.

For HIPP_BF2 and nearly all other RIPP_BF2 compounds, the absorption centered at about 350 nm is composed of two electronic transitions (Figure 3, (a)), mainly having a HOMO-LUMO (81.3% of first transition) or HOMO-LUMO+1 (83.5% of second transition) character. Compound NO2IPP_BF2 is characterized by a different UV-vis spectrum (Figure 3, (b)), where three calculated transitions are observed in the range 330-350 nm, mostly described as HOMO-LUMO (98.0%), HOMO-LUMO+1 (93.2%) and HOMO-LUMO+2 (89.7%) (Table 4). These contributions to single orbital transitions are associated to Natural Transition Orbitals (NTOs) reported in Figure 4 (see Figures S58-S59 for NTOs for all RIPP BF2). They show similar shapes among the RIPP BF2 series (R = H, Me, OMe, F, C, Br, I), with occupied NTOs (red contour) distributed over the entire molecule (NTO1 and NTO2), and the virtual NTOs (green contour) mainly localized on the imidazo[1,5-a]pyridine portion (as expected acting as the acceptor moiety) (NTO1) or also involving the phenol residue (NTO2). In NO2IPP BF2, all occupied NTOs are spread over the entire imidazo[1,5-a]pyridine phenol system, whereas virtual NTOs are localized on the phenol ring (NTO1) or on the entire molecule (NTO2 and NTO3). In all cases, no contribution is observed from the BF2 fragment, which ultimately enhances the _ fluorescence of the free (imidazo[1,5-a]pyridine-3-yl)phenols by giving more rigidity to the whole system.

In conclusion, the lower energy absorption band in $^{R}IPP_BF_2$ (R = H, Me, OMe, F, Cl, Br, I) is due to the contribution of two close vertical transitions, the first with a clear (highlighted by NTO1) and the second with a negligible (highlighted by NTO2) charge transfer character. Plausibly, the latter transition dominates in accordance with the absence of solvent effect experimentally observed. On the contrary, for $^{NO2}IPP_BF_2$ the lower energy absorption band is due only to a single 1CT transition (evidenced by NTO1), thus explaining the solvent dependence

Table 4. Contributions of single orbital transitions for HIPP_BF2 and NO2IPP_BF2.

RIPP_BF2	NTOs		
HIPP_BF2	NTO1	HOMO → LUMO	81.3%
_		HOMO-1 → LUMO	7.5%
		HOMO → LUMO +1	5.3%
		HOMO-2 → LUMO+1	1.3%
	NTO2	HOMO → LUMO+1	83.5%
		HOMO → LUMO	8.1%
		HOMO-1 → LUMO	2.1%
		HOMO-1 → LUMO+1	2.0%
		HOMO → LUMO+2	1.3%
NO2IPP_BF2	NTO1	HOMO → LUMO+1	98.0%
		HOMO-1 → LUMO	1.5%
	NTO2	$HOMO \to LUMO$	93.2%
		HOMO-1 → LUMO	3.5%
		$HOMO-3 \rightarrow LUMO+2$	1.1%
	NTO3	HOMO → LUMO+2	89.7%

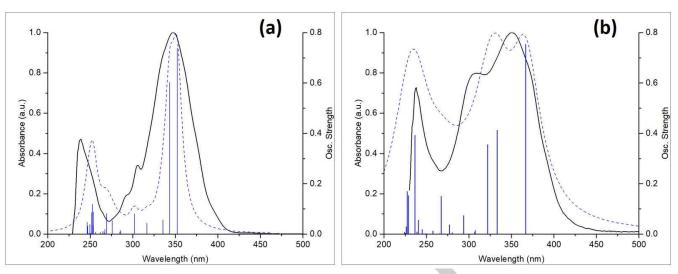


Figure 3. Calculated (dashed line) vs. experimental (full line) UV-vis traces in dichloromethane solution: (a) HIPP_BF₂, (b) NO2IPP_BF₂.

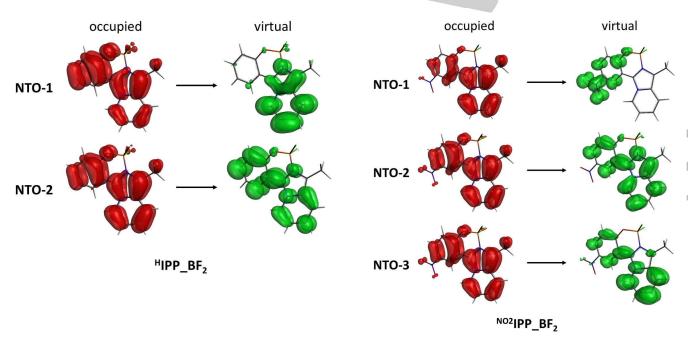


Figure 4. Natural Transition Orbitals (NTOs) calculated for compounds HPP_BF2 and NO2IPP_BF2 relative to the first (NTO-1), second (NTO-2) and (for NO2IPP_BF2) third (NTO-3) low energy transitions (see text).

We then performed geometry optimization of the S_1 excited state for R IPP_BF₂: worthy of note, the computed structures for S_1 match those of S_0 , with only very slight deviations (Figure S60). The Electron Difference Density Map (EDDM) computed at TDDFT level are very similar among the series (Figure 5): the electron density mainly moves from the phenolic residue to the imidazo-pyridine ring for all R IPP_BF₂ except for NO2 IPP_BF₂, where a more distinct charge separation is observed, with electron density transferred from the nitrogen heterocycle to phenol. Figure 5 reports the EDDM for H IPP_BF₂ and NO2 IPP_BF₂, whereas EDDM for all R IPP_BF₂ compounds are collected in Figure S61. These results support the conclusions based on NTOs shapes, once more underlying the different behavior of NO2 IPP_BF₂ when compared to the other R IPP_BF₂ and explain

its distinct emission (i.e., blue for most ${}^R IPP_BF_2$, orange for ${}^{NO2} IPP_BF_2$).

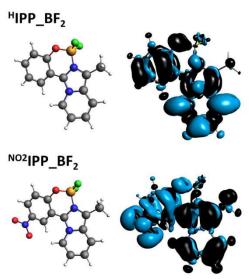


Figure 5. Electron Difference Density Maps (EDDM) for the lowest energy singlet electronic transition computed by TDDFT (black indicates a decrease in electron density, blue indicates an increase).

According to the contributions of single orbital transitions reported in Table 4, the higher percentages of contributions are associated to either HOMO-LUMO or HOMO-LUMO+1 transitions Table 5 collects the calculated HOMO, LUMO and LUMO+1 energies for RIPP_BF2 compounds: as expected, the introduction of an electron donor substituent like Me or OMe enhances the HOMO energy, whereas halogens lead to the opposite direction. The decrease in HOMO energy is even more dramatic for the nitro derivative. The LUMO energies follow the same trend, increasing with donor substituents and decreasing after introduction of halogens and NO2. Worthy of note, the HOMO-LUMO energy gap is maintained quite constant over the series, ranging from 2.087 (OMeIPP_BF2) to 2.472 eV (CIIPP BF2).

We then decided to search for a possible correlation between the electronic properties of RIPP BF2 compounds and the calculated HOMO, LUMO and LUMO+1 energies, which are in turn related to the emissive properties. As reported in Figure S62 (Supporting) LUMO+1 energies are related by a linear relationship to LUMO energies for all RIPP_BF2 derivatives. Thus, HOMO-LUMO energy gap can be used in the studied correlations, since it describes also contributions from LUMO+1. We chose σ_p Hammett constants of the substituent R as the best descriptor of its electronic features. When correlated to σ_p , HOMO and LUMO energies follow a linear trend, with the energy of both frontier orbitals decreasing in the presence of electron-withdrawing substituents (namely, with increasing σ_p). Worthy of note, irrespective of σ_p (i.e., the electronic character of R), the HOMO/LUMO energy gap is maintained almost constant over the whole series (Figure 6, Table 5), including NO2IPP_BF2. Thus, as previously discussed, the origin of its different emission is ascribed to the diverse electronic transitions due to the different topology of NTOs involved.

Table 5. Calculated HOMO, LUMO and LUMO+1 energies (eV) and HOMO-LUMO energy gap for RIPP_BF₂.

RIPP_BF2	Номо	Lимо	Lumo+1	$\Delta_{\text{H-L}}$	σ_{p}
HIPP_BF2	-5.339	-2.976	-2.305	2.363	0
MeIPP_BF2	-5.228	-2.940	-2.287	2.288	-0.17
OMeIPP_BF2	-5.048	-2.961	-2.321	2.087	-0.27
FIPP_BF2	-5.402	-3.082	-2.410	2.320	0.06
CIPP_BF2	-5.414	-3.098	-2.396	2.316	0.18
BrIPP_BF2	-5.445	-3.114	-2.416	2.330	0.23
'IPP_BF₂	-5.434	-3.105	-2.414	2.472	0.23
NO2IPP_BF ₂	-5.860	-3.541	-3.060	2.319	0.78

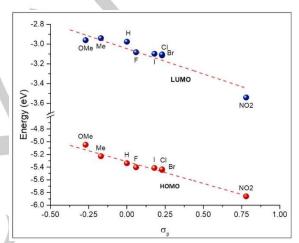


Figure 6. HOMO (red) and LUMO (blue) energies of ^RIPP_BF₂ vs Hammet's σ_p of substituent R. Linear fit: R² = 0.916 and 0.967 respectively for LUMO and HOMO.

Conclusion

In this work we presented the synthesis, the characterization, and the study of the photophysical properties of a series of (imidazo[1,5-a]pyridine-3-yl)phenols functionalized with the BF2 fragment. The series was obtained by changing substituent R para to the hydroxyl group on the phenolic ring. Nearly all these compounds show a blue fluorescence emission, with large Stokes shifts, good absolute quantum yields as well as excellent photostability in solution. TDDFT calculations performed on both S₀ and S₁ allowed to explain the different emissive properties (i.e., solvent effect) of the NO2-substituted derivative compared to the other compounds of the series. The main electronic transitions were then defined as ¹ILT for ^RIPP_BF₂ and ¹CT for ^{NO2}IPP_BF₂. The emission of our compounds has also been correlated to the electronic properties of the substituent R on the phenolic ring, leading to a linear correlation between R Hammett constant (σ_p) and the HOMO-LUMO energy gap. This study proves the possibility to use imidazo[1,5-a]pyridine phenols as N,O ligands toward BF2 fragment, thus expanding the scope of emissive boron containing compounds.

FULL PAPER

Due to their good optical properties, especially their high Stoke shifts and photostability, we believe that these compounds constitute an interesting class of blue-emissive dyes. Furthermore, the possibility to functionalize these molecules by changing the substituent R according to the desired properties (such as solubility in water, or addition of long alkyl chains), while maintaining the intense blue fluorescence, suggests that these compounds can be an interesting alternative for producing cheap blue-emissive dyes.

Experimental Section

General procedure for the synthesis of boron difluoride compounds ${}^{R}\mathsf{IPP_BF}_2$

(imidazo[1,5-a]pyridine-3-yl)phenol R IPP (1 g, 1 eq) was suspended in 6 mL of deoxygenated dichloromethane, then BF₃·Et₂O (2.5 eq), diluted in 1-2 mL of deoxygenated CH₂Cl₂, was added dropwise. Finally, Et₃N (1.2 eq) was added. An exothermic reaction occurred, leading to the formation of a dark red solution, which was stirred at room temperature for a time varying from 30 minutes to 2 hours. During this time, precipitation of a solid occurred, which was filtered by suction filtration and washed with a small amount of cold dichloromethane, then dried in vacuo to give a crude solid. This was dissolved in few millililiters of dichloromethane (max 5 mL) and the solution was filtered over a pad of silica gel to remove the last traces of Et₃NHF. The solvent was then removed under reduced pressure to give the pure product.

CCDC-2076375 (HIPP_BF₂) and 2076376 (OMeIPP_BF₂) contain the supplementary crystallographic data for this paper. These data are provided free of charge by the joint Cambridge Crystallographic Data Centre and Fachinformationszentrum Karlsruhe Access Structures service https://www.ccdc.cam.ac.uk/structures

Acknowledgements


GC thanks the Ministero dell'Università e della Ricerca (MIUR) and the University of Insubria for partial funding. SB and GAA greatly acknowledge Fondazione Banca del Monte di Lombardia (FBML) for generous funding through the Research Project "Transiton-metals based coordination compounds for light emitting device applications".

Keywords: Boron • Blue emission • fluorescence • HOMO-LUMO gap • TD-DFT

- [1] G. M. Farinola, R. Ragni, Chem. Soc. Rev. 2011, 40, 3467-3482.
- [2] R. D. Costa, E. Ortì, H. J. Bolink, F. Monti, G. Accorsi, N. Armaroli, Angew. Chem., Int. Ed. 2012, 51, 8178–8211; Angew. Chem. 2012, 124, 8300-8334.
- [3] M. Grätzel, Acc. Chem. Res. 2009, 42, 1788-1798.
- [4] a) K. M.-C. Wong, M. M.-Y. Chan, V. W.-W. Yam, Adv. Mater. 2014, 26, 5558–5568;
 b) D.-L. Ma, V. P.-Y. Ma, D. S.-H. Chan, K.-H. Leung, H.-Z. He, C.-H. Leung, Coord. Chem. Rev. 2012, 256, 3087–3113.
- [5] J. A. G. Williams, S. Develay, D. L. Rochester, L. Murphy, Coord. Chem. Rev. 2008, 252, 2596–2611.
- [6] Y. You, W. Nam, Chem. Soc. Rev. 2012, 41, 7061–7084.
- [7] M. W. Cooke, M.-P. Santoni, B. Hasenknopf, G. S. Hanan, *Dalton Trans*. 2016, 45, 17850–17858.
- [8] C. B. Larsen, H. van der Salm, G. E. Shillito, N. T. Lucas, K. C. Gordon, Inorg. Chem. 2016, 55, 8446–8458.

- [9] M. Al-Eid, S. Lim, K. Park, B. Fitzpatrick, C. Han, K. Kwak, J. Hong, G. Cooke, *Dyes and Pigments* 2014, 104, 197–203.
- [10] Y.-L. Song, B.-J. Jiao, C.-M. Liu, X.-L. Peng, M.-M. Wang, Y. Yang, B. Zhang, C.-X. Du, *Inorg. Chem. Commun.* 2020, 112, 107689.
- [11] A. Gusev, E. Braga, Y. Baluda, M. Kiskin, M. Kryukova, N. Karaush-Karmazin, G. Baryshnikov, A. Kuklin, B. Minaev, H. Ågren, W. Linert, *Polyhedron* 2020, 191, 114768.
- [12] G. Volpi, E. Priola, C. Garino, A. Daolio, R. Rabezzana, P. Benzi, A. Giordana, E. Diana, R. Gobetto, *Inorg. Chim. Acta* 2020, 509, 119662.
- 13] U. Balijapalli, S. K. Iyer, Eur. J. Org. Chem. 2015, 23, 5089–5098.
- [14] R. Deng, L. Li, M. Song, S. Zhao, L. Zhou, S. Yao, CrystEngComm 2016, 18, 4382-4387.
- [15] A. John, M. Bolte, H.-W. Lerner, G. Meng, S. Wang, T. Peng, M. Wagner, J. Mater. Chem. C 2018, 6, 10881-10887.
- [16] A. Bessette, G. S. Hanan, Chem. Soc. Rev. 2014, 43, 3342-3405.
- [17] T. Kowada, H. Maeda, K. Kikuchi, Chem. Soc. Rev. 2015, 44, 4953-4972.
- 18] J. Bañuelos, Chem. Rec. 2016, 16, 335-348.
- [19] G. Li, Y. Otsuka, T. Matsumiya, T. Suzuki, J. Li, M. Takahashi, K. Yamada, Materials 2018, 11, 1297.
- [20] J. Tao, D. Sun, L. Sun, Z. Li, B. Fu, J. Liu, L. Zhang, S. Wang, Y. Fang, H. Xu, *Dyes and Pigments* 2019, 168, 166–174.
- [21] S. Swavey, J. Quinn, M. Coladipietro, K. G. Cox, M. K. Brennaman, RSC Adv. 2017, 7, 173-179.
- [22] B. Hinkeldey, A. Schmitt, G. Jung, ChemPhysChem 2008, 9, 2019–2027.
- [23] L. Yang, R. Simionescu, A. Lough, H. Yan, *Dyes and Pigments* 2011, 91, 264-267.
- [24] S. L. Niu, G. Ulrich, R. Ziessel, A. Kiss, P. Renard, A. Romieu, Org. Lett. 2009, 11, 2049-2052.
- [25] a) Y. Kubota, T. Tsuzuki, K. Funabiki, M. Ebihara, M. Matsui, *Org. Lett.* 2010, 12, 4010-4013; b) Q-D. Liu, M. S. Mudadu, R. Thummel, Y. Tao,
 S. Wang, *Adv. Funct. Mater.* 2005, 15, 143-154.
- [26] a) C. A. M. Salla, J. Teixeira dos Santos, G. Farias, A. J. Bortoluzi, S. F. Curcio, T. Cazati, R. Izsák, F. Neese, B. de Souza, I. H. Bechtold, *Eur. J. Inorg. Chem.* 2019, 2247-2257; b) M. Santra, H. Moon, M-H. Park, T-W. Lee, Y. K. Kim, K. H. Ahn, *Chem. Eur. J.* 2012, *18*, 9886-9893.
- [27] a) A. Kamal, G. Ramakrishna, P. Raju, A. V. Subba Rao, A. Viswanath, V. Lakshma Nayak, S. Ramakrishna, Eur. J. Med. Chem. 2011, 46, 2427–2435; b) C. Hamdouchi, J. D. Blas, M. D. Prado, J. Gruber, B. A. Heinz, V. J. Vance, J. Med. Chem. 1999, 42, 50-59.
- [28] E. Yamaguchi, F. Shibahara, T. Murai, J. Org. Chem. 2011, 76, 6146–6158.
- [29] G. Volpi, G. Magnano, I. Benesperi, D. Saccone, E. Priola, V. Gianotti, M. Milanesio, E. Conterosito, C. Barolo, G. Viscardi, *Dyes and Pigments* 2017, 137, 152–164.
- a) S. Chen, H. Li, P. Hou, Anal. Chim. Acta 2017, 993, 63–70; b) S. Chen,
 P. Hou, J. Wang, S. Fu, L. Liu, Anal. Biol. Chem. 2018, 410, 4323–4330.
- [31] L. Salassa, A. Albertino, C. Garino, G. Volpi, C. Nervi, R. Gobetto, K. I. Hardcastle, Organometallics 2008, 27, 1427–1435.
- [32] C. Garino, T. Ruiu, L. Salassa, A. Albertino, G. Volpi, C. Nervi, R. Gobetto, K. I. Hardcastle, Eur. J. Inorg. Chem. 2008, 23, 3587–3591.
- [33] M. D. Weber, C. Garino, G. Volpi, E. Casamassa, M. Milanesio, C. Barolo, R. D. Costa, *Dalton Trans.* 2016, 45, 8984–8993.
- [34] N. Kundu, S. M. Towsif Abtab, S. Kundu, A. Endo, S. J. Teat, M. Chaudhury, *Inorg. Chem.* 2012, 51, 2652–2661.
- [35] A. L. Guckian, M. Doering, M. Ciesielski, O. Walter, J. Hjelm, N. M. O'Boyle, W. Henry, W. R. Browne, J. J. McGarvey, J. G. Vos, *Dalton Trans.* 2004, 23, 3943–3949.
- [36] M. Nakatsuka, T. Shimamura, Chem. Abstr. 2001, 134, 170632. Jpn. Kokai Tokkyo JP 2001035664, 2001.
- [37] T. Tominaga, T. Kohama, A. Takano, Chem. Abstr. 2001, 134, 93136.
 Jpn. Kokai Tokkyo JP 2001006877, 2001.
- [38] D. Kitasawa, T. Tominaga, A. Takano, Chem. Abstr. 2001, 134, 200276.
 Jpn. Kokai Tokkyo JP 2001057292, 2001.
- [39] G. A. Ardizzoia, S. Brenna, S. Durini, B. Therrien, *Polyhedron* 2015, 90, 214–220.
- [40] G. A. Ardizzoia, S. Brenna, S. Durini, B. Therrien, M. Veronelli, Eur. J. Inorg. Chem. 2014, 26, 4310–4319.
- [41] G. A. Ardizzoia, G. Colombo, B. Therrien, S. Brenna, Eur. J. Inorg. Chem. 2019, 13, 1825–1831.

- S. Durini, G. A. Ardizzoia, B. Therrien, S. Brenna, New J. Chem. 2017, 41. 3006-3014.
- A. Marchesi, S. Brenna, G. A. Ardizzoia, Dyes and Pigments 2019, 161, 457-463.
- T. Murai, E. Nagaya, K. Miyahara, F. Shibahara, T. Maruyama, Chem. Lett. 2013 42, 828830.
- [45] F. Yagishita, T. Kinouchi, K. Hoshi, Y. Tezuka, Y. Jibu, T. Karatsu, N. Uemura, Y. Yoshida, T. Mino, M. Sakamoto, Y. Kawamura, Tetrahedron 2018. 74. 3728-3733.
- G. Colombo, A. Romeo, G. A. Ardizzoia, J. Furrer, B. Therrien, S. Brenna, Dyes and Pigments 2020, 182, 108636.
- G. A. Ardizzoia, D. Ghiotti, B. Therrien, S. Brenna, Inorg. Chim. Acta **2018**, 471, 384-390.
- [48] synthesis soon loses water in solution and this occurs also during the crystallization process. Thus, every attempt to grow single crystals of
- [49] J.-H. Kim, S.-Y. Kim, S. Choi, H.-J. Son, S. O. Kang, Inorg. Chem. 2021, 60, 246-262.
- [50] B. H. Jhun, D. Y. Jeong, S. Nah, S. Y. Park, Y. You, J. Mater. Chem. C **2021**, 9, 7083-7093.
- [51] E. A. Savicheva, J. Seikowski, J. I. Kast, C. R. Grünig, V. N. Belov, S. W. Hell, Angew. Chem. Int. Ed. 2021, 60, 3720-3726; Angew. Chem. 2021,
- [52] 2013, 42, 2921-2929.

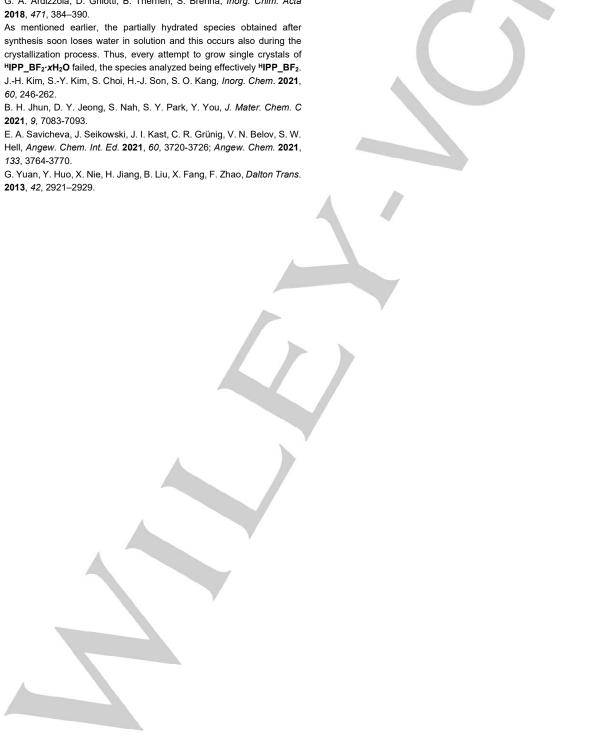

FULL PAPER

Entry for the Table of Contents



Blue emissive materials: boron containing fluorescent compounds have been prepared starting from imidazo[1,5-a]pyridine phenols. Large Stokes shift, high absolute quantum yields and good photostability are observed in solution. TD-DFT calculations allowed to find a linear correlation between the HOMO-LUMO energy gap of these compounds and the Hammett constants of substituents R para to the hydroxyl group of the phenols.

Institute and/or researcher Twitter usernames: https://twitter.com/Uni-Insubria