



Carbon-14 release and speciation during corrosion of irradiated steel under radioactive waste disposal conditions



Typhaine Guillemot^{a,1}, Gary Salazar^b, Martin Rauber^b, Dominik Kunz^a, Sönke Szidat^b, Erich Wieland^{a,*}


^a Paul Scherrer Institute, Laboratory for Waste Management, 5232 Villigen PSI, Switzerland

^b University of Bern, Department of Chemistry, Biochemistry and Pharmaceutical Sciences & Oeschger Centre for Climate Change Research, 3012 Bern, Switzerland

HIGHLIGHTS

- Radiocarbon is released during corrosion of irradiated steel in a deep geological repository.
- Speciation of radiocarbon determines its pathways of migration into the environment.
- ¹⁴C-bearing carboxylates and carbonate are released in the first stage of corrosion.
- ¹⁴C-bearing methane is the main gaseous ¹⁴C carrier.
- The largest portion of the ¹⁴C inventory in irradiated steel is released in the gaseous form.

GRAPHICAL ABSTRACT

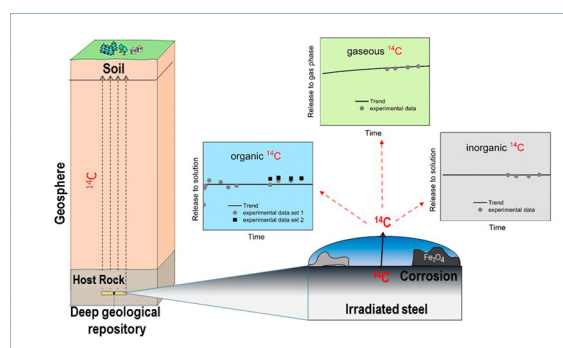

ARTICLE INFO

Article history:

Received 17 November 2021

Received in revised form 17 December 2021

Accepted 17 December 2021

Available online 25 December 2021

Editor: Frederic Coulon

Keywords:

Radiocarbon

Accelerator mass spectrometry

Compound-specific radiocarbon analysis

Corrosion

Irradiated steel

Radioactive waste

ABSTRACT

Carbon-14 is a key radionuclide in the safety assessment of deep geological repositories (DGR) for low- and intermediate-level radioactive waste (L/ILW). Irradiated metallic wastes generated during the decommissioning of nuclear power plants are an important source of ¹⁴C after their disposal in a DGR. The chemical form of ¹⁴C released from the irradiated metallic wastes determines the pathway of migration from the DGR into the environment. In a long-term corrosion experiment with irradiated steel simulating the hyper-alkaline, anoxic conditions of a cement-based DGR, total inorganic (TI¹⁴C) and organic (¹⁴C) contents (TO¹⁴C) in the liquid and gas phases (TG¹⁴C), as well as individual ¹⁴C-bearing carbon compounds by compound-specific radiocarbon analysis (CSRA), were quantified using accelerator mass spectrometry (AMS). The AMS-based quantification allows the determination of ¹⁴C in the pico- to femtomolar concentration range. An initial increase in TO¹⁴C was observed, which could be attributed partially to the release of ¹⁴C-bearing oxygenated carbon compounds. In the long term, TO¹⁴C and the TI¹⁴C remain constant, while TG¹⁴C increases over time according to a corrosion rate of steel of 1 nm/yr. In solution, ¹⁴C-bearing carboxylic acids (CAs) contribute ~40% to TO¹⁴C, and they are the main ¹⁴C carriers along with ¹⁴C-bearing carbonate (¹⁴CO₃²⁻). The remaining fraction of TO¹⁴C (~60%) is likely due to the presence of as yet non-identified polymeric or colloidal organic material. In the gas phase, ¹⁴CH₄ accounts for more than 80% of the TG¹⁴C, while only trace amounts of ¹⁴CO, and other small ¹⁴C-bearing hydrocarbons have been detected. In a DGR, the release of ¹⁴C will be mainly in gaseous form and migrate via the gas pathway from the repository near field to the surrounding host rock and eventually to the environment.

* Corresponding author.

E-mail address: erich.wieland@psi.ch (E. Wieland).

¹ present address: Swiss National Cooperative for the Disposal of Radioactive Waste (Nagra), 5430 Wettingen, Switzerland

² TI¹⁴C: Total inorganic ¹⁴C; TO¹⁴C: total organic ¹⁴C; TG¹⁴C: total gaseous ¹⁴C

1. Introduction

Carbon-14 (^{14}C) is a key radionuclide in the safety analysis of deep geological repositories (DGR) for radioactive waste and near-surface facilities (e.g., Nuclear Decommissioning Authority, 2012; Johnson and Schwyn, 2008; Yim and Caron, 2006). Radiological assessments have shown that ^{14}C is an important dose-contributing radionuclide due to its long half-life (5700 years), the high mobility of gaseous and aqueous ^{14}C -bearing carbon compounds in the DGR and in the geosphere due to their weak interaction with mineral surfaces under near-neutral to alkaline conditions, and the fact that ^{14}C can be taken up into the human food chain. The Swiss concept for the safe disposal of radioactive waste envisages the storage of low- and intermediate-level waste (L/ILW) in a cement-based DGR at a suitable depth (few hundred meters below the surface) in the Opalinus Clay formation (Nagra, 2014a, 2016). The chemical form of the ^{14}C -bearing carbon species determines the pathway of ^{14}C migration in the engineered barrier system (EBS) of the DGR and the surrounding host rock, and is therefore responsible for the long-term contribution of ^{14}C to dose release from the repository (Johnson and Schwyn, 2008; Yim and Caron, 2006). ^{14}C decays if it can be retained in the EBS of the DGR for a sufficiently long time, while radiological consequences may arise when ^{14}C is released in the organic and especially gaseous form. Therefore, knowledge of the ^{14}C species produced during corrosion of irradiated metals is of paramount importance to evaluate the time dependence of ^{14}C release and its dose contribution over the period relevant to a DGR.

The Swiss Model Activity Inventory (MIRAM) identified irradiated steel as the main source of ^{14}C in the existing and future arising L/ILW (~ 75%) (Nagra, 2014b). ^{14}C in irradiated steel is primarily produced by the activation of nitrogen impurities contained in fuel assembly components and components of the core structural materials of light water reactors, as a consequence of the $^{14}\text{N}(n,p)^{14}\text{C}$ nuclear reaction. The release of ^{14}C occurs during the corrosion of irradiated steel components in the DGR. Very little information is available on the chemical form of ^{14}C during corrosion under strongly alkaline anoxic conditions relevant to a cement-based DGR (de Visser-Týnová et al., 2018; Swanton et al., 2015; Wieland and Hummel, 2015 and references therein). Both oxidized and reduced carbon compounds with a small number of carbon atoms (generally between C1 and C5) have been detected in corroding, non-irradiated iron-water systems in these conditions (Cvetković et al., 2018a; Guillemot et al., 2020a; Wieland and Hummel, 2015). Furthermore, a recent corrosion study using irradiated steel identified dissolved and gaseous ^{14}C -bearing small carbon compounds (de Visser-Týnová et al., 2018). In the present study on the corrosion of irradiated steel, we developed analytical methods that allow both oxidized and reduced ^{14}C -bearing carbon compounds to be identified and quantified at ultra-low concentrations in both the liquid and gas phases by accelerator mass spectrometry (AMS) (Cvetković et al., 2018b; Cvetković et al., 2018c; Guillemot et al., 2020b). The extremely low ^{14}C concentrations expected in this corrosion experiment are a consequence of the small size and low ^{14}C content of the irradiated steel samples, the extremely slow corrosion of stainless steel under alkaline anoxic conditions, and finally the small sample quantities available for analysis with the given experimental set-up. The AMS-based analytics allowed quantification of total ^{14}C contents in the solution and gas phase and identification of individual ^{14}C -bearing carbon compounds by compound-specific radiocarbon analysis (CSRA).

2. Materials and methods

2.1. Solutions and chemicals

All standard solutions were prepared using chemicals with high purity grade (> 98%) from Sigma-Aldrich (Buchs, Switzerland), Alfa Aesar (Karlsruhe, Germany) and Merck analytical grade ("pro analysis") (Hohenbrunn, Germany). Ultrapure (deionized, de-carbonated) water (MilliQ® water; 18.2 M Ω -cm resistivity), generated by a MilliQ Gradient A10 purification system (Millipore, USA), was used to prepare solutions and sample

dilutions. Degassed water was obtained by boiling ultrapure water for 2 h under continuous N₂ purge. The O₂ concentration (< 1 ppb) was controlled using a PreSens PST6 planar oxygen sensor (Regensburg, Germany). An artificial cement pore water (ACW) with pH 12.5, used to simulate pore water conditions in the near field of a cement-based DGR and corresponding to a solution saturated w.r.t. Ca(OH)₂, was prepared as reported elsewhere (Cvetković et al., 2018c).

2.2. Irradiated steel

Two small specimens of irradiated stainless steel with a total mass of 1.718 g, a dose rate of ~20 mSv/h per gram of steel, and a total surface area of 11.15 cm² were used for the corrosion experiment (Schumann et al., 2014; Wieland et al., 2018; Wieland et al., 2017). The type of the stainless steel used to fabricate the guide-tube nuts is not exactly known, while there is information from the manufacturer to suggest that the nuts were produced from one of the following alloys: X6CrNiTi18–10 (1.4541), X6CrNiNb18–10 (1.4550) or X6CrNiMoTi17–12–2 (1.4571). The small samples used for the corrosion experiment were prepared from an irradiated steel nut exposed to a thermal neutron flux for two years during operation at the nuclear power plant Gösgen (Switzerland) (Wieland et al., 2017). The thickness of the oxide layer of the irradiated steel samples was not determined experimentally prior to the corrosion experiment. However, based on ample evidence presented in the literature (e.g., Chimi et al., 2016; Hanbury and Was, 2019; Raiman and Was, 2017; Sakuragi et al., 2016; Was, 2017; Zhao et al., 2021), it is safe to assume that a few tenths to few hundred nanometer thick oxide layer had formed during irradiation in the nuclear reactor.

^{14}C is expected to be mainly produced by the activation of ^{14}N impurities in the irradiated bulk metal matrix. It is conceivable that in the oxide layer the conversion of ^{17}O according to the nuclear reaction $^{17}\text{O}(n,\alpha)^{14}\text{C}$ was an additional source of ^{14}C . However, the amount of ^{14}C resulting from ^{17}O conversion is expected to be much lower than the ^{14}C released during the corrosion of the bulk metal due to the much lower isotopic abundance of ^{17}O (0.038%) compared to ^{14}N (99.632%) and the much lower thermal neutron cross section of ^{17}O (0.235) compared to ^{14}N (1.82). The ^{14}C content of the irradiated steel nut was determined to be 17.8 ± 2.1 kBq/g (corresponding to 0.107 ± 0.012 μg ^{14}C /g) using a digestion procedure in oxidative media and ^{14}C quantification by liquid scintillation counting (LSC) (Schumann et al., 2014).

2.3. Reactor

The experimental set-up consists of a gas-tight overpressure reactor (stirred autoclave type "Versoclave Type 3", Büchi AG, Uster, Switzerland) surrounded by a 10-cm-thick lead shielding (Wieland et al., 2018; Wieland et al., 2017) (Supplementary Information (S.I.) Fig. S1-1). Before starting the corrosion experiment, tests of the background ^{14}C activity and the concentrations of carbon compounds were carried out (Cvetković et al., 2018c) (S.I. S2). For the experiment, two specimens of irradiated steel were mounted to a sample holder connected to a stirring device in the reactor. The reactor was tightly sealed and purged with N₂ to ensure O₂-free conditions. A volume of 300 mL ACW was injected via the in-house developed sampling system located outside the lead shielding (Cvetković et al., 2018c; Wieland et al., 2018; Wieland et al., 2017). After one day, the solution was replaced with a fresh one and the experiment started (Cvetković et al., 2018c). The ^{14}C background of the injected ACW solution was monitored over time (S.I. Table S2–1).

2.4. Samplings

Liquid and gas phase samples were collected on days 1, 14, 28, 92, 286, 412, 552, 1114, 1252, 1462 and 1637 (S.I. Table S3–1). Each time, approximately 7 mL solution and 50 mL gas were collected in separate sampling tubes as reported elsewhere (Cvetković et al., 2018c). After sampling, 7 mL of O₂-free ACW and N₂ were immediately injected into the reactor

to maintain similar conditions throughout the experiment (i.e. ~ 300 mL solution and ~ 5 bar pressure with N₂ atmosphere). During sampling, pressure, temperature and dissolved O₂ concentration were constantly monitored to verify gas-tightness of the reactor (Wieland et al., 2018; Wieland et al., 2017) (S.I. Table S3–1).

2.5. Analytical methods

2.5.1. Total inorganic and organic ¹⁴C contents of the liquid phase

The total organic ¹⁴C content (TO¹⁴C) was determined in three different ways: directly in the sampled solution (i.e. d-TO¹⁴C); after pre-treatment of the solution with an Ag/Ba/H cartridge (OnGuard cartridges, Dionex, Sunnyvale, CA, USA) (i.e. p-TO¹⁴C), and as the sum of the concentrations of all organic ¹⁴C-bearing carbon compounds identified and quantified. The total inorganic ¹⁴C content (TI¹⁴C), p- and d-TO¹⁴C were determined by wet oxidation (WO) as described elsewhere (Guillemot et al., 2021; Rauber, 2018). Briefly, 3 × 1.25 mL (on sampling day 1114) or 3 × 0.125 mL (starting from sampling day 1252) of the alkaline solutions collected from the reactor were pipetted into pre-cleaned EXETAINDER® vials (12 mL, screw cap, item 938 W, Labco Limited, Lampeter, UK) in triplicate inside a glovebox (O₂ and CO₂ < 0.1 ppm) (Guillemot et al., 2021; Rauber, 2018). The volume of the sample solution was adjusted that samples could be prepared that allowed ¹⁴C measurements in the optimal dynamic range of the AMS. The solutions were spiked with aliquots of ¹⁴C-free KH^{12/13}CO₃ and ^{12/13}C-acetate carriers to provide ~ 50 µg stable carbon. Three blanks were prepared by mixing 1.25 or 0.125 mL ACW, respectively, with the ¹⁴C-free carriers. All vials were tightly sealed, frozen and analyzed by WO combined with ¹⁴C quantification by AMS at the Laboratory for Analysis of Radiocarbon (LARA; University of Bern, Switzerland), as detailed elsewhere (Rauber, 2018). For d-TO¹⁴C measurements, 250 µL of oxidizing agent (10% K₂S₂O₈, Sigma-Aldrich, ACS reagent > 99%) solution in 5% H₃PO₄ (Merck 85% suprapur®) was injected into the sample vials after the TI¹⁴C measurements. Within the two hours of reaction, TO¹⁴C/TOC was converted to ¹⁴CO₂/CO_{2(g)}, which were transferred into the AMS via the gas interface system (GIS) (Rauber, 2018). The p-TO¹⁴C was determined by spiking 800 µL of the solution pre-treated with the Ag/Ba/H cartridge with 1.25 M ¹⁴C-free acetate carrier. Before sampling day 1114, 10 µL of the solution was combusted in an elemental analyzer (EA) (Elementar, Langensfeld, Germany) and ¹⁴CO₂/CO₂ injected into the AMS via the GIS (Cvetković et al., 2018; Salazar et al., 2015). Starting with sampling day 1114, p-TO¹⁴C was determined by WO, as this technique allows injection of ¹⁴CO₂ from 5 mL solution.

2.5.2. Aqueous ¹⁴C-bearing carbon compounds

Dissolved carbon compounds were separated and identified by high performance ion exchange chromatography (HPIEC) using an ICS-5000 ion chromatography (IC) in combination with a mass spectrometer (MS) system (Dionex/Thermo Fisher, Sunnyvale, CA, USA). Chromleon 7 software (SR 11d) was used for IC data acquisition and processing, while Xcalibur Finnigan Surveyor MSQ 1.1 ELMO software controlled the MS, as reported elsewhere (Cvetković et al., 2018a; Cvetković et al., 2018b; Guillemot et al., 2020a). To an 800 µL aliquot of solution previously pre-treated by the Ag/Ba/H cartridge, 2 µL of a 6 mM ¹⁴C-free acetate carrier were added. Pre-treatment with the cartridge removed interfering anions (e.g. Cl⁻) from solution and reduced the pH to ~6, which improved peak resolution. The mixture of solution and stable carbon carrier was injected into the IC via an injection loop (14 µL) and eluted at a flow rate of 0.25 mL/min using a 250 mm × 2 mm i.d. IonPac AS11-HC column, KOH as mobile phase, and an elution program described elsewhere (Cvetković et al., 2018b; Cvetković et al., 2018c; Guillemot et al., 2021).

Formic acid (FA), acetic acid (AA), lactic acid (LA), malonic acid (MA) and oxalic acid (OA) were the main dissolved stable carbon organics identified by HPIEC and separated according to their retention times using a fraction collector (Foxy Jr.® Fraction collector, Teledyne Isco, Lincoln, NE, USA) (Cvetković et al., 2018a; Cvetković et al., 2018b). The pre-treated solution was injected nine times consecutively and the nine

fractions of each individual carboxylic acid (CA) were collected in a single vial (total volume of ~ 500 µL). The sample was further diluted to 5 mL and analyzed by WO combined with ¹⁴C quantification by AMS.

2.5.3. Total gaseous ¹⁴C content

The gas chromatographic (GC) system used for identification and sample preparation consists of a TRACE™ GC (Thermo Fisher Scientific Inc., Waltham, USA, operated with the Thermo Xcalibur 3.0.63 software), an oxidation reactor (Thermo Finnigan, Bremen, Germany), and a custom-built fraction collector operated by a custom-built software (Brechtbühler AG, Schlieren, Switzerland). The GC setup as well as the methods developed to determine the total ¹⁴C content in the gas phase (TG¹⁴C) have been described in detail elsewhere (Guillemot et al., 2021; Guillemot et al., 2020b). Briefly, an aliquot of the gas collected from the reactor (i.e. 40 µL on day 1114; 500 µL thereafter) was loaded into the sample loop of the GC using a gas-tight syringe (Hamilton AG, Bonaduz, Switzerland). Also in this case, the volume of the sampled gas was adjusted to allow sample preparation for the optimal dynamic range of the AMS. ¹⁴C-free (fossil) CH₄ (grade 5.0; Carbagas, AG, Liebefeld, Switzerland) was injected as a stable carbon carrier via the carrier loop of the GC to achieve 50 µg of stable carbon. The sample and carrier were injected simultaneously and passed with the He flow through a fused silica capillary (1 m × 0.32 mm) to the oxidation reactor, which was operated at 1000 °C to convert carbon compounds into CO₂. Afterwards, the analyte stream sequentially passed through additional devices (a reduction oven to remove traces of O₂ and nitrous oxides (NO_x) and a water trap to remove residual water) before finally being collected in the fraction collector (Guillemot et al., 2021; Guillemot et al., 2020b). The fraction collector was transferred to LARA and connected to the GIS through a 1 m long 1/16" O.D. tubing. A He flow of ~ 30 mL/min was applied for 150–300 s to purge the mixture of ¹⁴CO₂/CO₂ from the sampling loops into the GIS zeolite trap, which was heated up to release the ¹⁴CO₂/CO₂ mixture into the AMS gas ion source for ¹⁴C quantification (Salazar et al., 2015; Wacker et al., 2013).

2.5.4. Gaseous ¹⁴C-bearing carbon compounds

The GC system previously described was also used to separate the individual ¹⁴C-bearing carbon compounds. The setup and development of the method have been described in detail elsewhere (Guillemot et al., 2021; Guillemot et al., 2020b). Briefly, 500 µL of gas sample was injected through the sample loop simultaneously with a defined amount of ¹⁴C-free (fossil) carrier through a second (carrier) loop. Previous studies reported CH₄, CO, C₂H₆ and C₃H₈ as the main gaseous carbon compounds produced during the corrosion of iron and steel (Cvetković et al., 2018a; de Visser-Týnová et al., 2018; Guillemot et al., 2020a; Wieland and Hummel, 2015) and therefore these compounds were added as ¹⁴C-free carriers. The compounds were separated using a Restek Rt®-Msieve 5A column (30 m × 0.32 mm with 0.025 mm film) and a temperature program previously reported (Guillemot et al., 2021; Guillemot et al., 2020b). The separated compounds were oxidized in the oxidation reactor (1000 °C) to ¹⁴CO₂/CO₂ and eventually collected in the sampling loops of the fraction collector. Injection into the AMS via the GIS was performed as previously described for TG¹⁴C analysis.

2.5.5. Hydrogen

The H₂ concentration in the gas phase was determined using GC–MS as it is an indicator of the anoxic corrosion of steel (Jelinek and Neufeld, 1982) (Eq. (1)). 10 mL of the gas volume collected from the reactor were withdrawn from the sampling tube using a gas-tight syringe and injected into a purged and evacuated 20 mL vial. To equalize pressure, each vial was then connected to a gas bag filled with N₂ (grade 5.0, Carbagas AG, Liebefeld, Switzerland) for five seconds. The Restek Rt®-Msieve 5A GC column (30 m × 0.32 mm with 0.025 mm film) was used in combination with the following temperature program: initial temperature of 45 °C (isothermal for 4 min), heating at a rate of 20 °C/min to 290 °C (isothermal for 10 min), resulting in a total run time of ~ 26 min. Hydrogen (H₂) was

detected by MS in selected ion monitoring (SIM) mode with standard EI parameters (i.e. 70 eV collision energy and 230 °C MS source temperature) and appeared in the chromatogram with the specific mass fragment 5 generated by protonation of the carrier gas (He) with by H⁺, as described elsewhere (Varlet et al., 2013). Standards were prepared in 20 mL vials in the dynamic range between 0 and 8 µg H₂/mL gas volume using pure H₂ (Messer Schweiz AG, Lenzburg, Switzerland) diluted with N₂ after pressure equalization. It should be noted that the scatter in the H₂ measurements was quite large, which is due to the possibility of different losses of small amounts of gas during the GC-MS measurements.

2.6. Accelerator mass spectrometry

Quantifications of Tl¹⁴C, d-TO¹⁴C, p-TO¹⁴C, individual ¹⁴C-bearing CAs, TG¹⁴C and individual ¹⁴C-bearing gaseous carbon compounds were performed at LARA using a 200 kV Mini CARBON DATING SYSTEM (MICADAS) (Szidat et al., 2014). The standards used were 5% CO₂ from oxalic acid II from National Institute of Standards and Technology (SRM 4990C) in helium prepared by Hekal AMS Lab (Hungary) and ~ 4.5% fossil CO₂ in He from Messer AG (Switzerland). The linear dynamic range of the ¹⁴C measurements was found to span three orders of magnitude between 0.06 F¹⁴C - 50 F¹⁴C (fraction modern carbon), corresponding to a concentration range from 0.01 to 9.8 pmol ¹⁴C/L in solution (Cvetković et al., 2018b). The MICADAS and associated equipment (i.e. GIS, EA etc.) were controlled and accessed by Transmission Control Protocol/Internet Protocol commands generated by LabView (Salazar et al., 2015; Szidat et al., 2014; Wacker et al., 2013).

2.7. Data treatment

Results from the ¹⁴C AMS measurements were expressed in terms of F¹⁴C. For the liquid samples, the F¹⁴C values were converted to molar ¹⁴C concentrations (M) and volume-related ¹⁴C activities (Bq/L), taking into account several parameters related to the analytical procedure used, such as the amount of stable carbon carrier added (i.e. 20–50 µg ^{12/13}C) and the volume of solution used for ¹⁴CO₂/CO₂ injection into the AMS source (S.I. S4). For the gas samples, F¹⁴C values were converted to ¹⁴C concentrations (mol/L gas volume) and volume-related ¹⁴C activities (Bq/L) based on the gas volume normalized to ambient temperature (22 °C) and pressure (1 bar) by taking into account the parameters related to the analytical procedure used, such as the amount of stable carbon carrier added and the volume of gas sample injected (S.I. S4). The evolution of the ¹⁴C concentrations in the reactor was quantified by correcting with the dilution factors of both aqueous and gas phases at each sampling due to the replacement of 7 mL sampled solution by ACW and the sampled gas by N₂. The dilution factors were calculated based on the weighted amount of solution sampled, the weighted amount of fresh ACW injected and the different pressure readings at each sampling step (S.I. Table S4–1).

3. Results

In this corrosion experiment with irradiated steel, ¹⁴C concentrations were in the pico- to femtomolar range (S.I. Table S5–1, S5–3, and S5–5), as expected, due to the small size and low ¹⁴C content of the two irradiated steel samples, the very slow corrosion of stainless steel in alkaline solution, and finally the small volume of solution and gas collected from the reactor and used for the ¹⁴C analyses. The AMS-based analytical techniques allowed us to quantify ¹⁴C in the ultra-trace range, but a relatively large statistical uncertainty (up to 30%) had to be accepted for the liquid samples due to limited repeatability of the measurements.

The ¹⁴C concentrations determined over time in the liquid and gas phases of the reactor were corrected with the corresponding dilution factors and normalized to the total surface area of the two steel samples (i.e., 11.15 cm²) in order to account for surface-related ¹⁴C release (Fig. 1) (S.I. Table S5–2, S5–4, and S5–6). The ¹⁴C content determined after pre-treatment of the solution with the OnGuard cartridge (p-TO¹⁴C)

was quantified from the beginning of the experiment (Fig. 1a). The other parameters were quantified on sampling day 1114 and thereafter, after the WO method was introduced (Guillemot et al., 2021) (Fig. 1 b-d).

Fig. 1a shows that p-TO¹⁴C increased sharply within the first ~ 30 days after immersion of the two samples in ACW, i.e. p-TO¹⁴C increased from 1.2×10^{-14} M to 6.4×10^{-13} M (S.I. Table S5–2) (Fig. 1a). Direct measurements of TO¹⁴C (i.e. d-TO¹⁴C) from sampling day 1114 and thereafter confirmed that after the initial phase, both p- and d-TO¹⁴C were constant during the course of steel corrosion (Fig. 1a). The d-TO¹⁴C varied between $8.3 \pm 1.1 \times 10^{-13}$ M and $9.8 \pm 3.5 \times 10^{-13}$ M (S.I. Table S5–2). Tl¹⁴C was also nearly constant with time (Fig. 1b), varying between $3.0 \pm 1.0 \times 10^{-13}$ M and $3.6 \pm 1.3 \times 10^{-13}$ M (S.I. Table S5–2). In contrast to p-TO¹⁴C, d-TO¹⁴C and Tl¹⁴C, the ¹⁴C content in the gas phase (TG¹⁴C) increased slowly but steadily with time over the 1.5-year gas sampling period from $2.6 \pm 0.1 \times 10^{-13}$ M to $4.2 \pm 0.1 \times 10^{-13}$ M (Fig. 1c) (S.I. Table S5–6).

The corrosion of stainless steel under anoxic conditions can be described as follows (Jelinek and Neufeld, 1982):



The time-dependent increase in H₂ concentration is thus a direct measure of the anoxic corrosion of steel and was determined on sampling day 1114 and thereafter (S.I. Table S5–7). Fig. 1d compares the surface-normalized H₂ release according to Eq. (1) and predicted by Eq. (2) with the experimental data. In addition to H₂, ¹⁴C is an additional tracer associated with the steel corrosion in this study.

The following equation was used to relate the release of ¹⁴C and H₂ (m(t)) to the corrosion rate of stainless steel (Cvetković et al., 2018c):

$$m(t) = \int_0^t \frac{R_c A \rho v}{M_w} dt \quad [\text{mol}] \quad (2)$$

R_c: Corrosion rate [m/yr];

A: Surface area of specimens in reactor ($A = m_{\text{Fe}} \cdot S_m$) [m²] with m_{Fe}: Mass of the two specimens (= 1.718×10^{-3} kg) and S_m: Specific surface area (= 0.649 m²/kg);

M_w: Molecular weight of iron (0.055845 kg/mol);

ρ: Density of iron (7855 kg/m³);

v: Stoichiometric factors: ¹⁴C (= 4.27×10^{-7}) expressed in terms of mol ¹⁴C/mol Fe of irradiated steel; H₂ (4/3) according to Eq. (1).

The ¹⁴C release into solution and gas phase (normalized to the surface area of the specimens) was modeled for corrosion rates between 1 nm/yr and up to 100 nm/yr. These values are within the range of rates reported for stainless steel corrosion in alkaline solution (Diomidis, 2014; Smart, 2009; Swanton et al., 2015). For modeling purposes, a constant ¹⁴C inventory of irradiated steel was assumed, which is supported by mass balance calculations. These show that less than 0.01% of the ¹⁴C inventory of stainless steel was released into the solution and the gas phase during more than four years of corrosion. The calculations further assume that ¹⁴C released from irradiated steel is converted to either gaseous or aqueous species. For consistency, the modeling was based on the assumption of an initial rapid release of ¹⁴C at a rate of 20 nm/yr for all parameters, as indicated by the increase in p-TO¹⁴C within the first 30 days of corrosion. This indicates the presence of surface sites on steel with higher reactivity in the case of the gaseous species.

A comparison of the distribution of the ¹⁴C contents between the liquid (Tl¹⁴C, TO¹⁴C) and gas phase (TG¹⁴C) fractions demonstrates the time-dependent increase in TG¹⁴C from $42 \pm 12\%$ on day 1114 to $53 \pm 16\%$ on day 1637 as a result of the corrosion process (Fig. 2). In contrast, TO¹⁴C and Tl¹⁴C remained constant, which means that their relative share decreases with time (Fig. 2).

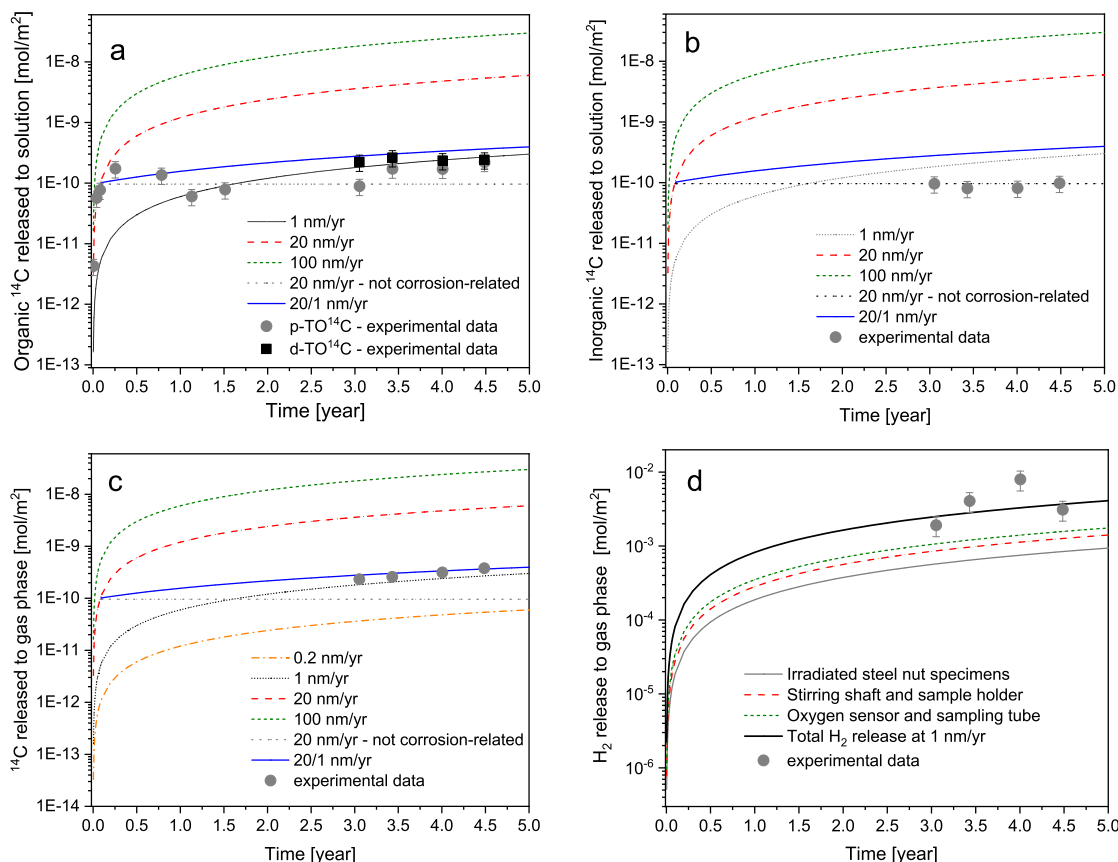


Fig. 1. Temporal evolution of (a) p- and d-TO¹⁴C, (b) TI¹⁴C, (c) TG¹⁴C and (d) H₂ release with a rate of 1 nm/yr. Experimental data and predictions (lines) for the experimental set-up using corrosion rates reported for stainless steel in hyper-alkaline conditions. The following assumptions were made to model the increase in ¹⁴C concentrations according to Eq. (2): i) continuous rate of 1 nm/yr, 20 nm/yr and 100 nm/yr; ii) fast corrosion at a rate of 20 nm/yr within 30 days and subsequently no release by corrosion; iii) fast corrosion at a rate of 20 nm/yr within 30 days and subsequent slow corrosion at a rate of 1 nm/yr (20/1 nm/yr).

The AMS-based CSRA was developed to identify and quantify the individual ¹⁴C-bearing carbon species in solution, such as ¹⁴C-FA, ¹⁴C-AA, ¹⁴C-OA, ¹⁴C-MA, and ¹⁴C-LA, as well as ¹⁴C-HCs (i.e. ¹⁴CH₄, ¹⁴C₂H₆, ¹⁴C₃H₈) and ¹⁴CO in the gas phase.

The concentrations of ¹⁴C-FA, ¹⁴C-AA, ¹⁴C-OA, ¹⁴C-MA, and ¹⁴C-LA were determined on sampling days 1252, 1462 and 1637 (S.I. Tables S5–3 and 5–4). The total concentration of the ¹⁴C-bearing CAs was calculated by assuming that each CA carries only one ¹⁴C atom (S.I. Table S5–4). The concentrations were averaged since no trend was discernible in the data. The average concentrations of the individual ¹⁴C-bearing CAs were as follows:

¹⁴C-FA = $7.4 \pm 1.1 \times 10^{-14}$ M, ¹⁴C-AA = $11.1 \pm 1.2 \times 10^{-14}$ M, ¹⁴C-OA = $9.0 \pm 3.4 \times 10^{-14}$ M, ¹⁴C-MA = $5.3 \pm 2.6 \times 10^{-14}$ M, and ¹⁴C-LA = $6.3 \pm 1.4 \times 10^{-14}$ M. Fig. 3a shows their contribution to the d-TO¹⁴C. It was estimated that the total concentration of the ¹⁴C-bearing CAs corresponds to $42 \pm 19\%$ and $58 \pm 10\%$ of the d-TO¹⁴C and p-TO¹⁴C, respectively.

The individual gaseous ¹⁴C-bearing compounds have been identified and quantified since sampling day 1114 (S.I. Tables S5–5 and 5–6). ¹⁴CH₄ proved to be the most important ¹⁴C-bearing HC (Fig. 3b). Its concentration increased from $2.6 \pm 0.1 \times 10^{-13}$ M to $3.5 \pm 0.2 \times 10^{-13}$ M between

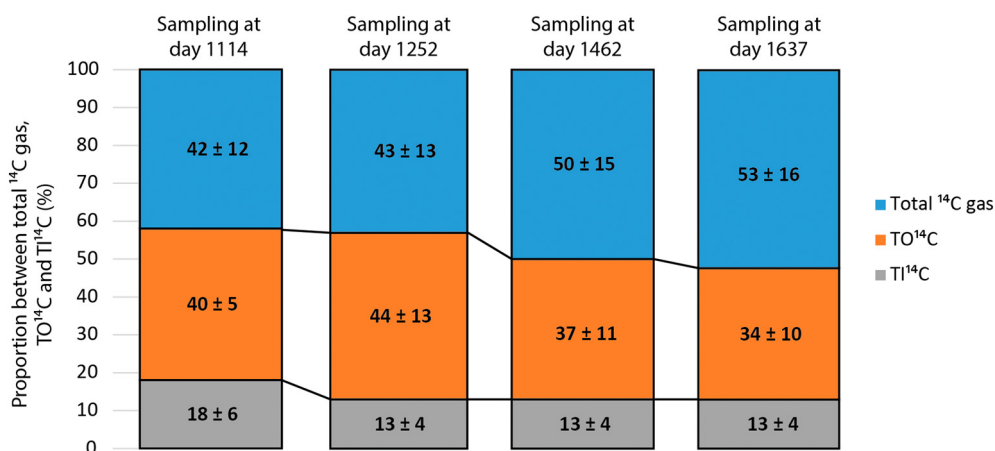


Fig. 2. Distribution of the ¹⁴C-bearing compounds in the liquid and gas phases between three and four years of alkaline anoxic corrosion of irradiated steel.

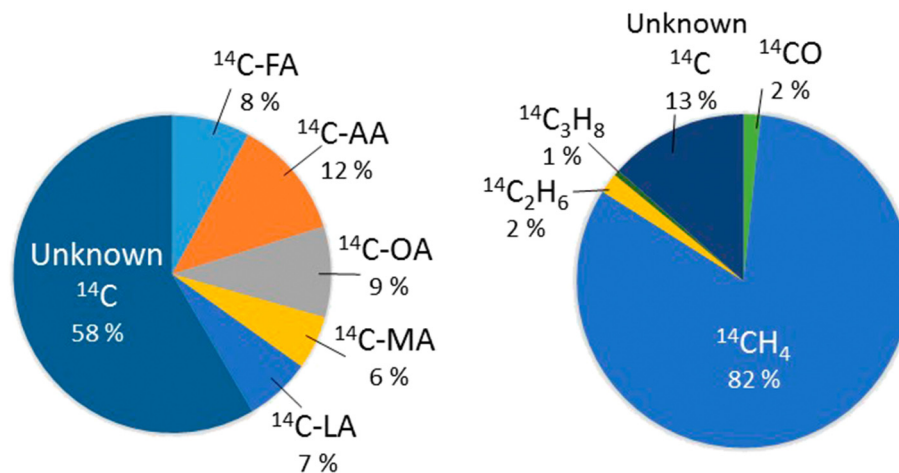


Fig. 3. Proportions of (a) ¹⁴C-bearing CAs to the d-TO¹⁴C (average from sampling day 1252 to 1637) and (b) ¹⁴C-bearing gaseous compounds to the TG¹⁴C on sampling day 1637.

sampling day 1114 and 1637 (S.I. Table S5–6). Additionally, other small ¹⁴C-bearing HCs and ¹⁴CO were quantified to estimate their contribution to TG¹⁴C (Fig. 3b). ¹⁴C₂H₆ showed a slight increase in concentration between sampling day 1252 and 1637 from $5.9 \pm 0.1 \times 10^{-15}$ M to $8.2 \pm 2.1 \times 10^{-15}$ M. ¹⁴C₃H₈ and ¹⁴CO were quantified only on sampling day 1637 ($2.3 \pm 0.9 \times 10^{-15}$ M and $7.0 \pm 2.1 \times 10^{-15}$ M, respectively). It should be noted that the concentrations of ¹⁴C₂H₆, ¹⁴C₃H₈ and ¹⁴CO were close to the limit of quantification (LOQ).

4. Discussion

4.1. Time-dependent release of ¹⁴C

The evolution of TI¹⁴C, p- and d-TO¹⁴C in solution and TG¹⁴C in the gas phase is related to the release from irradiated steel, since no other ¹⁴C source was identified in the reactor. In addition, replacing an aliquot of the solution in the reactor with ACW only slightly increased the background ¹⁴C content (S.I. Table S2–1).

The model predictions show that p-TO¹⁴C, d-TO¹⁴C and TI¹⁴C are not related to the long-term corrosion of irradiated steel, unlike TG¹⁴C. The ¹⁴C concentration in solution (TO¹⁴C, TI¹⁴C) is considered to be the result of a rapid release of ¹⁴C in the initial phase of the corrosion process. The long-term increase in TG¹⁴C, however, occurs in accordance with a corrosion rate of stainless steel of 1 nm/yr. This value agrees very well with rates reported in other work for the corrosion of stainless steel in anoxic alkaline conditions (e.g., Diomidis, 2014; Senior et al., 2021; Smart, 2009; Swanton et al., 2015).

Quantification of TO¹⁴C and TI¹⁴C in solution and TG¹⁴C in the gas phase allowed us to establish a mass balance for ¹⁴C during alkaline anoxic corrosion of irradiated steel. By knowing the ¹⁴C inventory of the irradiated steel (i.e. 1.31×10^{-8} mol/g; Schumann et al., 2014), it was possible to determine the fraction of ¹⁴C released since the beginning of the corrosion experiment. By day 1637 of alkaline anoxic corrosion, $\sim 8.0 \times 10^{-13}$ mol ¹⁴C had been released into the liquid and gas phases, corresponding to $\sim 0.0061\%$ of the initial ¹⁴C inventory of the irradiated steel samples.

The question arose whether the release of ¹⁴C occurs in stoichiometric proportion to H₂ production during corrosion. The modeling shows that the H₂ concentration in the gas phase also increased according to a corrosion rate of 1 nm/yr (Fig. 1d). However, it must be taken into account that in addition to the irradiated stainless steel specimens, the assembly parts of the reactor systems, such as parts of the stirring shaft with the sample holder, parts of the sampling tube and the oxygen sensor, were also exposed to alkaline solution (S.I. Fig. S1–1). The slow corrosion of these assembly parts made of stainless steel contributed to the H₂ production. It should be noted that

the assembly parts were not designed in a way to cause no H₂ production because the corrosion experiment was primarily focused on the ¹⁴C speciation during steel corrosion under alkaline anoxic conditions. In addition, the type of stainless steel used to make the assembly parts was not known, which led us to assume that the irradiated steel nuts and the assembly parts were made of the same stainless steel. The surface areas of the assembly parts are known (stirring shaft with sample holder: 16.75 cm², dissolved oxygen sensor and sampling tube: 20.84 cm²), so the contribution of corrosion of these parts to the H₂ production could be calculated and separated from H₂ release by the irradiated steel samples (surface area: 11.15 cm²). The corrosion of the latter samples contributed about 22% to the total H₂ production at a corrosion rate of 1 nm/yr. The results show that the release rate of ¹⁴C from the irradiated stainless steel samples is identical to the corrosion rate of the material (stoichiometric release).

4.2. Speciation

Literature reviews and corrosion studies with irradiated steel and non-irradiated iron indicate the formation of low molecular weight (LMW) organic carbon compounds, such as CAs, as well as carbonate and hydrocarbons (HCs) during iron/steel corrosion (Cvetković et al., 2018a; de Visser-Týnová et al., 2018; Guillemot et al., 2020a; Swanton et al., 2015; Wieland and Hummel, 2015).

The result shows that dissolved organic carbon compounds account for d- and p-TO¹⁴C. The two parameters agree quite well, as p-TO¹⁴C corresponds to $67 \pm 27\%$ of the d-TO¹⁴C on average. However, some of the ¹⁴C contributing to the TO¹⁴C was retained by the Ag/Ba/H cartridge, presumably as colloidal ¹⁴C or ¹⁴C associated with larger organic molecules retained during filtration, which explains the difference between d-TO¹⁴C and p-TO¹⁴C. In view of these results, the CAs can be considered as important organic ¹⁴C-carrying carbon compounds present in solution ($\sim 42\%$ of the organic ¹⁴C content in solution) during alkaline anoxic corrosion of irradiated steel (Fig. 3a). TI¹⁴C is attributed to the presence of ¹⁴CO₃²⁻ under the given high-pH conditions. TI¹⁴C is about a factor of 3 lower than d-TO¹⁴C (Fig. 2), suggesting that ¹⁴CO₃²⁻ is not the predominant ¹⁴C-bearing species.

Previous studies have shown that oxidized carbon compounds, e.g. CAs, can be detected in solution under the anoxic conditions of iron-water systems (Cvetković et al., 2018a; Guillemot et al., 2020a; Wieland and Hummel, 2015 and references therein). Hence, the same oxygen-bearing carbon compounds have been observed in the current and previous corrosion studies (e.g., Swanton et al., 2015; Wieland and Hummel, 2015) (Table 1). In general, the formation of small CAs containing between one and five C atoms is observed (Wieland and Hummel, 2015, and references therein). It has been hypothesized that CAs are formed when iron/steel is

Table 1
Stable carbon and ^{14}C -bearing compounds identified during alkaline anoxic corrosion of non-activated iron powders and irradiated stainless steel.

Corrosion of non-irradiated iron/steel ^a		Corrosion of irradiated steel ^b	
Gaseous stable carbon compounds	Aqueous stable carbon compounds	Gaseous ^{14}C -compounds	Aqueous ^{14}C -compounds
Methane	Formate	Methane	Formate
Ethane	Acetate	Ethane	Acetate
Ethene	Propionate	Propane	Malonate
Propane	Butanoate	Carbon monoxide	Oxalate
Propene	Malonate	Carbon dioxide	Lactate
Butane	Oxalate		Carbonate
Butylene ^c	Lactate		
Pentane ^c	Glycolate		
Pentene ^c	Carbonate		
Hexane	Alcohols/aldehydes ^d		

^a See Swanton et al. (2015); Wieland and Hummel (2015) and references therein; Cvetković et al. (2018a); Guillemot et al. (2020a).

^b See de Visser-Týnová et al. (2018); Kaneko et al. (2003); Yamashita et al. (2014); this study.

^c Including isomers (e.g. *trans*-2-butene, *cis*-2-butene, 1-butene, iso-butene as well as 2-methylbutane, *cis*-2-pentene, *trans*-2-pentene).

^d Including methanol, ethanol, propanol, formaldehyde, acetaldehyde, propionaldehyde.

exposed to oxic (humid) conditions and they are taken up by the oxide surface layer of the metal (Cvetković et al., 2018a; Guillemot et al., 2020a). Upon contact with a solution, the CAs are immediately released from the oxide layer by desorption. This hypothesis is further supported by the current study, as $p\text{-TO}^{14}\text{C}$ increased rapidly in the initial phase of steel corrosion and remained constant thereafter (Fig. 1a). It is assumed that the release of organic and inorganic ^{14}C occurs by diffusion through the oxide layer and/or as a result of the conversion of iron oxyhydroxides into magnetite (Ishikawa et al., 1998; Tamaura et al., 1983). Nevertheless, we cannot exclude the possibility that the oxidized carbon species were alternatively produced in the reactor during the initial phase of the experiment due to the presence of small amounts of residual O_2 in the solution.

Moreover, the irradiated stainless steel samples are the source of weak gamma radiation. The dose rate of a ~ 1 g specimen was estimated to be ~ 0.12 Gy/h, based on the ^{60}Co and ^{54}Mn contents (Schumann et al., 2014). Depending on the dose rate, gamma radiation can produce different chemical species, in particular radicals (e.g. $\text{HO}\cdot$, $\text{HO}_2\cdot$) and peroxide (H_2O_2) that act as oxidizing agents (Spinks and Woods, 1990). It should be noted that at the given very low dose rate of the irradiated steel samples, the concentration of H_2O_2 is expected to be far below the detection limit of standard analytical methods. However, the observed constant concentrations of ^{14}C -bearing CAs, TO^{14}C and TI^{14}C indicate that ^{14}C -CAs and ^{14}C -bearing carbonate were not produced by radiation-induced radiolysis on the steel surface, since in this case a continuous increase in the above parameters over time would be expected.

The formation of gaseous ^{14}C -bearing carbon compounds during the corrosion of irradiated steel was previously studied by de Visser-Týnová et al. (2018). These authors identified $^{14}\text{CH}_4$ as the main gaseous carbon compound, while smaller proportions of ^{14}CO and $^{14}\text{CO}_2$ were detected. The current study supports the results by de Visser-Týnová and coworkers. $^{14}\text{CH}_4$ accounts for more than 80% of the TG^{14}C in this study and is thus the predominant gaseous ^{14}C -bearing compound. $^{14}\text{C}_2\text{H}_6$, $^{14}\text{C}_3\text{H}_8$, and ^{14}CO are only minor contributors to the TG^{14}C with proportions of $\sim 2\%$, $\sim 1\%$, and $\sim 2\%$, respectively, assuming that each carbon compound carried only one ^{14}C atom (Fig. 3b). It should be noted that there is still a discrepancy between the sum of ^{14}C carried by the HCs and CO and the TG^{14}C , suggesting the presence of one or more additional, as yet unidentified ^{14}C -bearing compounds at low concentrations (Fig. 3b).

De Visser-Týnová et al. (2018) also observed that ^{14}C was mainly released into solution as ^{14}C -bearing carbonate. The fraction of ^{14}C released into the gas phase was comparatively small ($< 6\%$ of total ^{14}C released). The fraction of gaseous ^{14}C compared to ^{14}C released into solution (CAs,

carbonate) is significantly higher in this study (Fig. 2). The higher fraction of ^{14}C in the liquid phase compared to the gas phases in the study of de Visser-Týnová et al. (2018) could be explained by the preferential formation of oxygenated ^{14}C -bearing carbon compounds as a consequence of the higher dose rate of irradiated steel. The total dose rate of irradiated steel used in this study was about two orders of magnitude lower (~ 0.21 Gy/h) than the one of the material used by de Visser-Týnová et al. (2018) (~ 20 Gy/h) (Mibus et al., 2018). The higher dose rate implies higher concentrations of oxidizing radicals in solution generated by radiolysis at the interface with steel, which favors the formation of oxygenated, water-soluble carbon compounds such as CAs or carbonate.

Studies with non-irradiated iron powders have shown that the concentration of HCs released into the gas phase tends to decrease with increasing numbers of C atoms according to an Anderson-Schulz-Flory (ASF) product distribution (Cvetković et al., 2018a; Deng et al., 1997; Guillemot et al., 2020a). The latter distribution suggests a Fischer-Tropsch (F-T) type mechanism leading to the formation of HCs on the metal surface. This general trend also applies to the current study with irradiated steel, as it shows that $^{14}\text{CH}_4$ is the predominant HC formed during the corrosion of ^{14}C -containing stainless steel. However, in contrast to previous studies with non-irradiated iron powders (Cvetković et al., 2018a; Guillemot et al., 2020a), the HCs with higher molecular weights were quantified only in trace amounts. We suspect that the difference in speciation is due to the different chemical forms of the carbon in the materials used. The non-irradiated iron powders were produced by the reduction of $\text{Fe}(\text{CO})_5$ with H_2 and had a higher C content with the C probably in the chemical form of carbide. Iron carbides have multiple stoichiometries (Cotton and Wilkinson, 1980), such as Fe_3C , Fe_7C_3 , and Fe_2C , with Fe_3C being the main chemical form in steel (Davis, 1998). The structure of iron carbides consists of carbon chains running through distorted metal lattices (Cotton and Wilkinson, 1980), which can lead to the formation of HCs with higher molecular weights. In contrast, ^{14}C is produced by the activation of ^{14}N impurities in steel via the nuclear reaction $^{14}\text{N}(\text{n,p})^{14}\text{C}$, where N is accommodated in the interstices of metal crystals or bound by a substitutional solid solution replacing a solvent atom in a lattice position (Davis, 1998). Therefore, ^{14}C may be uniformly distributed as single species in the metal matrix, which explains the release of ^{14}C during corrosion mainly as single carbon species, i.e. $^{14}\text{CH}_4$.

4.3. Implications for the safe disposal of radioactive waste

Knowledge of the ^{14}C speciation is of paramount importance in the context of an overall assessment of the pathways of ^{14}C migration from the EBS of the DGR into the surrounding host rock and ultimately into the environment. The present study leads to the following conclusions with regards to application in safety assessment:

1. The corrosion of steel in cement-type solutions with a pH 12.5, and thus the release of ^{14}C , is a very slow process (corrosion rate of 1 nm/yr), while even lower rates have been determined for steel embedded in cementitious material (< 1 nm/yr) (Senior et al., 2020; Senior et al., 2021).
2. The amount of ^{14}C released as water-soluble oxygenated carbon compounds (e.g. CAs, carbonate) is very low (i.e. $\sim 0.003\%$ of the initial ^{14}C inventory of the irradiated steel samples used in this study) and occurs in the very early phase of corrosion by rapid release from the oxide layer of the steel upon contact with solution. There is no evidence that the amount of water-soluble oxygenated carbon compounds increases over time as a result of corrosion. The water-soluble organic ^{14}C fraction migrates from the EBS into the surrounding host rock by diffusion.
3. There is evidence that the proportion of ^{14}C released as $^{14}\text{CO}_3^{2-}$ in the early phase of anoxic corrosion of irradiated steel and at the given low dose rate of the material is slightly less than that released as water-soluble organic ^{14}C -bearing compounds. $^{14}\text{CO}_3^{2-}$ is strongly retained in the cementitious near field by precipitation as calcium carbonate or by isotopic exchange with CO_3^{2-} from calcium carbonate (Allard et al., 1981; Bayliss et al., 1988) and therefore ^{14}C decays within the repository.

- The initial amounts of ^{14}C -bearing CAs and presumably also $^{14}\text{CO}_2$ released into the solution depend on whether and to what extent the irradiated metal parts have been exposed to oxic conditions (e.g. storage in air, radiolysis-induced oxidation in nuclear power plants, etc.) before their final disposal.
- $^{14}\text{CH}_4$ is the main gaseous ^{14}C carrier produced during anoxic corrosion of irradiated steel and is capable of carrying ^{14}C from the EBS of a DGR into the environment. The release of ^{14}C into the gas phase occurs consistently with H_2 production at the appropriate corrosion rate (1 nm/yr in this study).

5. Conclusions

AMS-based analytical methods enabled the determination of ultra-low ^{14}C concentrations in a corrosion experiment with irradiated stainless steel (i.e. in the pico- to femtomolar range). Measurements of the total ^{14}C contents (d-TO ^{14}C , p-TO ^{14}C , TI ^{14}C , TG ^{14}C) and individual ^{14}C -bearing carbon compounds by CSRA in solution and the gas phase show the rapid release of aqueous ^{14}C -bearing carbon species in the early phase of the corrosion process (within ~ 30 days) and constant total inorganic (TI ^{14}C) and organic ^{14}C (d- and p-TO ^{14}C) contents in solution after the rapid release. About 40% of the TO ^{14}C is attributed to the presence of small ^{14}C -bearing CAs up to C3, while the remaining fraction has not yet been identified. TI ^{14}C is about a factor of 3 lower than the d-TO ^{14}C . In contrast, the total ^{14}C content in the gas phase (TG ^{14}C) increases over time concurrently with H_2 production and consistent with the corrosion of stainless steel at a rate of 1 nm/yr. $^{14}\text{CH}_4$ is the predominant gaseous species contributing $\sim 80\%$ of the TG ^{14}C , while other ^{14}C -bearing gaseous species (^{14}CO , $^{14}\text{C}_2\text{H}_6$ and $^{14}\text{C}_3\text{H}_8$) are present only in small amounts. Therefore, modeling of ^{14}C release from a DGR should take into account that most of the ^{14}C is likely released in gaseous form. In contrast, the amount of ^{14}C released as water-soluble ^{14}C is comparatively small. A total of 0.0061% of the initial ^{14}C inventory of the irradiated steel samples was released into the solution and gas phase during 1637 days of corrosion in anoxic alkaline conditions. Assuming that the water-soluble ^{14}C fraction does not increase with time and that corrosion proceeds at a rate of 1 nm/yr, it takes $\sim 1.5 \times 10^5$ years for the remaining ^{14}C inventory of the irradiated steel samples to be released into the gas phase. Considering the half-life of ^{14}C ($t_{1/2} = 5700$ years), which is short compared to the predicted release time, the ^{14}C inventory of irradiated steel and thus the contribution of ^{14}C to the dose release from a DGR will steadily decrease with time due to the radioactive decay.

CRedit authorship contribution statement

Typhaine Guillemot: Validation, Formal analysis, Investigation, Data curation, Writing – original draft, Visualization. **Gary Salazar:** Methodology, Software, Investigation, Writing – review & editing. **Martin Rauber:** Methodology, Investigation, Writing – review & editing. **Dominik Kunz:** Methodology, Investigation. **Sönke Szidat:** Validation, Resources, Writing – review & editing, Project administration. **Erich Wieland:** Conceptualization, Validation, Writing – review & editing, Supervision, Project administration, Funding acquisition.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

Partial financial support for this project was provided by swissnuclear (Project title: “Investigation of the chemical speciation of ^{14}C released from irradiated steel”) and by the National Cooperative for the Disposal of Radioactive Waste (Nagra), Switzerland. Partial funding was received from the

European Union's European Atomic Energy Community's (Euratom) Seventh Framework Programme FP7/ 2007–2013 under grant agreement no. 604779, the CAST project. Specific tasks within this project have been developed in co-operation with Brechbühler AG (Schlieren, Switzerland). The innovative technical developments and the valuable contributions to the project by Peter Pichler, Philippe Mottay and Benjamin Oberlin (all Brechbühler AG) are gratefully acknowledged. We would like to thank the NPP Gösgen for providing the irradiated steel nuts, Ines Günther-Leopold, Matthias Martin and Robin Grabherr (all PSI) for processing the material and the preparation of small specimens for laboratory experiments, as well as Dorothea Schumann and Tanja Stowasser (both PSI) for determining the ^{14}C inventory of the steel nuts. Thanks are extended to Jan Tits and Marcus Keller (both PSI) for their support during construction of the reactor and Andreas Lagotzki (PSI) for calculating the dose rate of the material.

Appendix A. Supplementary data

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.scitotenv.2021.152596>.

References

- Allard, B., Torstenfelt, B., Andersson, K., 1981. Sorption studies of H^{14}CO_3 on some geological media and concrete. *Mater. Res. Soc. Symp. Proc.* 3, 465–473.
- Bayliss, S., Ewart, F.T., Howse, R.M., Smith-Briggs, J.L., Thomason, H.P., Willmott, A., 1988. The solubility and sorption of lead-210 and carbon-14 in a near-field environment. *Mater. Res. Soc. Symp. Proc.* 112, 33–42.
- Chimi, Y., Kitsunai, T., Kasahara, S., Chatani, K., Koshiishi, M., Nishiyama, Y., 2016. Correlation between locally deformed structure and oxide film properties in austenitic stainless steel irradiated with neutrons. *J. Nucl. Mater.* 475, 71–80.
- Cotton, F.A., Wilkinson, G., 1980. *Advanced Inorganic Chemistry*. fourth edition. Wiley-Interscience, New York.
- Cvetković, B., Rothardt, J., Buttler, A., Kunz, D., Schlotterbeck, G., Wieland, E., 2018a. Formation of low-molecular-weight organic compounds during anoxic corrosion of zero-valent iron. *Environ. Eng. Sci.* 35, 447–461.
- Cvetković, B., Salazar, G., Kunz, D., Szidat, S., Wieland, E., 2018b. Analysis of C-14-bearing compounds released by the corrosion of irradiated steel using accelerator mass spectrometry. *Analyst* 143, 3059–3067.
- Cvetković, B.Z., Salazar, G., Kunz, D., Tits, J., Szidat, S., Wieland, E., 2018c. Quantification of dissolved organic C-14-containing compounds by accelerator mass spectrometry in a corrosion experiment with irradiated steel. *Radiocarbon* 60, 1711–1727.
- Davis, J.R., 1998. *Metals Handbook Vol 1: Properties and Selection: Irons, Steels, and High-performance Alloys*. American Society of Metals, Materials Park OH 44073, USA.
- Deng, B.L., Campbell, T.J., Burris, D.R., 1997. Hydrocarbon formation in metallic iron/water systems. *Environ. Sci. Technol.* 31, 1185–1190.
- Diomidis, N., 2014. Scientific Basis for the Production of Gas due to Corrosion in a Deep Geological Repository. Nagra Working Report NAB 14-21. Nagra, Wettingen, Switzerland.
- Guillemot, T., Cvetković, B.Z., Kunz, D., Wieland, E., 2020a. Processes leading to reduced and oxidised carbon compounds during corrosion of zero-valent iron in alkaline anoxic conditions. *Chemosphere* 250, 126230.
- Guillemot, T., Salazar, G., Cvetković, B.Z., Kunz, D., Szidat, S., Wieland, E., 2020b. Determination of ultra-low concentrations of gaseous C-14-bearing hydrocarbons produced during corrosion of irradiated steel using accelerator mass spectrometry. *Analyst* 145, 7870–7883.
- Guillemot, T., Cvetković, B.Z., Kunz, D., Salazar, G., Rauber, M., Szidat, S., Wieland, E., 2021. Development of Analytical Methods for the Detection of ^{14}C -bearing Carbon Compounds at Ultra-low Concentrations. Nagra Working Report NAB 21-03. Nagra, Wettingen, Switzerland.
- Hanbury, R.D., Was, G.S., 2019. Oxide growth and dissolution on 316L stainless steel during irradiation in high temperature water. *Corros. Sci.* 157, 305–311.
- Ishikawa, T., Kondo, Y., Yasukawa, A., Kandori, K., 1998. Formation of magnetite in the presence of ferric oxyhydroxides. *Corros. Sci.* 40, 1239–1251.
- Jelinek, J., Neufeld, P., 1982. Kinetics of hydrogen formation from mild-steel in water under anaerobic conditions. *Corrosion* 38, 98–104.
- Johnson, L., Schwyn, B., 2008. Proceedings of a Nagra/RWMC Workshop on the Release and Transport of C-14 in Repository Environments. Nagra Working Report NAB 08-22. Nagra, Wettingen, Switzerland.
- Kaneko, S., Tanabe, H., Sasoh, M., Takahashi, R., Shibano, T., Tateyama, S., 2003. A study on the chemical forms and migration behavior of carbon-14 leached from the simulated hull waste in the underground condition. *Mater. Res. Soc. Symp. Proc.* 757, 621–626.
- Mibus, J., Diomidis, N., Wieland, E., Swanton, S.W., 2018. Release and speciation of C-14 during the corrosion of activated steel in deep geological repositories for the disposal of radioactive waste. *Radiocarbon* 60, 1657–1670.
- Nagra, 2014a. Sicherheitstechnischer Bericht zu SGT-Etape 2: Sicherheitstechnischer Vergleich und Vorschlag der in Etappe 3 weiter zu untersuchenden geologischen Standortgebiete. Nagra Technical Report 14-01. Nagra, Wettingen, Switzerland.
- Nagra, 2014b. Modellhaftes Inventar für radioaktive Materialien MIRAM 14. Nagra Technical Report 14-04. Nagra, Wettingen, Switzerland.

- Nagra, 2016. Waste Management Programme 2016 of the Waste Producers. Nagra Technical Report NTB 16-01E. Nagra, Wettingen, Switzerland.
- Nuclear Decommissioning Authority, 2012. Geological Disposal - Carbon-14 Project - Phase 1 Report. Technical Report NDA/RWMD/092. Harwell, Didcot, United Kingdom.
- Raiman, S., Was, G.S., 2017. Accelerated corrosion and oxide dissolution in 316L stainless steel irradiated in situ in high temperature water. *J. Nucl. Mater.* 493, 207–218.
- Rauber, M., 2018. Compound-specific Radiocarbon Analysis of Aerosols. Faculty of Science. University of Bern, Bern, Switzerland Master thesis.
- Sakuragi, T., Yoshida, S., Kato, O., Tateishi, T., 2016. Study of stainless steel corrosion by hydrogen measurement under deoxygenated, low-temperature and basic repository conditions. *Prog. Nucl. Energy* 87, 26–31.
- Salazar, G., Zhang, Y.L., Agrios, K., Szidat, S., 2015. Development of a method for fast and automatic radiocarbon measurement of aerosol samples by online coupling of an elemental analyzer with a MICADAS AMS. *Nucl. Instrum. Methods Phys. Res., Sect. B* 361, 163–167.
- Schumann, D., Stowasser, T., Volmert, B., Günther-Leopold, I., Linder, H., Wieland, E., 2014. Determination of the C-14 content in activated steel components from a neutron spallation source and a nuclear power plant. *Anal. Chem.* 86, 5448–5454.
- Senior, N.A., Martino, T., Diomidis, N., Gaggiano, R., Binns, J., Keech, P., 2020. The measurement of ultra low uniform corrosion rates. *Corros. Sci.* 176, 108913.
- Senior, N.A., Martino, T., Gaggiano, R., Diomidis, N., 2021. The corrosion of mild and stainless steel in alkaline anaerobic conditions representing the Belgian “supercontainer” concept and the Swiss L/ILW repository. *Mater. Corros.* 72, 67–74.
- Smart, N.R., 2009. Corrosion behavior of carbon steel radioactive waste packages: a summary review of Swedish and U.K. research. *Corrosion* 65, 195–212.
- Spinks, J.W.T., Woods, R.J., 1990. *An Introduction to Radiation Chemistry*. 3rd ed. John Wiley and Sons, New York.
- Swanton, S.W., Baston, G.M.N., Smart, N.S., 2015. Rates of Steel Corrosion and Carbon-14 Release From Irradiated Steel - State of the Art Review. CAST WP2 Deliverable D 2.1. European Union, Brussels.
- Szidat, S., Salazar, G.A., Vogel, E., Battaglia, M., Wacker, L., Synal, H.-A., Türlér, A., 2014. C-14 analysis and sample preparation at the new Bern laboratory for the analysis of radiocarbon with AMS (LARA). *Radiocarbon* 56, 561–566.
- Tamura, Y., Ito, K., Katsura, T., 1983. Transformation of γ -FeO(OH) to Fe₃O₄ by absorption of iron(II) ion on γ -FeO(OH). *J. Chem. Soc. Dalt. Trans.* 189–194.
- Varlet, V., Smith, F., Augsburg, M., 2013. Indirect hydrogen analysis by gas chromatography coupled to mass spectrometry (GC-MS). *J. Mass Spectrom.* 48, 914–918.
- de Visser-Týnová, E., Swanton, S.W., Williams, S.J., Stijkel, M.P., Walker, A.J., Otlet, R.L., 2018. C-14 release from irradiated stainless steel. *Radiocarbon* 60, 1671–1681.
- Wacker, L., Fahrni, S.M., Hajdas, I., Molnar, M., Synal, H.A., Szidat, S., Zhang, Y.L., 2013. A versatile gas interface for routine radiocarbon analysis with a gas ion source. *Nucl. Instrum. Methods Phys. Res. Sect. B* 294, 315–319.
- Was, G., 2017. *Fundamentals of Radiation Materials Science*. 2nd ed. Springer-Verlag, Berlin Heidelberg.
- Wieland, E., Hummel, W., 2015. Formation and stability of C-14-containing organic compounds in alkaline iron-water systems: preliminary assessment based on a literature survey and thermodynamic modelling. *Mineral. Mag.* 79, 1275–1286.
- Wieland, E., Cvetković, B.Z., Kunz, D., Salazar, G., Szidat, S., 2017. Identification and formation of carbon-14 containing organic compounds during anoxic corrosion of activated steel in alkaline conditions. 16th International High-Level Radioactive Waste Management Conference (IHLRWM 2017), Charlotte, NC, USA.
- Wieland, E., Cvetković, B., Kunz, D., Salazar, G., Szidat, S., 2018. Carbon-14 speciation during anoxic corrosion of activated steel in a repository environment. *Atw-Int. J. Nucl. Power* 63, 34–39.
- Yamashita, Y., Tanabe, H., Sakuragi, T., Takahashi, R., Sasoh, M., 2014. C-14 release behavior and chemical species from irradiated hull waste under geological disposal conditions. *Mater. Res. Soc. Symp. Proc.* 1665, 187–194.
- Yim, M.-S., Caron, F., 2006. Life cycle and management of carbon-14 from nuclear power generation. *Prog. Nucl. Energy* 48, 2–36.
- Zhao, Y., Li, Y., Wu, Q., Qi, W., Zhang, T., Wang, F., 2021. Effect of thermal aging and irradiation on the electrochemical and passivation behavior of 308L stainless steel in simulated pressurized water reactor environment. *Mater. Lett.* 286, 129157.