

# Osteoinductive potential of 4 commonly employed bone grafts

Richard J. Miron<sup>1,2,3,4</sup> · Qiao Zhang<sup>1</sup> · Anton Sculean<sup>3</sup> · Daniel Buser<sup>4</sup> · Benjamin E. Pippenger<sup>5</sup> · Michel Dard<sup>6</sup> · Yoshinori Shirakata<sup>7</sup> · Fatiha Chandad<sup>2</sup> · Yufeng Zhang<sup>1</sup>

Received: 17 August 2015 / Accepted: 12 January 2016 / Published online: 27 January 2016  
© Springer-Verlag Berlin Heidelberg 2016

## Abstract

**Objectives** Guided bone regeneration (GBR) aims to predictably restore missing bone that has been lost due to trauma, periodontal disease or a variety of systemic conditions. Critical to this procedure is the ability of a bone grafting material to predictably serve as a 3-dimensional scaffold capable of inducing cell and bone tissue in-growth at the material surface. Although all bone grafts are osteoconductive to bone-forming osteoblasts, only a small number of commercially available bone grafts with FDA approval are

osteoinductive including demineralized freeze-dried bone allografts (DFDBA) and scaffolds containing bone morphogenetic proteins (BMPs). Recently, a class of synthetic bone grafts fabricated from biphasic calcium phosphate (BCP) sintered at a low temperature have been shown to form ectopic bone formation in non-skeletal sites without the use of growth factors. Therefore, the present study aimed to compare the osteoinductive potential of this group of synthetic BCP alloplasts with autografts, allografts and xenografts.

**Materials and methods** In the present study, 4 types of bone grafting materials including autogenous bone harvested with a bone mill, DFDBA (LifeNet, USA), a xenograft derived from bovine bone mineral (NBM, BioOss, Geistlich, Switzerland) and a novel synthetic biphasic calcium phosphate (BCP, Straumann, Switzerland) were implanted into intramuscular pouches of 24 rats and analysed histologically for their ability to form ectopic bone formation around grafting particles. A semi-quantitative osteoinductive score was used to quantify the osteoinductive ability of each bone graft.

**Results** The results from the present study reveal that (1) autogenous bone resorbed rapidly in vivo, (2) the xenograft showed no potential to form ectopic bone formation and (3) both DFDBA and BCP were able to stimulate ectopic bone formation.

**Conclusion** These studies demonstrate that these newly developed synthetic bone grafts have potential for inducing ectopic bone formation similar to DFDBA. Future clinical testing is necessary to reveal their bone-inducing properties in clinical scenarios including GBR procedures and in combination with implant dentistry.

**Clinical relevance** Novel BCP scaffolds are able to induce ectopic bone formation without the use of osteoinductive growth factors such as BMP2 and thus demonstrate a large clinical possibility to further enhance bone formation for a variety of clinical procedures.

✉ Richard J. Miron  
richard.miron@zmk.unibe.ch

✉ Yufeng Zhang  
zyf@whu.edu.cn

<sup>1</sup> The State Key Laboratory Breeding Base of Basic Science of Stomatology (Hubei-MOST) & Key Laboratory of Oral Biomedicine Ministry of Education, School & Hospital of Stomatology, Wuhan University, 237 Luoyu Road, Wuhan 430079, People's Republic of China

<sup>2</sup> Faculté de Médecine Dentaire, Pavillon de Médecine Dentaire, Université de Laval, 2420 rue de la Terrasse, Québec G1V 0A6, Canada

<sup>3</sup> Department of Periodontology, University of Bern, School of Dental Medicine, Bern, Switzerland

<sup>4</sup> Department of Oral Surgery and Stomatology, School of Dental Medicine, University of Bern, Bern, Switzerland

<sup>5</sup> Institut Straumann AG, Basel, Switzerland

<sup>6</sup> Department of Periodontology and Implant Dentistry, New York University, New York, NY, USA

<sup>7</sup> Department of Periodontology, Kagoshima University Graduate School of Medical and Dental Sciences, Kagoshima, Japan

**Keywords** Osteoinduction · Osteoinductive potential · Bone grafts · Natural bone mineral

## Introduction

Despite the increasing number of new bone grafting substitutes that have emerged in recent years, to date, there exists no single ideal replacement grafting material [1]. Autogenous bone has been considered the golden standard for bone replacement procedures in dentistry due to its release of osteogenic growth factors including bone morphogenetic proteins (BMPs) able to promote the proliferation and differentiation of progenitor cells [2, 3]. Furthermore, they carry no risk of immunologic reaction or disease transmission and their use provides an optimal environment for new blood vessel formation [2, 3]. In contrast, many bone grafting substitutes fabricated from a variety of synthetic materials such as hydroxyapatite,  $\beta$ -tricalcium phosphate and bioactive glasses may provide an osteoconductive matrix but without osteoinductive potential [4].

The field of osteoinductive bone grafting materials has been the cornerstone of much research over the past few decades [5]. Historically, osteoinduction refers to the process by which one tissue, or product derived from it, causes a second undifferentiated tissue to differentiate into bone [5]. In 2 classical studies by Marschall Urist in 1965 and 1967, osteoinduction was defined as “the mechanism of cellular differentiation towards bone of one tissue due to physicochemical effect or contact with another tissue” [6]. In that study, the ability of an implanted demineralized bone matrix to induce in-growth ectopic bone formation in connective tissue of rabbits, dogs and rats was investigated [7]. Later, a group of low molecular weight proteins extracted from demineralized bone matrix (DBM), termed bone morphogenetic proteins (BMPs), were isolated and characterized showing more osteoinduction than DBM alone [8]. Despite these early advancements in the field of osteoinductive biomaterials, to date, only DFDBA and bone biomaterials containing BMPs are approved by the FDA as truly osteoinductive materials [5].

Recently, Yuan et al. demonstrated that synthetically fabricated bone grafts sintered at low temperatures possess the capability of forming ectopic bone formation in large animal models [9]. Bone defects loaded with these synthetic bone grafts were also shown to heal as rapidly as autogenous bone [9]. In light of these recent findings, our group aimed to investigate the use of this novel synthetic scaffold fabricated from biphasic calcium phosphate (BCP). BCP bone grafting particles were compared to 3 commonly employed bone grafting materials including autogenous bone chips derived from a bone mill, demineralised freeze-dried bone allografts (DFDBA) and a commonly employed xenograft (a natural bone mineral, NBM). The osteoinductive potential of each

bone graft was compared for their ability to induce ectopic bone formation in an animal model.

## Materials and methods

### Bone graft selection

#### *Autogenous bone*

Autogenous bone was harvested from Wistar rats using cortico-cancellous block grafts harvested with a trephine and ground to particulated bone chips using a bone mill. The selection of bone mill as the selection for autogenous bone harvesting is because it stimulated the highest osteogenic response and ability to release growth factors to the surrounding environment [10, 11].

#### *Allograft bone*

Demineralized freeze-dried bone allograft (DFDBA) from LifeNet (USA) was utilized as the DFDBA of choice due to previous handling and its ability to form ectopic bone formation in vivo [12, 13].

#### *Xenograft bone*

A natural bone mineral (NBM) of bovine origin (BioOss, Geistlich, Switzerland) was used as the xenograft of choice due to its widespread use in dentistry and our laboratories' previous use in its handling [14–16].

#### *Alloplast bone ceramic*

In the present study, a biphasic calcium phosphate (BCP) was tested. The BCP graft was utilized using a 90:10 ration of beta-tricalcium phosphate and hydroxyapatite (Vivoss, Straumann AG, Basel, Switzerland) as previously described [17].

### Scanning electron microscopy

Bone grafting materials were fixed in 1 % glutaraldehyde and 1 % formaldehyde for 2 days for SEM. Following serial dehydration with ethanol, samples were critically point dried (Type M.9202 Critical Point Dryer, Roth & Co. Hatfield, PA, USA) followed by overnight drying. The following day, samples were sputter coated using a Balzers Union Sputtering Device (DCM-010, Balzers, Liechtenstein) with 10 nm of gold and analyzed microscopically using a Philips XL30 FEG scanning electron microscope to determine surface variations between bone grafts.

### Animal experiments


Twenty-four male Wistar rats (mean body weight 200 g) were used with all handling and surgical procedures in accordance with the policies of the Ethics Committee for Animal Research at the University of Wuhan, China. Animals were given food and water ad libitum with constant temperature at 20–25 °C.

All operations were conducted under strictly sterile conditions. For surgery, the rats were generally anesthetized with intraperitoneal injection of chloral hydrate (10 %, 4 ml/kg body weight) as previously described [18]. After skin preparation and disinfection, bilateral muscle pouches were made in the gastrocnemius muscle of each animal as previously described [13]. Subsequently, an equal mass of autogenous bone (20 mg per pouch), DFDBA particles (20 mg per pouch), NBM (20 mg per pouch) and BCP (20 mg per pouch) were implanted intramuscularly and incisions were sutured in two layers. Postoperatively, penicillin (400,000 IU/ml, 0.1 ml/kg) was injected for 3 days. After 3 and 6 weeks postimplantation, rats were sacrificed and samples were removed and prepared for histological analysis.

### Histological analysis

The samples were decalcified in 10 % EDTA replaced twice weekly for 3 weeks at room temperature. Samples were then dehydrated in a series of graded concentrations of ethanol from 30 to 100 % followed by embedding in paraffin as previously described [19]. Serial sections of 5 μm were cut and mounted on polylysine-coated microscope slides and stained with H&E (Sigma #S2255; Sigma-Aldrich, St. Louis, USA) in accordance with the manufacturer’s protocol and also as previously described to visualize ectopic bone formation. All samples were observed for evidence of ectopic bone formation and remaining bone grafting particles. Furthermore, the ability of the samples to induce new ectopic bone formation was semi-qualitatively evaluated by two independent observers (QZ, YZ) blinded to treatment and rated according to a previously published scheme [20–24]. Three consecutive sections (3 to 4 μm each) were obtained at 3 different levels throughout the block along the longitudinal axis for evaluation. The ability of the samples to induce new bone was qualitatively evaluated by the 2 independent observers and rated accordingly as described below. In total, 4 separate fields in

**Fig. 1** SEM images of autogenous bone harvested via bone milling **a, b**, an allograft (DFDBA) **c, d** and a xenograft (NBM) **e, f** at low **a, c, e** and high **b, d, f** magnification

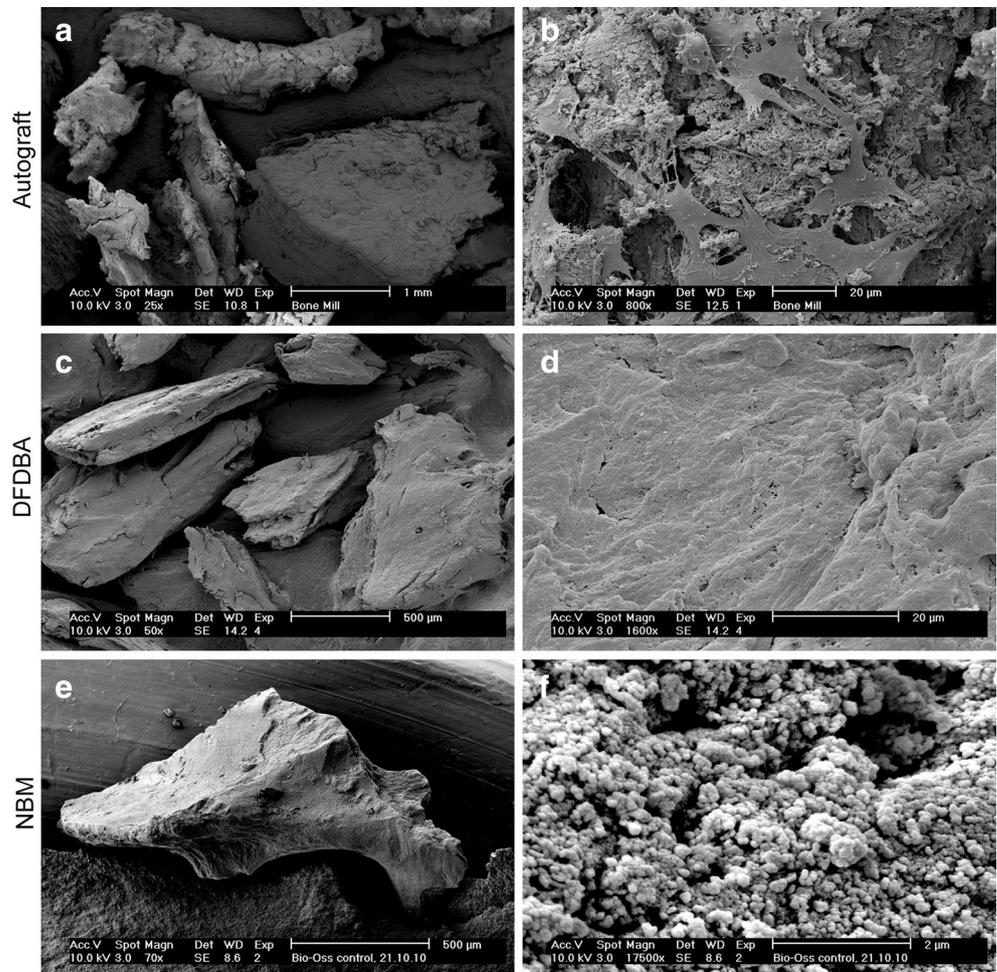

each of the 3 different sections were evaluated for ectopic bone formation according to the following score: A score of 1 indicated the presence of particles without any bone; 2 indicated the production of a new bone in one site within the section and covering less than 40 % of the surface area examined; 3 indicated the production of a new bone in more than one site, covering more than 40 % but less than 70 %, of the surface area examined; and 4 indicated the production of a new bone in more than one site, covering more than 70 % of the surface area examined. The overall grade for each implant was obtained by averaging the scores from all specimens in the group.

## Results

### Scanning electron microscopy


SEM was utilized to visualize bone grafting particles both at low and high magnification (Figs. 1 and 2). Autogenous bone chips derived from a bone mill showed various shapes and sizes from 0.1 mm to slightly greater than 1 mm (Fig. 1a). The high-resolution magnification demonstrated a number of proteins remaining on the particle surface with a number of cells still present on its surface following sample harvesting (Fig. 1b). On the other hand, DFDBA particles were slightly smaller in size with particle surface devoid of any visible proteins and with a very smooth surface (Fig. 1c, d). Xenograft particles were also very similar in size to DFDBA ranging from 0.3 to approximately 1 mm (Fig. 1e). Interestingly, the material surface had quite a roughened surface when compared to either autogenous bone or the alloplast (Fig. 1f). The material surface was completely devoid of all proteins (Fig. 1f).

Following analysis of 3 commonly used bone grafting materials, BCP grafts were visualized (Fig. 2). As can be depicted from the SEM images at a low magnification, the new synthetic bone grafts present with many macrotopographies (Fig. 2a). Furthermore, the high-resolution SEM images demonstrate extremely roughened surfaces (Fig. 2c).

### Ectopic bone formation


Following SEM analysis, ectopic bone formation was investigated for all bone grafting particles at 3 and 6 weeks postimplantation (Fig. 3). Interestingly, autogenous bone demonstrated some signs of ectopic bone formation at 3 weeks (Fig. 3a, arrow). By 6 weeks, the bone graft was entirely resorbed and muscle was found surrounding the original defect site (Fig. 3b). NBM derived from bovine origin

demonstrated no signs of ectopic bone formation either at 3 or 6 weeks (Fig. 3c). Following 6 weeks, the xenograft material was still present in muscle pouches with a large number of infiltration inflammatory monocytes found within connective tissues surrounding the bone particles (Fig. 3c). The implantation of DFDBA to the muscle pouches demonstrated signs of ectopic bone formation at both time points (Fig. 3e, f). Results varied between the 6 animals tested, largely dependent

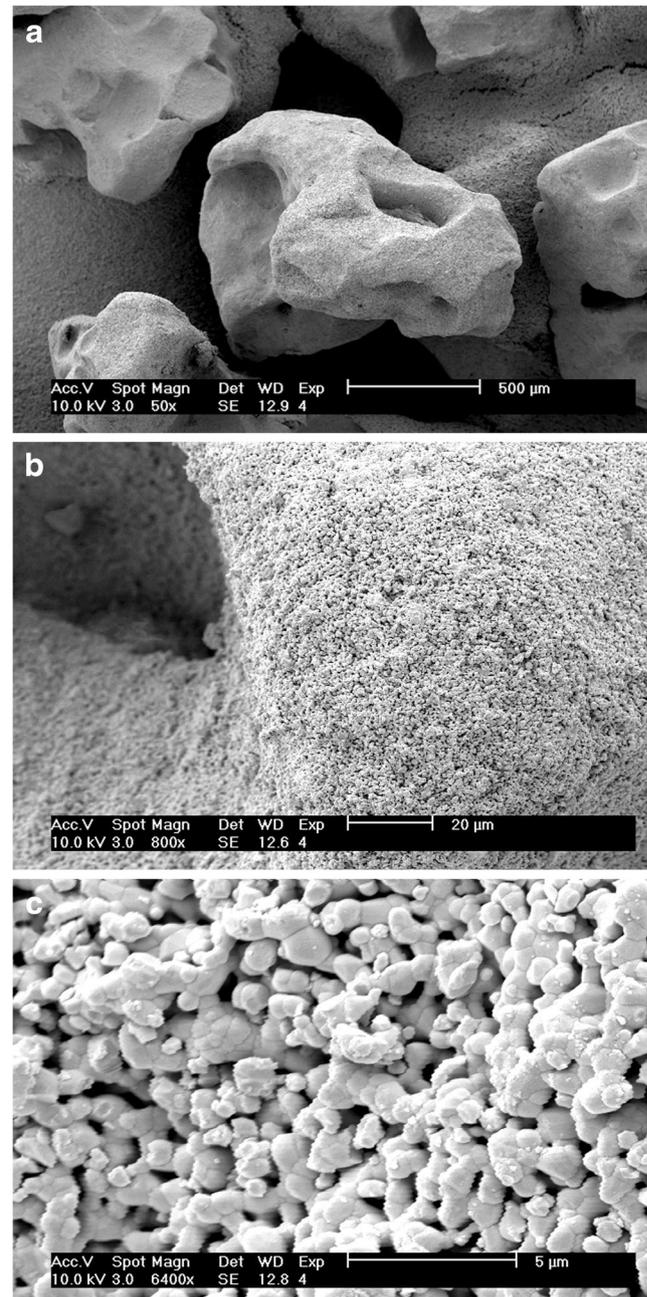

**Fig. 2** SEM images of novel BCP bone grafting material demonstrating many macro- and nano-topographies at low **a**, moderate **b** and high **c** magnification

**Fig. 3** H&E staining of bone grafts (BG) tested for ectopic bone formation in the gastrocnemius muscle of rats at 3 and 6 weeks postimplantation. (*Bar* = 500  $\mu$ m; *BG* = bone graft, *CT* = connective tissue, *Mu* = muscle; *arrows* indicate new ectopic bone formation)

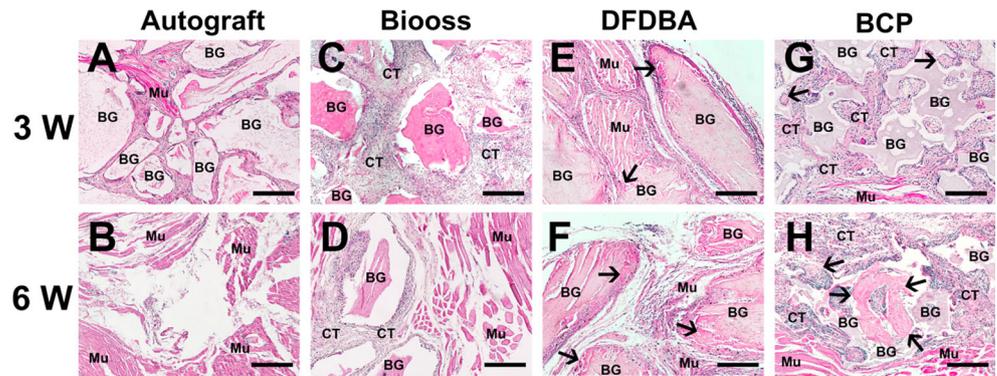

on the batch of DFDBA chosen; however, most of the new bone formation was found adjacent to the scaffold surface (Fig. 3e, f, arrows). Interestingly, the BCP group with a high macro- and microtopographies (Fig. 2) was able to form ectopic bone formation as depicted in Fig. 3g, h. Ectopic bone formation was found in all samples adjacent to the bone grafting particle surface at 3 weeks with an additional bone being formed by 6 weeks (Fig. 3h). All samples were quantified using a semi-quantitative osteoinduction score (Fig. 4). By 6 weeks, all autografts were resorbed with some signs of osteoinduction visible at 3 weeks. The NBM had no ability to form ectopic bone formation and remained present at 6 weeks (Fig. 4). Both DFDBA and BCP demonstrated the ability to form ectopic bone formation. More variability was found for DFDBA samples (Fig. 4).


**Discussion**

The aim of the present study was to test the osteoinductive potential of 4 bone grafting materials commonly utilized in the field of implant dentistry. There exists a large variability between the bone-forming capabilities of various bone grafts, and the osteoinductive potential remains one of the key features to improve the integration of implanted bone grafts [5]. While the field of implant dentistry has made a number of significant advances in recent years, the use of an autogenous bone has remained the gold standard for bone grafting procedures over the past several decades. Despite this, numerable attempts have been made to substitute autogenous bone grafts with other replacement options due to their drawbacks that include increased patient morbidity, limited availability and extra surgical time/costs.

Therefore, the present study investigated a newly developed synthetic bone graft fabricated from a biphasic calcium phosphate fabricated from 10:90 ratio of hydroxyapatite and  $\beta$ -tricalcium phosphate (Fig. 2). These novel grafts show promising features as a bone grafting material by

demonstrating extremely high macro- and nanoporosities, ideal characteristics for bone growth [25–27] capable of forming ectopic bone formation (Fig. 3). Previously, Dahlin et al. compared these same BCP bone grafts with a 2nd BCP-II grafting material composed of 60 % hydroxyapatite/40 %  $\beta$ -TCP, as well as a NBM in surgically created defects in the mandible of minipigs [28]. It was found that BCP-I showed significant higher amounts of newly formed bone when compared to the other 2 groups including the NBM utilized in our study [28]. Therefore, consistent with those results, the osteoinductive model utilized in the present study demonstrated similar in vivo characteristics on new bone formation as presented previously by Dahlin et al. [28].

Not surprisingly, the natural bone mineral derived from bovine origin was unable to show signs of ectopic bone formation. These bone grafts have been used extensively in bone grafting procedures over the years due to their ability to remain present with little to no evidence of bone resorption even years after implantation [29–31]. While these grafts demonstrated numerous clinical advantages, there drawbacks include no osteoinductive potential limiting their ability to rapidly stimulate new bone formation. Previously, Donos et al. further

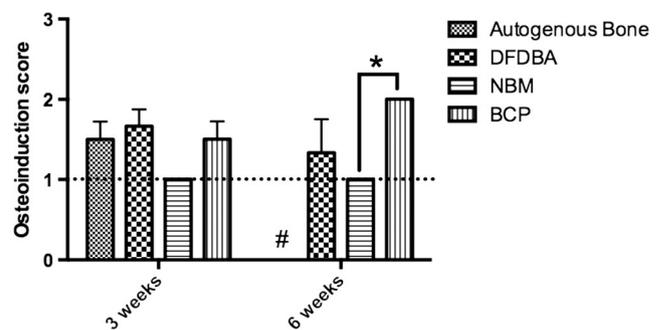

**Fig. 4** The effect of different bone grafts on osteoinductivity using a qualitative scoring system: 0 = no evidence of any bone graft, 1 = only original bone graft present, 2 = one site with visible ectopic bone formation, 3 = two or more sites of ectopic bone formation, 4 = >70 % of field at  $\times 10$  covered by a new bone (\* $p$  < 0.05, # $p$  < 0.05; group lower than all other groups)

showed that these xenografts were also incapable of forming ectopic bone formation [32], consistent with the results found in our study.

It was also noted in the present study that the allografts demonstrated selective ability to form ectopic bone formation with variable rates of bone around the implanted grafts. It has previously been reported that DFDBA has variable rates of bone formation largely dependent on donor age, medical condition as well as sterilization procedures [13, 33]. Thus, while the ability for DFDBA to form ectopic bone formation was confirmed in the present study, one of the advantages of using a synthetic material could more predictably produce new bone formation when compared to DFDBA from various donor batches.

One of the key remaining questions presently investigated by our group is to determine the mechanism by which these novel BCP bone grafting materials are able to direct and induce ectopic bone formation. Recent studies have begun to implicate immune cells as the possible governing cells responsible for dictating new bone formation around certain classes of bone biomaterials [34–36]. A special subset of macrophages (osteal macrophages, also referred to as OsteoMacs) is currently being investigated as possible key players responsible for guiding new bone formation around these bone biomaterials [37]. While limited available data still exists in the literature, future strategies to further characterize these cells within osteal tissues as well as their plausible roles in bone induction of biomaterials remains necessary.

In conclusion, the results from the present study demonstrate that these novel BCP scaffolds possess an osteoinductive potential by demonstrating ectopic bone formation in skeletal sites in a rat muscle. While autogenous bone is still considered the gold standard of bone grafting materials due to its excellent combination of osteogenesis, osteoinduction and osteoconduction, novel synthetic materials are slowly paving a path which may demonstrate equivalent bone-forming abilities in the near future.

#### Compliance with ethical standards

**Conflict of interest** BCP grafts were kindly provided by Straumann AG, Switzerland. Benjamin Pippenger and Michel Dard are both employees of Straumann AG who contributed to the experimental design and provided the bone grafting materials. All other authors declare no conflict of interest.

**Funding** This study was supported by a grant from the American Academy of Implant Dentistry to Richard J. Miron (2013).

**Ethical approval** All applicable international, national and/or institutional guidelines for the care and use of animals were followed by the University of Wuhan, Department of Oral Implantology, China.

**Informed consent** No informed patient consent was necessary.

#### References

- Jensen SS, Bomstein MM, Dard M, Bosshardt DD, Buser D (2009) Comparative study of biphasic calcium phosphates with different HA/TCP ratios in mandibular bone defects. A long-term histomorphometric study in minipigs. *J Biomed Mater Res B Appl Biomater* 90:171–181. doi:10.1002/jbm.b.31271
- Mazock JB, Schow SR, Triplett RG (2004) Proximal tibia bone harvest: review of technique, complications, and use in maxillofacial surgery. *Int J Oral Maxillofac Implants* 19:586–593
- Jakse N, Seibert FJ, Lorenzoni M, Eskici A, Pertl C (2001) A modified technique of harvesting tibial cancellous bone and its use for sinus grafting. *Clin Oral Implants Res* 12:488–494
- Giannoudis PV, Dinopoulos H, Tsiridis E (2005) Bone substitutes: an update. *Injury* 36(Suppl 3):S20–S27. doi:10.1016/j.injury.2005.07.029
- Miron RJ, Zhang YF (2012) Osteoinduction: a review of old concepts with new standards. *J Dent Res* 91:736–744. doi:10.1177/0022034511435260
- Urist MR, Silverman BF, Buring K, Dubuc FL, Rosenberg JM (1967) The bone induction principle. *Clin Orthop Relat Res* 53:243–283
- Urist MR (1965) Bone: formation by autoinduction. *Sci (New York, NY)* 150:893–899
- Urist MR, Strates BS (1971) Bone morphogenetic protein. *J Dent Res* 50:1392–1406
- Yuan H, Fernandes H, Habibovic P, de Boer J, Barradas AM, de Ruiter A, Walsh WR, van Blitterswijk CA, de Bruijn JD (2010) Osteoinductive ceramics as a synthetic alternative to autologous bone grafting. *Proc Natl Acad Sci U S A* 107:13614–13619. doi:10.1073/pnas.1003600107
- Miron RJ, Gruber R, Hedbom E, Saulacic N, Zhang Y, Sculean A, Bosshardt DD, Buser D (2012) Impact of bone harvesting techniques on cell viability and the release of growth factors of autografts. *Clin Implant Dent Relat Res*. doi:10.1111/j.1708-8208.2012.00440.x
- Miron RJ, Hedbom E, Saulacic N, Zhang Y, Sculean A, Bosshardt DD, Buser D (2011) Osteogenic potential of autogenous bone grafts harvested with four different surgical techniques. *J Dent Res* 90:1428–1433. doi:10.1177/0022034511422718
- Miron RJ, Bosshardt DD, Laugisch O, Dard M, Gemperli AC, Buser D, Gruber R, Sculean A (2013) In vitro evaluation of demineralized freeze-dried bone allograft in combination with enamel matrix derivative. *J Periodontol* 84:1646–1654. doi:10.1902/jop.2013.120574
- Wei L, Miron RJ, Shi B, Zhang Y (2013) Osteoinductive and osteopromotive variability among different demineralized bone allografts. *Clin Implant Dent Relat Res*. doi:10.1111/cid.12118
- Miron RJ, Bosshardt DD, Laugisch O, Katsaros C, Buser D, Sculean A (2012) Enamel matrix protein adsorption to root surfaces in the presence or absence of human blood. *J Periodontol* 83:885–892. doi:10.1902/jop.2011.110404
- Miron RJ, Bosshardt DD, Zhang Y, Buser D, Sculean A (2012) Gene array of primary human osteoblasts exposed to enamel matrix derivative in combination with a natural bone mineral. *Clin Oral Investig*. doi:10.1007/s00784-012-0742-0
- Miron RJ, Wei L, Bosshardt DD, Buser D, Sculean A, Zhang Y (2014) Effects of enamel matrix proteins in combination with a bovine-derived natural bone mineral for the repair of bone defects. *Clin Oral Investig* 18:471–478. doi:10.1007/s00784-013-0992-5
- Miron RJ, Bosshardt DD, Gemperli AC, Dard M, Buser D, Gruber R, Sculean A (2014) In vitro characterization of a synthetic calcium phosphate bone graft on periodontal ligament cell and osteoblast behavior and its combination with an enamel matrix derivative. *Clin Oral Investig* 18:443–451. doi:10.1007/s00784-013-0977-4

18. Zhang Y, Wei L, Miron RJ, Shi B, Bian Z (2015) Anabolic bone formation via a site-specific bone-targeting delivery system by interfering with semaphorin 4d expression. *J Bone Miner Res Off J Am Soc Bone Miner Res* 30:286–296. doi:[10.1002/jbmr.2322](https://doi.org/10.1002/jbmr.2322)
19. Zhang Y, Wu C, Luo T, Li S, Cheng X, Miron RJ (2012) Synthesis and inflammatory response of a novel silk fibroin scaffold containing BMP7 adenovirus for bone regeneration. *Bone* 51:704–713. doi:[10.1016/j.bone.2012.06.029](https://doi.org/10.1016/j.bone.2012.06.029)
20. Ranly DM, Lohmann CH, Andreacchio D, Boyan BD, Schwartz Z (2007) Platelet-rich plasma inhibits demineralized bone matrix-induced bone formation in nude mice. *J Bone Joint Surg Am* 89:139–147. doi:[10.2106/jbjs.f.00388](https://doi.org/10.2106/jbjs.f.00388)
21. Schwartz Z, Mellonig JT, Carnes Jr DL, de la Fontaine J, Cochran DL, Dean DD, Boyan BD (1996) Ability of commercial demineralized freeze-dried bone allograft to induce new bone formation. *J Periodontol* 67:918–926. doi:[10.1902/jop.1996.67.9.918](https://doi.org/10.1902/jop.1996.67.9.918)
22. Schwartz Z, Weesner T, van Dijk S, Cochran DL, Mellonig JT, Lohmann CH, Carnes DL, Goldstein M, Dean DD, Boyan BD (2000) Ability of deproteinized cancellous bovine bone to induce new bone formation. *J Periodontol* 71:1258–1269. doi:[10.1902/jop.2000.71.8.1258](https://doi.org/10.1902/jop.2000.71.8.1258)
23. Miron RJ, Sculean A, Shuang Y, Bosshardt DD, Gruber R, Buser D, Chandad F, Zhang Y (2015) Osteoinductive potential of a novel biphasic calcium phosphate bone graft in comparison with autographs, xenografts, and DFDBA. *Clin Oral Implants Res*. doi:[10.1111/clr.12647](https://doi.org/10.1111/clr.12647)
24. Wei L, Miron RJ, Shi B, Zhang Y (2015) Osteoinductive and osteopromotive variability among different demineralized bone allografts. *Clin Implant Dent Relat Res* 17:533–542. doi:[10.1111/cid.12118](https://doi.org/10.1111/cid.12118)
25. Chan O, Coathup MJ, Nesbitt A, Ho CY, Hing KA, Buckland T, Champion C, Blunn GW (2012) The effects of microporosity on osteoinduction of calcium phosphate bone graft substitute biomaterials. *Acta Biomater* 8:2788–2794. doi:[10.1016/j.actbio.2012.03.038](https://doi.org/10.1016/j.actbio.2012.03.038)
26. Coathup MJ, Hing KA, Samizadeh S, Chan O, Fang YS, Champion C, Buckland T, Blunn GW (2012) Effect of increased strut porosity of calcium phosphate bone graft substitute biomaterials on osteoinduction. *J Biomed Mater Res A* 100:1550–1555. doi:[10.1002/jbm.a.34094](https://doi.org/10.1002/jbm.a.34094)
27. Habibovic P, Gbureck U, Doillon CJ, Bassett DC, van Blitterswijk CA, Barralet JE (2008) Osteoconduction and osteoinduction of low-temperature 3D printed bioceramic implants. *Biomaterials* 29:944–953. doi:[10.1016/j.biomaterials.2007.10.023](https://doi.org/10.1016/j.biomaterials.2007.10.023)
28. Dahlin C, Obrecht M, Dard M, Donos N (2015) Bone tissue modelling and remodelling following guided bone regeneration in combination with biphasic calcium phosphate materials presenting different microporosity. *Clin Oral Implants Res* 26:814–822. doi:[10.1111/clr.12361](https://doi.org/10.1111/clr.12361)
29. Bornstein MM, Chappuis V, von Arx T, Buser D (2008) Performance of dental implants after staged sinus floor elevation procedures: 5-year results of a prospective study in partially edentulous patients. *Clin Oral Implants Res* 19:1034–1043. doi:[10.1111/j.1600-0501.2008.01573.x](https://doi.org/10.1111/j.1600-0501.2008.01573.x)
30. Jensen SS, Aaboe M, Janner SF, Saulacic N, Bornstein MM, Bosshardt DD, Buser D (2013) Influence of particle size of deproteinized bovine bone mineral on new bone formation and implant stability after simultaneous sinus floor elevation: a histomorphometric study in minipigs. *Clin Oral Implants Res*. doi:[10.1111/cid.12101](https://doi.org/10.1111/cid.12101)
31. Jensen SS, Bosshardt DD, Gruber R and Buser D (2014) Long-term stability of contour augmentation in the esthetic zone. Histologic and histomorphometric evaluation of 12 human biopsies 14 to 80 months after augmentation. *J Periodontol*:1–15. doi:[10.1902/jop.2014.140182](https://doi.org/10.1902/jop.2014.140182)
32. Donos N, Kostopoulos L, Tonetti M, Karring T, Lang NP (2006) The effect of enamel matrix proteins and deproteinized bovine bone mineral on heterotopic bone formation. *Clin Oral Implants Res* 17:434–438. doi:[10.1111/j.1600-0501.2006.01260.x](https://doi.org/10.1111/j.1600-0501.2006.01260.x)
33. Schwartz Z, Somers A, Mellonig JT, Carnes Jr DL, Dean DD, Cochran DL, Boyan BD (1998) Ability of commercial demineralized freeze-dried bone allograft to induce new bone formation is dependent on donor age but not gender. *J Periodontol* 69:470–478. doi:[10.1902/jop.1998.69.4.470](https://doi.org/10.1902/jop.1998.69.4.470)
34. Davison NL, Gamblin AL, Layrolle P, Yuan H, de Bruijn JD, Barrere-de Groot F (2014) Liposomal clodronate inhibition of osteoclastogenesis and osteoinduction by submicrostructured beta-tricalcium phosphate. *Biomaterials* 35:5088–5097. doi:[10.1016/j.biomaterials.2014.03.013](https://doi.org/10.1016/j.biomaterials.2014.03.013)
35. Davison NL, Su J, Yuan H, van den Beucken JJ, de Bruijn JD, Barrere-de Groot F (2015) Influence of surface microstructure and chemistry on osteoinduction and osteoclastogenesis by biphasic calcium phosphate discs. *Eur Cell Mater* 29:314–329
36. Davison NL, ten Harkel B, Schoenmaker T, Luo X, Yuan H, Everts V, Barrere-de Groot F, de Bruijn JD (2014) Osteoclast resorption of beta-tricalcium phosphate controlled by surface architecture. *Biomaterials* 35:7441–7451. doi:[10.1016/j.biomaterials.2014.05.048](https://doi.org/10.1016/j.biomaterials.2014.05.048)
37. Miron RJ, Bosshardt DD (2016) OsteoMacs: key players around bone biomaterials. *Biomaterials* 82:1–19. doi:[10.1016/j.biomaterials.2015.12.017](https://doi.org/10.1016/j.biomaterials.2015.12.017)